

Jana Publication & Research

Systematic Review on Mycodegradation of Plastic

 VRC04

Document Details

Submission ID

trn:oid::2945:312989982

Submission Date

Sep 18, 2025, 11:18 AM GMT+5:30

Download Date

Sep 18, 2025, 11:22 AM GMT+5:30

File Name

IJAR-53886.pdf

File Size

2.7 MB

78 Pages

30,725 Words

157,263 Characters





13% Overall Similarity

The combined total of all matches, including overlapping sources, for each database.




Filtered from the Report

- Bibliography
- Quoted Text

Match Groups

-  **178** Not Cited or Quoted 8%
Matches with neither in-text citation nor quotation marks
-  **121** Missing Quotations 5%
Matches that are still very similar to source material
-  **0** Missing Citation 0%
Matches that have quotation marks, but no in-text citation
-  **0** Cited and Quoted 0%
Matches with in-text citation present, but no quotation marks

Top Sources

- 5%  Internet sources
- 10%  Publications
- 4%  Submitted works (Student Papers)

Match Groups

- 178** Not Cited or Quoted 8%
Matches with neither in-text citation nor quotation marks
- 121** Missing Quotations 5%
Matches that are still very similar to source material
- 0** Missing Citation 0%
Matches that have quotation marks, but no in-text citation
- 0** Cited and Quoted 0%
Matches with in-text citation present, but no quotation marks

Top Sources

- 5% Internet sources
- 10% Publications
- 4% Submitted works (Student Papers)

Top Sources

The sources with the highest number of matches within the submission. Overlapping sources will not be displayed.

- 1** Internet
link.springer.com <1%
- 2** Publication
Ken Suzuki, Hironori Sakamoto, Yukiko Shinozaki, Jun Tabata et al. "Affinity purifi... <1%
- 3** Internet
www.ncbi.nlm.nih.gov <1%
- 4** Internet
www.science.gov <1%
- 5** Internet
www.researchgate.net <1%
- 6** Publication
Dajana Kučić Grgić, Martina Miloloža, Vesna Ocelić Bulatović, Šime Ukić, Miroslav ... <1%
- 7** Internet
worldwidescience.org <1%
- 8** Publication
Brenda Hernández-Sánchez, Ericka Santacruz-Juárez, Francisco Figueroa-Martínez... <1%
- 9** Internet
sci-hub.ru <1%
- 10** Publication
Mariusz Wróbel, Sonia Szymańska, Tomasz Kowalkowski, Katarzyna Hryniewicz. ... <1%

11	Publication	Xiao-Ya Shang, Xiong Fu, Xu-Dong Chen, Lian-Sheng Yang. "Biodegradation of ble..."	<1%
12	Publication	Navid Taghavi, Naresh Singhal, Wei-Qin Zhuang, Saeid Baroutian. "Degradation o..."	<1%
13	Publication	Miriam Ahuactzin-Pérez, Saúl Tlecuil-Beristain, Jorge García-Dávila, Manuel Gonz...	<1%
14	Publication	R.K. Soni, Shweta Soam, Krishna Dutt. "Studies on biodegradability of copolymers..."	<1%
15	Publication	Parth Bhavsar, Mrinal Bhawe, Hayden K. Webb. "Effective multi-stage biodegradat..."	<1%
16	Publication	Saira Saeed, Atia Iqbal, Farah Deeba. "Biodegradation study of Polyethylene and ..."	<1%
17	Publication	Feiyan Wu, Zhi Guo, Kangping Cui, Dazhuang Dong, Xue Yang, Jie Li, Zhangzhen ...	<1%
18	Publication	Koitaishi, Motoo, Masako T Noguchi, Yuka Sameshima-Yamashita, Syuntaro Hir...	<1%
19	Student papers	Southampton Solent University on 2021-07-06	<1%
20	Internet	pure.manchester.ac.uk	<1%
21	Internet	neptjournal.com	<1%
22	Publication	Thainá Araújo de Oliveira, Renata Barbosa, Avilnete B.S. Mesquita, Josie H.L. Ferre...	<1%
23	Publication	Seung-Yeol Lee, Leonid N. Ten, Kallol Das, Young-Hyun You, Hee-Young Jung. "Bio..."	<1%
24	Publication	Shilpi Khurana, Sajid Ali, Atul Kumar Srivastava, Anuradha Singh et al. "Bioremedi..."	<1%

25	Publication	Mohd Ashraf Dar, Preksha Palsania, Shalni Satya, Milap Dashora et al. "Microplast...	<1%
26	Publication	Oleg Milstein, Rolf Gersonde, Aloys Huttermann, Meng-Jiu Chen, John J. Meister. "...	<1%
27	Internet	pmc.ncbi.nlm.nih.gov	<1%
28	Publication	Kawinship Wichatham, Pitchaya Piyaviriyakul, Narin Boontanon, Nawatch Surink...	<1%
29	Publication	Elena Parparita, Traian Zaharescu, Raluca N. Darie, Cornelia Vasile. "Biomass Effe...	<1%
30	Student papers	Florida International University on 2021-07-24	<1%
31	Publication	Shriniketan Puranik, Amanda Shylla, M. Manoj, D. Vijaysri. "Chapter 3 Current Pro...	<1%
32	Publication	Shun Sato, Azusa Saika, Yukiko Shinozaki, Takashi Watanabe et al. "Degradation ...	<1%
33	Student papers	University College for the Creative Arts at Canterbury, Epsom, Farnham, Maidsto...	<1%
34	Internet	pure.sruc.ac.uk	<1%
35	Internet	www.redalyc.org	<1%
36	Publication	Shriniketan Puranik, Livleen Shukla, Aditi Kundu, Deeba Kamil et al. "Exploring Po...	<1%
37	Publication	Al Hosni, Asma Said Khalid. "Biodegradation of Polycaprolactone Bioplastic in Co...	<1%
38	Publication	D. S. Rosa, M. A. G. Bardi, C. G. F. Guedes, D. A. Angelis. " Role of polyethylene-graf...	<1%

39	Publication	Sahebnazar Zahra, Shojaosadati Seyed Abbas, Mohammad-Taheri Mahsa, Nosrati...	<1%
40	Student papers	University of Warwick on 2021-09-08	<1%
41	Publication	V. Balasubramanian, K. Natarajan, V. Rajeshkannan, P. Perumal. "Enhancement o...	<1%
42	Publication	Swapan Kumar Ghosh, Sujoy Pal. "De-polymerization of LDPE plastic by Penicilliu...	<1%
43	Publication	A. Manzur, M. Limón-González, E. Favela-Torres. "Biodegradation of physicochemi...	<1%
44	Publication	Jie Zeng, Junruo Yao, Weiming Zhang, Miaomiao Zhang, Tan Wang, Xun Yu, Yongx...	<1%
45	Publication	Rui-Fang Xu, Saowaluck Tibpromma, Samantha C. Karunarathna, Kevin D. Hyde e...	<1%
46	Internet	fjps.springeropen.com	<1%
47	Internet	ueaeprints.uea.ac.uk	<1%
48	Publication	Babafemi Raphael Babaniyi, Sesan Abiodun Aransiola, Gabriel Gbenga Babaniyi, ...	<1%
49	Publication	Hiroko Kitamoto, Shigenobu Yoshida, Motoo Koitabashi, Kimiko Yamamoto-Tamu...	<1%
50	Student papers	University of Nebraska, Lincoln on 2024-04-16	<1%
51	Student papers	University of South Africa (UNISA) on 2024-07-07	<1%
52	Publication	Yan Zhang, Jacob Nedergaard Pedersen, Bekir Engin Eser, Zheng Guo. "Biodegrad...	<1%

53	Internet	www.mdpi.com	<1%
54	Publication	Butnaru, Elena, Raluca Nicoleta Darie-Niță, Traian Zaharescu, Tiberius Balaș, Căt...	<1%
55	Publication	Mohan K. R. Konduri. "Effect of pro-oxidants on biodegradation of polyethylene (L...	<1%
56	Publication	Rongrong Gao, Rui Liu, Chaomin Sun. "A marine fungus <i>Alternaria alternata</i> FB1 ...	<1%
57	Student papers	Universitas PGRI Adi Buana Surabaya on 2024-01-14	<1%
58	Internet	chembioagro.springeropen.com	<1%
59	Internet	www.udspub.com	<1%
60	Publication	Asma S. Al Hosni, Jon K. Pittman, Geoffrey D. Robson. "Microbial degradation of fo...	<1%
61	Publication	Hsiao-Lin Chien, Yi-Ting Tsai, Wei-Sung Tseng, Jin-An Wu, Shin-Liang Kuo, Sheng-L...	<1%
62	Publication	Mal-Nam Kim, Ae-Ri Lee, Jin-San Yoon, In-Joo Chin. "Biodegradation of poly(3-hydr...	<1%
63	Publication	Carmen Sánchez, Lorena Ferrer-Parra, Dolores Itzel López-Nicolás, Rocío Martíne...	<1%
64	Publication	Eman Abdullah M. Ali, Tahany M. A. Abdel-Rahman, Dalia M. I. Ali, Al-Shaimaa Hos...	<1%
65	Publication	José Maria Rodrigues da Luz, Sirlaine Albino Paes, Karla Veloso Gonçalves Ribeiro,...	<1%
66	Publication	Mewada, Mitu. "Municipal Solid Waste Characterization and Its Assessment for F...	<1%

67	Student papers	University of Sydney on 2023-10-20	<1%
68	Publication	Angel González-Márquez, Ariadna Denisse Andrade-Alvarado, Rosario González-M...	<1%
69	Publication	Cátia Venâncio, Paulo Cardoso, Anna Ekner-Grzyb, Jagna Chmielowska-Bąk, Toma...	<1%
70	Publication	Sadia Mehmood Satti, Ziaullah Shah, Aaisha Luqman, Fariha Hasan, Muhammad ...	<1%
71	Publication	Vieyra, Horacio, Eduardo San Martín-Martínez, Esmeralda Juárez, Ulises Figueroa-...	<1%
72	Publication	Nehala Sona Payanthoth, Nik Nurhidayu Nik Mut, Palas Samanta, Guanlin Li, Jinh...	<1%
73	Publication	Saeed Hanifi, Abdulrasoul Oromiehie, Shervin Ahmadi, Hassan Farhadnejad. "(Cor...	<1%
74	Publication	Sánchez Carmen. "Microbial capability for the degradation of chemical additives ...	<1%
75	Publication	Vincent Tournier, Sophie Duquesne, Frédérique Guillaumot, Henri Cramail, Daniel ...	<1%
76	Publication	Zhenyan Lin, Tuo Jin, Xin Xu, Xiao Yin et al. "Screening and degradation characteri...	<1%
77	Student papers	Chandigarh Group of Colleges on 2023-11-30	<1%
78	Publication	Fuad Ameen, Mohammad J. Alsarraf, Tarad Abalkhail, Steven L. Stephenson. "Eval...	<1%
79	Publication	Klun, U.. "Polyamide-6 fibre degradation by a lignolytic fungus", Polymer Degrad...	<1%
80	Publication	Sanjana Sridhar, Nivetha Murugesan, Mohan Gopalakrishnan, Dao Janjoren, Suna...	<1%

81	Publication	Sarunpron Khruengsai, Teerapong Sripahco, Patcharee Pripdeevech. "Low-Densit...	<1%
82	Student papers	University of the Western Cape on 2025-08-25	<1%
83	Internet	microbiologyjournal.org	<1%
84	Internet	worldresearchersassociations.com	<1%
85	Publication	"Sustainable Microbial Technology for Synthetic and Cellulosic Microfiber Biorem...	<1%
86	Publication	Kong-Yang Wu, Tong-Xiang Yang, Meng Yang, Jin-Qiu Wu, Xue Li, Xue-Dong Chen,...	<1%
87	Publication	Manal T. El-Sayed, Gamal H. Rabie, Esraa A. Hamed. "Biodegradation of low-densit...	<1%
88	Publication	Ming Hung Wong. "Ecological and Human Health Impacts of Contaminated Food ...	<1%
89	Publication	Natalia N. Pozdnyakova, Tatiana S. Babicheva, Daria S. Chernova, Irina Yu. Sungu...	<1%
90	Student papers	National University of Ireland, Maynooth on 2023-12-20	<1%
91	Publication	Sarunpron Khruengsai, Teerapong Sripahco, Patcharee Pripdeevech. "Biodegrada...	<1%
92	Publication	Shilpa, Nitai Basak, Sumer Singh Meena. "Microbial biodegradation of plastics: Ch...	<1%
93	Student papers	Victoria Point State High School on 2020-08-15	<1%
94	Internet	cjb.ijournals.cn	<1%

95	Internet	www.frontiersin.org	<1%
96	Publication	André L. Catto, Larissa S. Montagna, Scheyla H. Almeida, Rosa M.B. Silveira, Ruth ...	<1%
97	Publication	Bo Ram Kang, Soo Bin Kim, Hyun A Song, Tae Kwon Lee. "Accelerating the Biodeg...	<1%
98	Publication	Daniela Dal Castel Krein, Flavia Melara, Jeferson Stefanello Piccin, Aline Dettmer. ...	<1%
99	Publication	Elena Efremenko, Nikolay Stepanov, Olga Senko, Aysel Aslanli, Olga Maslova, Ilya ...	<1%
100	Publication	Maria Fernanda Rodríguez-Fonseca, Jeysson Sánchez-Suárez, Manuel Fernando V...	<1%
101	Publication	Mehran Babaee, Mehdi Jonoobi, Yahya Hamzeh, Alireza Ashori. "Biodegradability ...	<1%
102	Student papers	Mueller College on 2024-08-05	<1%
103	Publication	Samaneh Hadian-Ghazvini, Fahimeh Hooriabad Saboor, Leila Safaee Ardekani. "C...	<1%
104	Publication	Sartaj Ahmad Bhat, Vineet Kumar, Fusheng Li, Fuad Ameen, Sunil Kumar. "Enviro...	<1%
105	Publication	Shraddha Awasthi, Neha Srivastava, Tripti Singh, D. Tiwary, Pradeep Kumar Mishr...	<1%
106	Publication	Tadahiro Ohmi. "Ultraclean Technology Handbook - Ultrapure Water", CRC Press, ...	<1%
107	Student papers	The University of the South Pacific on 2019-04-07	<1%
108	Student papers	Universiteit Utrecht on 2025-01-30	<1%

109	Student papers	University of Cape Town on 2014-05-05	<1%
110	Publication	Wolfgang Zimmermann. "Degradation of Plastics by Fungi", Elsevier BV, 2021	<1%
111	Publication	Xinran Qiu, Zhiping Qi, Zhuozhi Ouyang, Peng Liu, Xuetao Guo. "Interactions bet...	<1%
112	Publication	Zhu Gong, Long Jin, Xingye Yu, Baoteng Wang, Shuang Hu, Honghua Ruan, Yun-Ju...	<1%
113	Internet	agris.fao.org	<1%
114	Internet	bibliotecadigital.udea.edu.co	<1%
115	Internet	bmcgenomics.biomedcentral.com	<1%
116	Internet	bradscholars.brad.ac.uk	<1%
117	Internet	ito01.gs.niigata-u.ac.jp	<1%
118	Internet	ogma.newcastle.edu.au	<1%
119	Internet	plasticdb.org	<1%
120	Publication	"Impact of Plastic Waste on the Marine Biota", Springer Science and Business Me...	<1%
121	Publication	"Microplastics in the Ecosphere", Wiley, 2023	<1%
122	Publication	"Pollutants and Recent Trends in Wastewater Treatment", Springer Science and B...	<1%

123	Publication	Aneta K. Urbanek, Waldemar Rymowicz, Mateusz C. Strzelecki, Waldemar Kociuba...	<1%
124	Student papers	Asian Institute of Technology on 2024-10-27	<1%
125	Publication	Avinash Sharma, Vadakkumcheri Akathoottu Subrahmanian Nampoothiri Devad...	<1%
126	Publication	Ayesha Baig, Muhammad Zubair, Muhammad Nadeem Zafar, Mujahid Farid, Muh...	<1%
127	Student papers	Bath Spa University College on 2019-05-17	<1%
128	Student papers	Birkbeck College on 2025-04-28	<1%
129	Publication	Chioma Odigbo, Clementina Adenipekun, Ibrahim Oladosu, Adeniyi Ogunjobi. "Po...	<1%
130	Publication	Deependra Singh, Durgesh Nandini Chauhan, Nagendra Singh Chauhan, Manju R...	<1%
131	Publication	Glória Maria Vinhas, Suzana Moreira de Lima, Lívia Almeida Santos, Maria Alice G...	<1%
132	Publication	Haruna Adamu, Usman Bello, Usman IbrahimTafida, Zaharaddeen N. Garba et al. ...	<1%
133	Student papers	Higher Education Commission Pakistan on 2012-10-10	<1%
134	Publication	José Maria Rodrigues da Luz, Sirlaine Albino Paes, Mateus Dias Nunes, Marliane d...	<1%
135	Publication	M. Arefian, M. Zia, A. Tahmourespour, M. Bayat. "Polycarbonate biodegradation b...	<1%
136	Publication	Michel Chaves, Maria Lima, Lusiane Malafatti-Picca, Derlene de Angelis, Aline de ...	<1%

137	Publication	Muhammad Aitzaz Akram, Rangasamy Savitha, Gemma K. Kinsella, Kieran Nolan, ...	<1%
138	Student papers	Northeastern Illinois University on 2021-10-08	<1%
139	Publication	O. O. Oladipo, H. A. Oyewusi. "Mycoremediation: An Insight to Cleanup of Polluta...	<1%
140	Student papers	Oregon State University on 2023-12-08	<1%
141	Publication	Parisa Ebrahimbabaie, Kimiya Yousefi, John Pichtel. "Photocatalytic and biological...	<1%
142	Student papers	Queen Mary and Westfield College on 2014-12-15	<1%
143	Student papers	Queensland University of Technology on 2021-11-08	<1%
144	Student papers	RMIT University on 2023-06-08	<1%
145	Student papers	Universiti Teknologi Malaysia on 2022-03-14	<1%
146	Student papers	University of Derby on 2024-04-30	<1%
147	Student papers	University of Durham on 2021-01-22	<1%
148	Student papers	University of East London on 2025-04-02	<1%
149	Publication	Vaishali Dhaka, Simranjeet Singh, Amith G. Anil, T. S. Sunil Kumar Naik et al. "Occ...	<1%
150	Publication	Wei-Sung Tseng, Min-Jia Lee, Jin-An Wu, Shin-Liang Kuo, Sheng-Lung Chang, Shu-J...	<1%

151	Publication	Y.J. Phua, N.S. Lau, K. Sudesh, W.S. Chow, Z.A. Mohd Ishak. "Biodegradability studi...	<1%
152	Publication	Yukiko Shinozaki, Tomotake Morita, Xiao-hong Cao, Shigenobu Yoshida et al. "Bio...	<1%
153	Internet	assets-eu.researchsquare.com	<1%
154	Internet	bbrc.in	<1%
155	Internet	bilselkongreleri.com	<1%
156	Internet	journal.hep.com.cn	<1%
157	Internet	openarchive.usn.no	<1%
158	Internet	opus.lib.uts.edu.au	<1%
159	Internet	prr.hec.gov.pk	<1%
160	Internet	vdoc.pub	<1%
161	Internet	www.sciencegate.app	<1%
162	Publication	"Approaches in Bioremediation", Springer Science and Business Media LLC, 2018	<1%
163	Publication	B. Sasikumar, Santhosh J. Eapen. "Spices Production to Products - Purity and Auth...	<1%
164	Student papers	Chulalongkorn University on 2025-01-16	<1%

165	Publication	S. Lladó, S. Covino, A.M. Solanas, M. Viñas, M. Petruccioli, A. D'annibale. "Compara...	<1%
166	Publication	Tamer Elsamahy, Jianzhong Sun, Sobhy E. Elsilk, Sameh S. Ali. "Biodegradation of I...	<1%
167	Student papers	University of Sheffield on 2017-10-08	<1%
168	Student papers	University of Sydney on 2023-07-02	<1%
169	Student papers	Institute of Technology, Sligo on 2022-10-04	<1%
170	Student papers	Queen's University of Belfast on 2018-04-10	<1%
171	Publication	Rachel Porter, Anja Černoša, Paola Fernández-Sanmartín, Antonio Martínez Cortiz...	<1%
172	Publication	Rui Zhuo, Fangfang Fan. "A comprehensive insight into the application of white r...	<1%
173	Publication	Swarup Roy, Tabli Ghosh, Wanli Zhang, Jong-Whan Rhim. "Recent progress in PBA...	<1%
174	Publication	Swati Solanki, Surbhi Sinha, Rachana Singh. "Myco-degradation of microplastics: ...	<1%

Systematic Review on Mycodegradation of Plastic

Abstract

Since plastic is versatile, durable, and easy to make, this material has widely been applied in almost every sector. Unfortunately, the big exertion of this material on the environment led to pollution, which is a world green disaster. Scientists have found that many living organisms, especially bacteria and fungi, can degrade many plastic polymers. In doing so, this paper shall be poised to highlight the possibility of fungi as a feasible approach to managing plastic waste, an environmentally conscious means. The research scope will extend to publications that have been made on plastic degradation for 30 years; and papers have been chosen for this analysis. The review explores three crucial aspects of the relationship between fungal species and plastic degradation, specifically: the diversity of the identified fungal species in specific plastic degradation, place of isolation, and the methods applied to analyze the plastic degradation of fungi.

Keywords: plastic, fungi, degradation, weight loss, SEM, FTIR, CO₂.

Highlights

- Plastic pollution and its environmental impact
- The potential of fungi as a viable, eco-friendly method for degrading plastic waste.
- Analysis of 30 years of scientific publications of fungal involvement in plastic degradation.
- Diversity of fungal species is involved in plastic degradation with place of isolation.
- Analytical methods used to study the degradation process.

Introduction

Plastic has been widely utilized because of its exceptional physical characteristics, such as its versatility, pliability, chemical and physical durability, and simplicity of manufacturing in comparison to alternative materials (Khruengsai et al., 2022). It contributes to managing population surges and promoting economic prosperity for human beings. The durability of plastics makes them suitable for use in disposable products (Kim et al., 1994). It is employed in several industries such as refrigeration insulation, packaging, electronics, aircraft, building, and construction (Khan et al., 2017). Plastic materials are used in many fields, which leads to the significant amounts of plastics waste. Plastic waste formation is a serious issue worldwide without an effective solution, threatening ecosystems and human health (P. Perera et al., 2023). Microplastics (MPs) are fine plastic particles which have recently surfaced as another major area of concern in environmental research. (Bernat et al., 2023). The present level of plastic pollution is alarming, and thus innovative and lasting methods need to be put into practice to reduce plastic waste.

Various methods for plastic degradation are in work by scientists across the globe. Biodegradation is the chemical or organic degradation of chemicals and substrates in the presence of a living entity. The scientists are now overcoming this challenge by applying various micro-organisms like bacteria, fungus, actinomycetes, or cyanobacteria either alone or in combinations with each other or as biofilm (Vimal Kumar et al., 2017). The soluble products of biodegradation are absorbed or assimilated by enzymes or other compounds secreted by microorganisms (Zeghal et al., 2021). Besides secreting degrading enzymes like cutinase, lipase, and protease, which constitute a part of lignocellulolytic enzymes, fungi also enhance the rate of plastic biodegradation by accelerating it with the help of pro-oxidant ions. This enzymatic activity breaks them into various functional groups and consequently let their degradation into low molecular weight oligomers (Napoli et al., 2023). This capability is ascribed to their enzymatic activities, which has developed to break down intricate organic substrates. Recently, numerous scientific studies have shown that different types of fungi can break down plastics, providing a promising solution to the problem of plastic pollution.

Hence, in the very first systematic review of this kind, we undertook a comprehensive overview of plastic degradation by fungi. The rationale behind this study is to make an overall assessment of all the current knowledge on the topic of fungal decomposition of plastic. Our purpose for investigating all literature so far available is to show the possibility of fungi as a sustainable and eco-friendly manner in managing plastic waste, contributing towards the broader discourse on environmental conservation and the circular economy. In this comprehensive review, we dig into three crucial sides of the remarkable interaction between fungal species and plastic degradation. Initially, we compiled the remarkable range of fungal species that have been recognized as crucial participants in the breakdown of different kinds of plastics. We have also studied a wide range of plastics that have been selected in particular for their degradation. A list of some of the most used substances comes under this category: polyethylene, polypropylene, polystyrene, and others. The successful degradation of such plastics by fungi could perhaps be the answer to the global plastic pollution crisis. Finally, we discuss the methods applied for the assessment of plastic biodegradation by fungi, which include laboratory experiments that explain the mechanisms of degradation, field studies oriented at evaluating feasibility in realistic conditions, and

environmental applications where fungi are applied for plastic biodegradation. Together, they form a complete view of the promising realm of plastic biodegradation through fungi.

Methodology:

To write a systematic review on plastic degradation by fungi, we used a well-known database 'SCOPUS'. With its strategic feature, we searched different combination of keywords related to our topic of interest to make a script. Among the nine scripts, we selected the following script which showed the largest number of publications. By the following script we could successfully get 680 research articles in the SCOPUS database until the date of March 4, 2024. Abstracts of all articles were screened for systematic review. Among which 355 papers were excluded in view of not meeting the criteria for inclusion. So, the total text of 325 papers was analyzed to evaluate the whole article. 120 were excluded as they had no focus on fungal plastic degradation, nor plastic degradation in general. Instead, the studies mainly focused on the degradation of polyaromatic hydrocarbons (PAHs), pesticides and dyes, or undertook a general review of plastic degradation. Finally, 205 papers were closely considered for this systematic review(Fig. 1).

Script:

```
TITLE-ABS-KEY ( ( ( plastic OR polythene OR polyethylene OR ldpe OR hdpe ) AND (
degradationOR degrading OR mycodegradation ) AND ( fungi OR fungus OR fungal ) ) )
AND ( LIMIT-TO (SRCTYPE , &quot;j&quot; ) ) AND ( LIMIT-TO ( DOCTYPE ,
&quot;ar&quot; ) )
```

```
AND ( LIMIT-TO ( LANGUAGE , &quot;English&quot; ) )
```

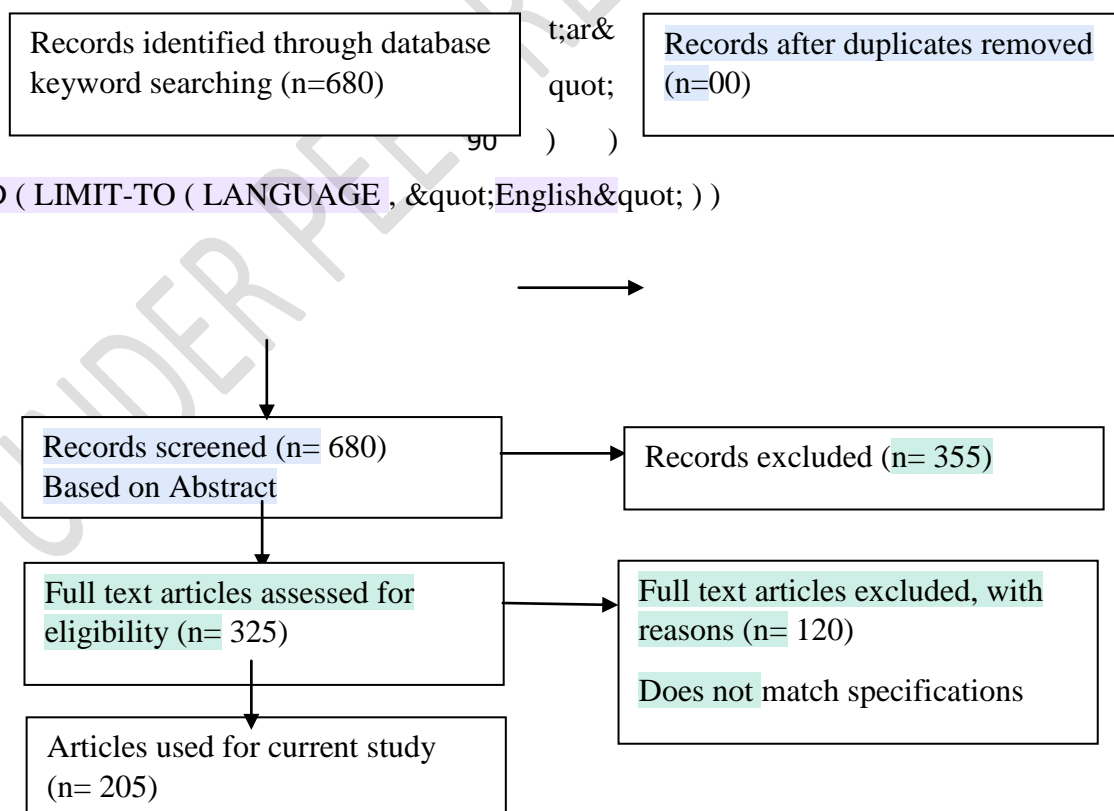


Fig. 1. Flow chart of data collection and analysis

Results and Discussion

After gathering and processing all the data, observations were categorized based on the kind of plastic degraded by fungi.

Polyethylene (PE)

Degradation of PE was observed to be up to 140 days by an adapted strain of *Aspergillus niger*. The characterizations were carried out using Differential Scanning Calorimetry (DSC) and Fourier Transform Infrared Spectroscopy (FTIR). In the FTIR analysis, the bio-treated PE sheet exhibited the presence of double bonds, which were detected by using absorbance at 1640 cm^{-1} and 940 cm^{-1} . Whereas in abiotically treated PE sheets, the ketonic carbonyl group was associated with an absorption band observed at a wavenumber of 1715 cm^{-1} (Raghavan & Torma, 1992). Interestingly, the lignin-degrading fungus IZU-154 showed a significant decrease of 73% in tensile strength within a span of only 12 days (Iiyoshi et al., 1998). Within a one-month period, *A. glaucus*, was able to break down 28.80% of polythene bags and 7.26% of plastic cups which was isolated from mangrove soil (Kathiresan, 2003). In 30 days, polythene bags ranging in thickness from 0.5 to 5 mm were broken down by the *A. oryzae* that was isolated from the soil. Weight reduction served as confirmation of it (Kannahi & Rubini, 2012). Plastic cups and polythene bags were tested in Mangrove soil (M), Petroleum soil (P), and Molasses soil (MS) as well as in Lab (L) for 9 months. The recorded weight loss for *A. niger* was L – 13.25, M – 15.5, P – 4.62, MS – 3.37 for plastic cups, and L – 14.75, M – 10.75, P – 6.75, MS – 3.25 for polythene bags. Also, L – 17.25, M – 12, P – 3.5, MS – 2.25 for plastic cups and L – 16, M – 11, P – 6.37, MS – 2.25 for polythene bags by *A. glaucus*. SEM analysis observed the physical alterations of the surface, and the degradation was confirmed (Sugana Rani & Prasada Rao, 2012).

Pleurotus ostreatus PLO6 brought from Laboratory of Mycorrhizal Associations/DMB/BI OAGROU/FV degraded oxo-biodegradable plastic bags in 45 days. The confirmation was done by X-Ray Diffraction (XRD), scanning electron microscopy (SEM), FTIR and enzymatic assay (da Luz et al., 2013). *P. ostreatus* PLO6 collected from the Department of Microbiology degraded oxo-biodegradable polyethylene in 90 days. The confirmatory tests were SEM, FTIR, mechanical properties, and CO_2 measurement (Da Luz et al., 2014). *Curvularia lunata*, *Alternaria alternata*, *Penicillium simplicissimum*, and *Fusarium* sp. were isolated in a garbage site. Each of these fungi showed a decrease in weight of 1.2, 0.8, 7.7, and 0.7% respectively. However, when all of them were combined as a consortium, they experienced a weight loss of 27% after being kept for three months (Sowmya et al., 2015). *P. simplicissimum* from a dumpsite exhibited a diverse degradation rate for each treatment. Compared to autoclaved (16%) and surface-sterilized (7.7%) polyethylene, the treated PE (38%) exhibited a rapid weight reduction over a three-month period. Further confirmation was provided by nuclear magnetic resonance (NMR), SEM, FTIR and analysis (Sowmya, Ramalingappa, Krishnappa, et al., 2015).

The marine fungus, *Zalerionmaritimum* isolated from its soil, successfully decomposed microplastic (MP) span of only 28 days. This degradation was tested and verified with Attenuated Total Reflectance-Fourier transform infrared (ATR-FTIR) and NMR (Paço et al., 2017). *Candida sp.* consumed a polythene bag of 20 Grams per Square Meter (GSM) with a weight loss of 2.3 percent, while *Aspergillus sp.* isolated from landfill soil degraded a polythene bag of 40 GSM with a weight loss of 6%. FTIR verified the change in condition (Ratna Kumari & Kulkarni, 2018). *Avicenniamarina's* rhizosphere contained *A.sydowii* strain PNPf15/TS which reduced 94.4±42.40% tensile strength and *A.terreus* strain MANGF1/WL reduced 50% of weight in 60 days. This decomposition was evidenced by SEM and FTIR (Sangale et al., 2019). Additional sources of *A. niger*, *A. flavus*, and unidentified fungi have been found to include cooking oil, grease, and petroleum products. The black polyethylene exhibited degradation by weight at the rates of 38, 27, and 64%, while the white polyethylene showed degradation at rates of 26, 16, and 45%, respectively. SEM visuals confirmed the breakage of plastic surface (Padmanabhan et al., 2019). *Aspergillus strain* MH119104.1 was isolated from marine water and showed that around 22% of the plastic bottle strip decomposed within a period of 6 weeks. FTIR, SEM and XRD were used to verify degradation (Sarkhel et al., 2020). The degradation percentage of weight of PE in liquid media (L) by *A. niger* (NG_065763.1) and *A. glaucus* (NG_063391.1) during a period of 28 days was 40±3.3 and 25±3.3%, respectively. Whereas the rate of degradation in soil (S) was as low as 12±3 and 15±3% (Saeed et al., 2022). *A.alternata* FB1, isolated from marine sediment, efficiently degraded commercial PE bags, including additive-containing (type ET3113, 0.25 mm thick) and additive-free (type ET3111, 0.025 mm thick) plastics in 120 days. The degradation was confirmed by gel permeation chromatography (GPC), gas chromatography-mass spectroscopy (GC-MS), FTIR, XRD and SEM analyses (Gao et al., 2022).

Zone formation was observed in plastic-rich Mineral Salt Media (MSM) plates among the following species: *A. terreus* (F4), *A. terreus* (F5), *Talaromyces islandicus* (F6), *A. terreus* (F8), *Aspergillus sp.* (F7), *Phoma sp.* (F2), *Eupenicillium rubidurum* (F1), and *Neosartorya fischeri* (F3) from different soils of Morogoro, Tanzania. After 13 days, the visibility zone varied between 30 and 66.3 mm of all the organisms tested, *Aspergillus sp.* (F7) had the best performance in breaking down PE bags (Nakei et al., 2022). *A. flavus* found in the Gut of *Galleria mellonella* larvae, degraded PE when the larvae fed on PE of freezer, garbage, and shopping bags. The consumed PE were scanned with SEM and Atomic Force Microscopy (AFM) for confirmation of the degradation (Riabi et al., 2023). From soil that had been contaminated with plastic, *Trichoderma harzianum* was isolated and treated with PE, and showed 3.39 ± 0.3% weight loss after 30 days. This consumption was supported by SEM, FTIR and GC-MS analysis (Ruan et al., 2023). Several microorganisms were identified from the municipal waste disposal site and were found to degrade the PE in 90 days. These included *Fusarium solani* (OL919442, OL919446), *F. oxysporum* (OL91944, 3OL919445), *Lecanicillium maraneicola* (OL919438, OL919441), and *T. lixii* (OL919447). The SEM analysis showed presence of fungal shreds of varying lengths on the external surface of granules, confirmed the micro-damage. The degradation studies are also supported by FTIR (Wróbel et al., 2023) (Table No. 1).

Low Density Polyethylene (LDPE)

Prior to being subjected to biodegradation, plastic sheets were photo-oxidized for 0 to 100 hours. *A. niger* was procured from the National Chemical Laboratory (NCL), India, successfully decomposed the pre-treated LDPE in compost for over a period of 6 months, resulting in a weight reduction of 22% whereas, the untreated LDPE film was degraded less than 15%. The degradation was confirmed using Variation in Viscosity, Chain Scission, FTIR and SEM (Pandey & Singh, 2001). Thermally oxidized LDPE was decomposed in a period of 31 months in a culture of *A. niger* and *P. pinophilum* and verified by DSC, SEM, FTIR and XRD (Volke-Seplveda et al., 2002). The consortium of *A. niger* (ATCC 9642,7), *Gliocladium virens* (ATCC 9645,9), *P. pinophilum* (ATCC 11,797,7), and *Phanerochaete chrysosporium* (H2896) efficiently breakdown the physico-chemically pretreated LDPE within a period of 9 months. Wide angle X-ray scattering (WAXS), Gas Chromatography (GC), DSC, FTIR, and SEM were used for verification (Manzur et al., 2004). *A. niger* and *P. funiculosum* were extracted from the waste, modified with 60% (wt/wt) Bionolle within a period of 90 days. *P. funiculosum* completely degraded LDPE whereas *A. niger* exhibited a weight reduction of 7.53%. It showed tensile strength of 17.9 ± 0.6 MPa and further studied by SEM and FTIR (Labuzek et al., 2004). *Fusarium sp.* AF4 isolated from soil has been degraded LDPE in 3 months which was confirmed by FTIR (Shah et al., 2008). *A. fumigatus*, *A. terreus*, and *F. solani*, which were obtained from solid waste, decomposed LDPE over a period of 100 days. Molecular weight changes of polyethylene were measured by high-temperature gel-permeation chromatography (HT-GPC). And further it was verified using FTIR and SEM (Zahra et al., 2010). *P. Chrysosporium* and *T. Wortmannii* obtained from culture collection at the Federal University of Brazil degraded LDPE/modified starch in 90 days, which were examined by XRD, SEM, and FTIR (Ferreira et al., 2010).

The most significant decrease in both elongation percentage (62%) and tensile strength (51%) was observed in the pro-oxidant manganese stearate (MnS) treated with *A. oryzae* with weight loss of 47.2%. This treatment involved UV irradiation and incubation in soil for a period of 3 months. In comparison, other pro-oxidant treated LDPE films showed elongation percentage, loss of tensile strength and weight [45, 45, 41.6% for titanium stearate (TiS)], [43, 40 and 36.1% for iron stearate (FeS)], and [41, 39 and 34% for cobalt stearate (CoS)]. LDPE treated with UV irradiation and *A. oryzae* showed 18, 21 and 24% weight loss, tensile strength and elongation percentage; whereas LDPE incubated with only *A. oryzae* (UT) showed 5, 26 and 3% respectively (Konduri et al., 2011). In a study conducted by (Nowak et al., 2011) LDPE that had been modified with bionolle was immersed in waste coal, a forest and an extinct volcano crater over a period of 225 days. *A. awamori*, *Mortierella subtilissima*, and *G. viride* were identified on the buried plastic film. The weight loss for films 0 (pure LDPE), 1 (modified), and 2 (polyester) was 0.26, 0.25, and 5.76% in waste coal; 0.13, 0.52 and 2.02% in forest and 0.28, 0.26 and 17.03% in soil, respectively. The tensile strength measurements for film 0 and film 1 obtained from waste coal were 13.7 and 6.7 MPa, forest 13.7 and 6.9 MPa and crater 13.2 and 7.3 MPa, respectively. Film 2 was determined to be the most delicate among all the sites because of elongation at break of 98%. The findings were further supported by SEM and FTIR.

A. niger along with five other species of the same genus, as well as two species of *Fusarium* found in municipal solid waste were able to adhere on the surface of LDPE film and to grow in the synthetic medium supplemented with 0.1% LDPE as they utilized it as a sole carbon and energy source. The fungal strains caused considerable degradation of LDPE within a 30-day period. (Kumar et al., 2013). *T. harzianum* isolated from soil of dumpsite degraded UV- treated, autoclaved and surface- sterilize LDPE with 40, 23 and 13% by weight in 15 days respectively. The confirmatory tests were SEM, FTIR and NMR (Sowmya et al., 2014). *Aspergillus sp.* F1- 16S isolated from soil of municipal landfill site degraded LDPE 20 µm films (25 days UV pre- treated) and powdered plastic in 56 days. The confirmatory tests were SEM, FTIR and XRD (Esmaeili et al., 2014). After 30-day incubation period, *Saccharomyces sp.*, *A. niger*, *A. flavus*, and *Streptomyces sp.* exhibited weight reductions of 43%, 72%, 11%, and 40%, respectively. Furthermore, *A. niger* exhibited a respiration and breakdown process, as evidenced by the production of 4.2 g/L of CO₂ just in a week (Muthumani & Anbuselvi, 2014). Strains of *Aspergillus sp.* and *Fusarium sp.* were isolated from municipal solid waste. Amongst them, FSM-3, FSM-5, FSM-6, FSM-8 and FSM-10 were found to be degrading LDPE with weight loss of 8, 5, 7, 7 and 9% and CO₂ evolution of 20.26, 18.47, 17.93, 17.84 and 19.38 g/L respectively. Further confirmation was added by testing change in pH, SEM and FTIR (Das & Kumar, 2014). LDPE and sago starch filled LDPE (70/30) was degraded by *A. niger* in 30 days with recorded weight loss of 0.09 and 6.52% respectively. It was additionally confirmed by SEM (Beg et al., 2015). *Lasiodiplodia theobromae* isolated from *Psychotria flavida*, *Aspergillus sp.*, and *Paecilomyces lilacinus* isolated from *Humboldtia brunonis* has degraded LDPE (20 µm) in 90 days as confirmed by the FTIR, DSC, SEM and changes in viscosity tests (Sheik et al., 2015). *P. ostreatus* PLO6 procured from collection of the Department of Microbiology of the Federal University of Viçosa, MG, Brazil degraded LDPE with 50% green polymer plastic in 90 days. The confirmatory tests were tensile strength, CO₂ evolution, SEM and FTIR (Da Luz et al., 2015). Within a span of 90 days, two distinct microorganisms, namely *A. niger* JAPE1 and *Streptomyces sp.* AJ1, effectively decomposed LDPE which were isolated from waste disposal site. The study showed that the weight losses of by fungi were 4.9% and 5.2% respectively. Additionally, the rate of CO₂ evolution was recorded as 2.85 and 4.27 g/L after 4 weeks of incubation (Gajendiran et al., 2016a). *A. clavatus* JASK1 (KT148627) reduced the weight of LDPE by 35% within a span of only 90 days. The degradation also confirmed by the CO₂ evolution after 4 weeks at the rate of 2.32 g/L (Gajendiran et al., 2016b). In 90 days, *Chamaeleomyces viridis*, which was isolated from the dumping site soil, consumed LDPE, causing a weight loss of 14.8%, which was further verified by SEM, AFM and FTIR (Gajendiran et al., 2016c). The study conducted by (Awasthi et al., 2017) demonstrated that *Rhizopus oryzae* NS5 (KT160362) have the ability to break down thermally (hot air oven at 70°C for 10 days) pretreated LDPE. The tensile strength had a 60% decrease within a month, whereas the weight fell by 8.43%. SEM, FTIR, and AFM techniques were used to further validate the findings.

Two *Penicillium* species are isolated from a plastic landfill, *P. oxalicum* NS4 (KU559906) and *P. chrysogenum* NS10 (KU559907), wiped out LDPE within 90 days. For each fungus, weight degradation of 36.60 and 34.35% was observed. AFM, FTIR and Field Emission Scanning Electron Microscopy (FESEM) were used for further confirmation (Ojha et

al., 2017). *A. oryzae* strain A5, 1 (MG779508) was discovered in a dumpsite and has been found to decompose approximately $36.4 \pm 5.53\%$ of plastic by weight within a 16-week period. It was further tested and confirmed with FTIR, GC-MS (Muhonja et al., 2018). To obtain plastic degrading fungus, plastic bags were buried in soil for a duration of six months. *A. oryzae* was identified as a plastic degrading organism. It was further used to degrade green LDPE. Weight losses of 25 and 32.5% were observed in potato dextrose broth (PDB) and Czapek dextrose broth (CDB) for surface-sterilized plastic sheet, whereas pre-treated plastic sheet with palmitic acid showed decreased in weight by 30 and 40% respectively after 90 days (Jayaprakash & Palempalli, 2018). Gómez-Méndez et al., (2018) implemented chemical, physical, biological and combined treatments. Among them *P. ostreatus* pretreated with glow discharge plasma degraded LDPE in 150 days and noted that fungus colonized 88.72 %. The degradation was also confirmed by SEM and FTIR (Gómez-Méndez et al., 2018) (Gómez-Méndez et al., 2018). *A. flavus* and *A. versicolor*, as well as *F. solani*, were obtained from a municipal garbage yard in Chennai, India. They exhibited the capacity to decompose LDPE during a span of 60 days. They achieved a reduction in plastic weight of 17, 19, and 13% respectively. The levels of CO₂ evolution were correspondingly 20.8, 20.98, and 19.22 g/L. Additional confirmation was obtained using FTIR and FESEM (Das et al., 2018). *Mucor circinelloides* (MTCC No. 3945) significantly reduced LDPE weight by $1.328 \pm 0.27\%$ without pre-treatment after 45 days, whereas thermally pre-treated samples lost weight by 0.770333%. FTIR added further confirmation (Sharma et al., 2019). In 11 weeks, *A. terreus* and *A. niger* that were isolated from the soil on the Santay Island mangrove, broke down LDPE of 100 μm , resulting in a 22.4 and 35.3 % weight loss that was verified by SEM (Sáenz et al., 2019a).

A. flavus and *A. terreus* isolated from soil, when exposed to LDPE, caused its degradation within 4 months in a laboratory condition and 9 months in soil. The weight loss of plastic by *A. flavus* and *A. terreus* in soil were measured to be 30.6 and 11.4%, respectively. In media, 14.3% for *A. flavus* and 13.1% for *A. terreus* (Verma & Gupta, 2019). After a period of 77 days, *A. terreus* and *A. niger*, which were obtained from mangrove, degraded LDPE by 35.3% and 22.14% in terms of weight, respectively. The study was supported by SEM (Sáenz et al., 2019b). *T. hamatum* FR87271, obtained from a plastic-contaminated environment, decomposed virgin, UV/T60 and γ T150-pretreated LDPE by $0.5 \pm 0.4\%$, $1.3 \pm 0.4\%$ and $0.9 \pm 0.1\%$ during a span of 7 days, respectively. The experiment was facilitated by the use of FTIR, Thermogravimetric Analysis (TGA), GPC, and SEM techniques (Malachová et al., 2020). The black untreated LDPE (U-LDPE) degrading fungus *A. carbonarius* MH 856457.1 and *A. fumigatus* MF 276893, isolated from landfills, exhibited degradation rates of 3.8 and 2.267%, respectively over a period of 16 weeks. However, when these fungi were cultured together, the degradation rate increased to 5.01%. The percentage of degradation was 39.1 after subjecting the plastic sheets to thermal pretreatment (80 °C for 30 days, T-LDPE). The application of chemical treatment with 65% HNO₃ (C-LDPE) led to a degradation of 17.76%. Gamma radiation (22 KGy, γ -LDPE) showed the least degradation (5.79%) as determined using mixed culture analysis (El-Sayed et al., 2021). Khruengsai et al., (2021) obtained the strains viz., *Diaporthe italiana*, *Thyrostromajaczevskii*, *Collectotrichum fructicola* and *Stagonosporopsis citrullicola*, from the Institute of Excellence in Fungal Research, Mae Fah Luang University, Thailand and *A. niger* ATCC 10254 as reference

31 fungal strain acquired from Thailand Institute of Scientific and Technological Research, Bangkok, Thailand. Over a span of 90 days, they observed decline in tensile strength of 1.56, 1.78, 0.43, 1.86, and 3.34%, respectively. Additionally, there was a corresponding weight loss in LDPE of 43.90, 46.34, 48.78, 45.12, and 28.78%. The measurement of CO₂ evolution ranged from 0.45 to 1.45, 0.36 to 1.22, 0.45 to 1.45, 0.33 to 1.26, and 0.37 to 1.27 g/l. Five different fungal strains were isolated from soil at a disposal site, in which *Fusarium spp.*, *A. fumigatus* and *Penicillium spp.* degraded LDPE in 40 days with weight loss of 7.08±0.05, 21.88±0.03 and 19.17±0.02 % respectively. The biodegradation was also confirmed through SEM-EDAX and FTIR (Lakshmi & Selvi, 2021). The production of laccase enzyme using bio efficacy assay confirmed the degradation of LDPE by *T. viride* in 5 days (Johnnie et al., 2021).

1 Within a span of 30 days, *Thermomyces lanuginosus* (NCIM 1394) procured from NCL, effectively degraded LDPE (9.21±0.84% weight loss) that had been subjected to UV radiation (15 W and 50 Hz), high temperatures (100 °C), and chemical treatment (69% nitric acid) each for 7 days. The confirmation was also obtained by SEM and FTIR (Chaudhary et al., 2021). *Purpureocillium lilacinum*, *P. chrysogenum*, *F. oxysporum*, *T. brevicompactum* and *F. falciforme* were recovered from an abandoned dumpsite and degraded LDPE in 30 days, as proven by SEM and FTIR analysis (Spina et al., 2021). Two strains of *P. simplicissimum* derived from plastic debris collected from municipal sources and evaluated on LDPE sheets for 150-day. The untreated sheets achieved weight reduction of 58.0 ± 4.04 and 24.78 ± 3.94%, while the pre-alcohol treated sheets achieved weight loss of 60.1 ± 3.56 and 25.58 ± 2.72%. The strains F1 (Bar2) and F2 exhibited CO₂ evolution rates of 20 ± 3.45 and 05 ± 1.67 g/L, respectively (Ghosh & Pal, 2021). The plastic decomposition process was carried out by *Fusarium sp.*, *Penicillium sp.*, and *A. fumigatus*, which were found in waste disposal site. Over a period of 40 days, these species caused weight losses of 7.08, 19.17, and 21.88%, respectively. Other techniques like Plate assay method, Zone method, SEM-EDAX, FT-IR were also used to screen and confirm the degradation (Lakshmi & Selvi, 2021). *Cephalosporium sp.* NCIM 1251, which was procured from NCL, caused 12.22±0.82% reduction in weight of nitric acid pretreated LDPE over a period of 8 weeks. FTIR, SEM, XRD were used to study the surface and change in material nature (Chaudhary et al., 2022). *R. oryzae* MT259131, obtained from a landfill, achieved a 60% degradation efficiency of LDPE within a span of 60 days. The degradation was verified by SEM and FTIR (Seenivasagan et al., 2022). *P. chrysogenum*, *R. nigricans*, *Chaetomium murorum*, *Memmoniella echinata*, *A. fumigatus*, *Stachybotrys chartarum*, *A. niger*, *C. globosum* and *A. flavus*, which were isolated from polyethylene waste, showed the degradation of LDPE in 30-day period. The weight reduction of the plastic was 8, 6, 2, 3, 7, 2, 9, 5, 7 and 3% in comparison to biodegradable plastic, which experienced weight reductions of 23, 14, 5, 8, 15, 7, 28, 10, 18 and 8% respectively. The study was also supported by SEM analysis (Saxena et al., 2022).

31 *T. harzianum* KKP 534 consumed LDPE MPs in a matter of nine days which was studied with enzymatic activity (Bernat et al., 2023). The wood-decaying fungus *Phlebiopsis flavidoalba* had successfully degraded LDPE with CO₂ emissions of 3.07 ± 0.13% mg/L and percent weight loss 46.79 ± 0.67 after 45 days. SEM and FTIR provided further confirmation (P. Perera et al., 2023). The untreated LDPE was degraded by *Cladosporium sp.*

CPEF-6 showed $0.30 \pm 0.06\%$ by weight after 30 days, while the heat-treated LDPE showed a rise of $0.4 \pm 0.0\%$. Environmental scanning electron microscopy (ESEM) and FTIR corroborated the findings (Gong et al., 2023). The yeasts isolated from the gut of wood feeding termite identified as *Sterigmatomyces halophilus* SSA1575, *Meyerozyma guilliermondii* SSA1547, *M. caribbica* SSA1654 successfully degraded LDPE in 45 days. They showed tensile loss of 43.6, 19.2, 32.0 and weight loss of 18.6, 11.1 and 13.3 % respectively. The maximum tensile and weight loss of 63.4 and 33.2 % respectively was detected in the yeast consortium (Elsamahy et al., 2023). *C. cladosporioides* (strain Clc/1, Gen. bank: OP729904) found from agricultural field successfully degraded LDPE in 90 days. The structural changes of the LDPE were screened by using SEM, ATR-FTIR, normal Raman and with an unconventional Surface-enhanced Raman scattering (SERS) (Puliga et al., 2023). FE-SEM, FTIR, and TGA verified that, *P. citrinum* isolated from the soils of a plastic waste dump yard in Bhopal, India, broke down LDPE ($51 \mu\text{m}$) in 90 days. For untreated LDPE, the weight loss was 38.82 ± 1.08 , while for nitric acid-treated LDPE, it was 47.22 ± 2.04 (Khan et al., 2023).

Aspergillus sp. 1, *Aspergillus sp. 2*, *Trichoderma sp.*, *Rhizopus sp.*, *Penicillium sp.*, *Alternaria sp.*, and *Candida parapsilosis* were isolated from the activated sludge, river sediment, and compost. They experimented with LDPE, 20 % thermoplastic starch (TPS), LDPE + TPS, LDPE + TPS + styrene-ethylene-styrene degradation (SEBS). The fungi isolated from activated sludge and river sediment showed 3.3184%, 14.1152%, and 16.0062% weight loss. Whereas 3.9625%, 20.4520% and 21.9277% degradation were observed in fungi isolated from compost. SEM, FTIR/ATR data demonstrated that degradation was more intense in fungi isolated from compost than in activated sludge and river sediment (Kučić Grgić et al., 2023). After being examined for degradation, *Geotrichum candidum* HAU-F1 (OQ940537), *F. oxysporum* HAU-F2 (OQ940538), and *Trichoderma sp.* HAU-F3 (OQ940550) were discovered on the residual mulch film (RMF) of PE from a vegetable field that had been mulched. After ninety days, the weight loss percentages were 1.5809, 1.7823, and 1.8398, in that order. A consortium comprising all fungi demonstrated a weight decrease of 1.6239%. SEM confirms that surface LDPE film wrinkles and holes are the result of biodegradation (Lin et al., 2024) (Table No. 2).

High Density Polyethylene (HDPE)

Aspergillus and *Penicillium* have been shown to break down HDPE in three months, as demonstrated by DSC and FTIR tests (Ojeda et al., 2009). *A. niger* consumed HDPE in 6 months, as demonstrated by SEM, FTIR and viscosity variation (Alariqi & Singh, 2010). *A. niger* ITCC 6052, obtained from a waste disposal site, decomposed plastic within a span of 30 days. The sheet had a reduction in weight of around 3.44%, accompanied by a loss of 61% in tensile strength. SEM and FTIR supported the study (Mathur et al., 2011). The plastic was destroyed *A. terreus* MF12, collected from a garbage yard, within a period of 30 days. The HDPE sheet was exposed to heat at 50°C for 72 h. further they programmed for alternate exposure of UV (312 nm) and humidity for 5 cycles per day. A reduction in weight of $9.4 \pm 0.1\%$ was observed and verified by using FTIR, SEM, and GC-MS (Balasubramanian et al., 2014). Consortium of fungi isolated from compost, degraded HDPE 80/Starch 20 (pretreated UV for 500 hrs) in 20 and 200 days. The confirmatory tests were Synchrotron-

FTIR microscope (SFTIR- M), SEM, FTIR and tensile testing(X. Liu et al., 2013). In 30 days, duration *A.tubingensis* VRKPT1 and *A. flavus* VRKPT2 isolated from plastic waste dump site in Gulf of Mannar, India has degraded HDPE (40 μ m) with 6.02 ± 0.2 and $8.51 \pm 0.1\%$ weight loss for both fungi respectively. The degradation was confirmed by FTIR analysis(Sangeetha Devi et al., 2015).*P.oxalicum* KU559906 and *P.chrysogenum* KU559907 were obtained from a location where plastic waste was dumped. They showed 55.34 and 58.59% weight reduction of HDPE respectively, within a period of 90 days. FE-SEM and AFM were used to study the surface morphology whereas FTIR was used to analyze functional changes(Ojha et al., 2017).Polyethylene bags were kept in soil for 6 months to get plastic degrading fungus from which *A.oryzae*was obtained. It showed complete degradation of black HDPE within 90 days.The weight loss for surface sterilized plastic was 22.6 and 28% for PDB and CDB, respectively. Pre-treated plastic sheet with palmitic acid in PDB and CDB lost 24% and 33% of their weight. Additional confirmation was added in support with SEM and FTIR(Jayaprakash & Palempalli, 2018).

Bjerkanderaadusta TBB-03, which was isolated from the Ohgap Mountains in North Chungcheong Province, South Korea, decomposed HDPE (0.05 mm thick) in 90 days. SEM and Raman spectroscopy were used for conformation(Kang et al., 2019). *M.circinelloides* (MTCC 3945) degraded HDPE of 10 and 38 μ sheet for a period of 45 days, resulting in weight reductions of 1.428 ± 0.51 and $0.709 \pm 0.14\%$ for untreated plastic strips, and 1.13 and 0.610% for pre-thermally treated (80°C) plastic strips respectively. The sample was obtained from a pure culture and the findings were validated using FTIR analysis (Sharma et al., 2019).The digestive tract of a wax moth (*G.mellonella*) was shown to harbor *A. flavus* PEDX3, which may degrade polyethylene MPs within a span of only 28 days. FTIR measurements confirmed the breakdown of HDPE due to the presence of microplastic carbonyl groups and ether groups (Zhang et al., 2020).*A.fumigatus*, *A.flavus*, and *F.solani*, were collected from soil and degraded plastic over a period of 90 days. The weight reduction of polyethylene following physical(UV 300 nm wavelength for 10 days), thermal (80°C for 120 hours), and chemical treatment (concentrated nitric acid for 10 days)was 2.12, 1.38 and 2.58%, respectively. In contrast, untreated (UT) polyethylene experienced weight loss of 1.43, 1.31 and 1.84%. The findings were supported by SEM and FTIR(Rani et al., 2020).*A. flavus*isolated from farm sludge (FS), soil, wax and meal worms' excretaand degraded 5.5% and 2.5% of the weight ofHDPE plastic sheets, after a span of 100 days. SEM and FTIR was used for confirmation of degradation(Taghavi et al., 2021).*C.parapsilosis* ATCC 96144, encountered for its ability to degrade HDPE, was found in the sediments of the deep sea. The degradation of plastic was observed within 96 hours, as evidenced by FTIR and SEM analysis(M. M. Oliveira et al., 2022).The*Cephalosporium* strain NCIM 1251, obtained from NCIM, NCL, India, reduced HDPE 18.22% by weight in 56 days following 6 hours of drying at 60°C, 7 days of exposure to UV light in a laminar flow, and 69% exposure in nitric acid. TGA, FTIR, and SEM provided further evidence(Chaudhary et al., 2022).Within 20 days, the powdered form of HDPE could be consumed by *C. halotolerans*, which was isolated from the digestive tract of *G. mellonella* larvae. An SEM analysis was performed on the particles. This was further validated by FTIR, enzyme and protein analysis (Napoli et al., 2023) (Table No. 3).

PolyesterPolyurethane (PS-PU)

Five strains of *Nectriagliocladioides*, *P. ochrochloron*, and seven strains of *Geomycespannorum* derived from PS-PU soil degraded within 44 days. The maximum reduction in tensile strength of PS-PU was recorded by 60%. This study was supported by SEM analysis(Barratt et al., 2003).The fungal communities (*G.pannorum*and *Phoma sp.*) in soil showed degradation of PS-PU in just five months. It was confirmed by tensile strength in soil and reviled up to 95%(Cosgrove et al., 2007).(Ibrahim et al., 2011) isolated different fungi from soil, wall paints (Latex), plastic debris and shields of street light posts for degradation of PS-PU. In shaken liquid (L) culture, *F. solani* (FsM-6) completely degraded (100%) followed by *A.solani* (FsH-3) and *A. terreus* (FsH-8) with 71.8%; *A. fumigatus* (FopI-4) accounts for 40.5%; *A. flavus* (FopI-2) by 26.1% and *Spicaria sp.* (Fp-7) with 12.7% of PS-PU weight loss in 21 days. Similarly, in petriplate (P)tests 72.5%, 22.9%, 63.6%, 58.0%, 94.8%, and 39.5%weight loss was observed respectively. Clear zone test was performed in addition to confirm the growth and degradation.

Pestalotiopsismicrospora completely decomposed the plastic within a span of 14 days. The degradation was confirmed by the utilisation of zone clearance, enzyme activity, and FTIR analysis (Russell et al., 2011).*L.theobromae*, *P.janthinellum*, *F.verticilloides* and *P.puntonii* isolated from forest soil degraded PS-PU in 15 days. It was authenticated with biomass determination and clear zone formation(Urzo et al., 2017).*Papiliotremalaurentii* 5307AH, isolated and identified during a microbiome analysis of an aircraft. Polyethylene succinate (PES) and polyethylene adipate (PEA)along with thermoset PS-PU andIrogran,were used to decomposed during a span of 8 days. The highest concentration of CO₂ (1.2 ± 0.2 mol%) was observed in PES. The reduction was also confirmed using IR microscopy techniques (Hung et al., 2019).Within a short span of fourteen days, *Embarriaclematidis*, obtained from Institute of Excellence in Fungal Research, Thailand, caused the degradation of PS-PU. The presence of degradation was evidenced by a quantification of 0.85 g/L of CO₂. Additionally, enzymaticactivity assay, FTIR and GC-MS analyses were conducted (Khruengsai et al., 2022)(Table No. 3).

Polystyrene (PS)

P.variabile, showed degradation of polystyrene in 16 weeks. It was screened and verified by SEM, FTIR, and GPS(Tian et al., 2017). PS is an artificial polymer made from styrene monomers.*T.hamatum* FR87271 originated from a buried plastic fragment, decreased the amount of virgin PS by 0.9±0.4% within a span of 7 days. Additional confirmation was conducted using FTIR, TGA, GPCand SEM(Malachová et al., 2020).*P. glaucoroseum* was isolated from soil, farm sludge, activated sludge, and worm dung, could degrade 1.8% of PS within a span of 100 days. Due to colonisation of fungus and penetrationof microbial metabolites into the PS, surface deteriorationand formed cavities on the incubated PS could be seenby AFM and SEM. FTIR results were also in support of the study(Taghavi et al., 2021).*Cephalosporium sp.* (NCIM 1251) procured from NCL, had a degradation rate of 12.22±0.82% on nitric acid-treated PS over a period of 56 days.It was further confirmed by SEM, FTIR, XRD, TGA.(Chaudhary et al., 2022).In just 35 days, the PS weight was reduced by 19.7 % using *P. chrysosporium* (BKMF-1767, CCTCC, No. AF-96007) which was

obtained from the China Centre for Type Culture Collection, China. Further verification was carried out using GC-MS, FTIR and SEM (F. Wu et al., 2023)(Table No. 3).

Polyurethane (PU)

The fungus *P.chrysosporium*ME446 (ATCC34541) demonstrated the production of lignin peroxidase when immobilized on polyurethane (PU) foam. Within 10 days, under multiple operational conditions like number of polyurethane foam cubes, glucose concentration and temperature. Also, it showed various amount of enzyme production on addition of various additives(Nakamura et al., 1997). Weight loss, FTIR and SEM have verified that the culture of *C.globusom* from the biological research institution Romania's microbiology department, has effectively broken down the polyurethane in 130 days(Oprea, 2010). Three fungal species, namely *Monascus sp.*, *M.ruber*, and *M.sanguineus* were obtained from the soil at the dumping site. *M. ruber* had the most elevated esterase concentration, with *M. sanguineus* following closely behind. Production of esterase by *M. ruber*, SEM, and Zeta analysis, showed that the PU was completely degraded within a span of 5 days (El-Morsy et al., 2017).According to an enzymatic essay, *Pestalotiopsis sp.*, which was isolated from *Nepenthes ampullaria*, broke down polyurethane in three weeks.(Bong et al., 2017).The fungi *Xepiculopsisgraminea*, *C.cladosporioides*, and *P.griseofulvum*, along with the plant pathogen *Leptosphaeria sp.*, were detected in plastic waste from the shoreline of Lake Zurich. These organisms were observed to possess the ability to decompose PU within a span of 6 days. Also, they observed that the *Agaricusbisporus* and *Marasmiusoreades*from fungal culture can decompose PU around 14 days. The degradation was validated using GC-MS(Brunner et al., 2018).*A. fumigatus* S45 (KF961003), obtained from waste dumping site soil, decomposed PU film within a span of 28 days. The degradation was indicated by a measurement of 10.05 g/L of CO₂, and a weight loss of 15-20%. FTIR, DSC, SEM and Esterase Activity Assay were used for verification of breakdown(Osman et al., 2018).SEM, GC-MS, and liquid chromatography-mass spectroscopy (LC-MS) confirmed that PU cubes were degraded in 12 weeks by uncultured *Arthrographis*, *Apiotrichum*, *Aspergillus*, *Thermomyces*, and compost-derived *Arthrographis*, *Thermomyces*, *Apiotrichum*, and *Mortierella*(Gunawan et al., 2020a). *Cladosporium* SI3, and *P.chrysogenum* SIO2 were isolated from PU rich site in an ocean, examined for consumption of PU for 15/30 weeks and it was screened by SEM, FTIR, and GC-MS (Gunawan et al., 2022b). The PU degrading strains, *R. oryzae* P2072 and *A.alternata* P2073 were isolated from the soil,showing a degradation rate of 2.7% and 3.3% weight loss respectively after incubation of 2 months.SEM and enzymatic analysis also supported the results(K. Y. Wu et al., 2023).

Liu et al., (2023) isolated *Cladosporium sp.* P7 from an activated sludge. The fungal strain degraded 32.42% of PU on Poly(1,4-butylene adipate- Polyurethane (PBA-PU) whereas it increased up to 43.91% along with PDB after 28 days. Similarly, fungus cultured with PU foam on MSM and PDB medium showed 15.3% and 83.8% degradation respectively after 14 days. It was further confirmed by SEM and FTIR(J. Liu et al., 2023).In the liquid media (L), PU was consumed by fungal strains *Clonostachy* PB54 (38%), PB62 (36%) and *Purpureocillium spp.* PB57 (33%) whereas on solid media (S), strains PB54, PB57 and PB49 produced the highest average weight loss of 45%, 42% and 39% after 90 days of incubation. These strains were isolated from the landfill. The degradation was further confirmed by

FTIR, LC-MS and X-ray photoelectron spectroscopy (XPS)(Bhavsar et al., 2024).*L.iraniensis* (ZHKUCC 22-0282), *M.alpina* (ZHKUCC 22-0283) which were found growing on PU foam, degraded 13.55 on malt extract agar (MEA) and 26.30% on malt agar medium containing chloramphenicol (CMEA) by mass in four months. The results of the SEM analysis corroborate the confirmation (Xu et al., 2024)(Table No. 3).

Polyvinyl Chloride (PVC)

Soil containing *P.chrysosporium* combined with municipal sewage sludge showed degradation of PVC sheets (treated with cellulose (1:1)) in three months. FTIR was used to confirm it(M. I. Ali et al., 2009). The degradation of PVC occurs during a span of 10 months when it is subjected to *P.chrysosporium* EU543990, *Lentinustigrinus*EU543989, *A. niger* EU543987, and *A. sydowii*EU543988 found in soil. The maximum production (7.31g/L) by *P.chrysosporium* and (6.02g/L) of CO₂ by *A. niger* after 4 weeks. The analytical techniques of SEM, FTIR, GPC, and NMR also demonstrated a notable adaptation in biotransformation(M. I. Ali et al., 2014). *Cochliobolus sp.* isolated from soil of plastic industry has degraded PVC in 7 days, as confirmed by FTIR, GC-MS and SEM(Sumathi et al., 2016). A 75% reduction in the weight of PVC was seen within a period of 28 days by *C.globosum* ATCC 16021 from a culture collection. Further it was supported by SEM analysis(Vivi et al., 2019). *PhanerocheateChrysosporium* isolated from plastic waste and wood material which degraded PVC sheets in 2 months with the weight loss of 31%. FTIR and SEM confirm the breakdown(Khatoun et al., 2019).

T.hamatum FR87271, *Trichaptumabietinum* J768676, *Byssochlamys nivea* FK1 and *B. nivea* JM5 broke down PVC within a period of 2 months, with rates of 20.0±0.5, 17.5±0.7, 18.4±0.7, and 15.5±0.9 respectively in liquid medium. The sample was derived from soil collected from different localities and subsequently subjected to analysis utilizing FTIR, TGA, GPC, and SEM techniques(Malachová et al., 2020). *A. niger* NG_065763.1 exhibited a degradation rate of 10±3.3% and *A. glaucus* NG_063391.1 showed a degradation rate of 32±3.3% when exposed to liquid media containing PVC over a period of 28 days. The changes in surface topography were confirmed by SEM and the changes in functional groups intensity was observed using the FTIR(Saeed et al., 2022). *Fusarium sp.*, *T.viridae*, *A. flavus*, *A. fumigatus*, *A. niger*, *P.glandicola*, and *P. chrysogenum* were found in a dump site. Over a period of 42 days, these fungi degraded PVC by 6%, 12%, 6%, 2%, 10%, 6%, and 10% by weight, respectively (Emmanuel-Akerele & Akinyemi, 2022). Weight reduction analysis showed that when *A. fumigatus-3* was isolated from landfill, showed highest reduction (2.15 ± 0.42%), followed by *A. fumigatus-2*, *Malassezia sp.* and *A. fumigatus-1*, with reduction percentages of 1.92±0.51, 1.46±0.7 and 0.718±0.1 respectively after 30 days. SEM analysis revealed that *A. fumigatus3*, *A. fumigatus2* and *Malassezia sp.* strains could create surface cracks on the PVC strips, with the most prominent erosion observed in the *A. fumigatus-3* strain. Whereas SEM images of control PVC strips displayed no surface erosion. The degradation study was also supported by enzymatic activity(El-Dash et al., 2023)(Table No.4).

Polypropylene (PP)

577 *Phanerochcetechrysosporium* ME-446 (ATCC34543) DSM has degraded PP with
 578 lignin in the duration of 30 days, which was confirmed by elongation at break and
 579 enzymatically(Mikulášová & Košíková, 1999). *A. niger*, when exposed to compost for a
 580 duration of six months, demonstrated the ability to decrease the size of a
 581 unirradiatedisotactic-PP sample by 22% weight loss. This finding was also supported by
 582 SEM and FTIR(Pandey & Singh, 2001).*A. niger* consumed isotactic polypropylene (i-PP) in
 583 6 months, as demonstrated by SEM, FTIR and viscosity variation(Alariqi & Singh, 2010).The
 584 blends of PP/TPS with 6 wt % of ethylene-(vinyl acetate) copolymer (EVA) were degraded
 585 by *Trichoderma* sp. in 3 weeks. The confirmatory tests were Small Angle X-ray Scattering
 586 (SAXS), Transmission Electron Microscopy (TEM), TGA, SEM and FTIR(Hanifi et al.,
 587 2014). *L.theobromae* isolated from *P.flavida*, *Aspergillus* sp., and *Paecilomyceslilacinus*
 588 isolated from *H.brunonis* has degraded PP (20 µm) in 90 days as confirmed by the FTIR,
 589 DSC, SEM and changes in viscosity tests(Sheik et al., 2015).*Trametes villosa*, *T. versicolor*,
 590 *Pycnoporus sanguineus*, *Fuscoporia ferrea* degradedPP and EVA blended with wood flour of
 591 *Eucalyptus grandis* and *Pinus elliotii* in 12 weeks with a coupling agent (CA). The observed
 592 weight loss by *F. ferrea* for PP-EVA-Eu-CA was 14% and for PP-EVA-Pi-CA was 16.5%.
 593 SEM and CO₂ production served as confirmation of degradation(Catto et al.,
 594 2016).According to SEM, FTIR, AFM, and static contact angles (SCA), *B.adusta* from the
 595 Research Laboratory for Fungi with Applications in Ecological Reconstruction of Polluted
 596 Soils with Heavy Metals (RECOSOL) degraded PP, PP/*E. globulus* (PP/EG), PP/*Pinecones*
 597 (PP/PC), and PP/*Brassica rapa* (PP/BR) in 49 days(Butnaru et al., 2016).An investigation
 598 was conducted to assess the capacity of culture collected *Aspergillus* and *Penicillium* to
 599 decompose pure PP. The degradation rates of both neat PP 1 cycle (-0.262 % mass loss) and
 600 neat PP 7 cycle (-0.620 mass loss) (temperature profile of 175, 180 and 190°C at a screw
 601 speed of 60 rpm), were observed to be 30 days. The SEM and FTIR offer supplementary
 602 support for the findings(T. A. De Oliveira et al., 2020).After being isolated from a solid waste
 603 disposal site, *A. fumigatus* consumed polypropylene (PP) cups in six months, causing an
 604 18.0% weight loss. Additionally verified by FTIR and SEM(Oliya et al., 2020).PP was
 605 consumed by *Coniochaetahoffmannii* and *Pleurostomarichardsiae*, isolated from
 606 hydrocarbon-contaminated environments in two months. The PP films were checked for
 607 degradation by SEM, Raman spectroscopy, FTIR-ATR and Enzymatic activity (Porter et al.,
 608 2023).The PP sheets were treated with *C.halotolerans* SUK PRAKASH (ON024632) which
 609 was isolated from soil of solid waste dumping siteand was examined for weight loss after 8
 610 months. The maximum weight loss was found in sunlight-exposed PP sheets (8.6%),
 611 followed by UV-exposed PP sheets (6.1%), and without pre-treated PP sheets (4.2%). FTIR
 612 spectroscopy showed the variance in the intensity of bands at the different locations (Parit et
 613 al., 2023).*A. flavus*OL919436 and OL919440, *A. fumigates* OL919439 and OL919437,
 614 *F.oxysporum*OL919444 and *P.granulatum*OL919448were isolated from municipal waste
 615 landfill siteand found to successfully degrade the PP in 90 days. The SEM images showed
 616 that the surface of the granule was covered with fungal shreds of different lengths. The empty
 617 spaces in the images visibly demonstrate delicate pits in the granule structure. Microdamage
 618 to the outer layer of the structure was clearly visible. The degradation studies are also
 619 supported by FTIR (Wróbel et al., 2023).

Polyethylene Terephthalate (PET)

Pseudomonas fluorescens, *A. niger*, and *P. pinophilum* were employed to degrade PET (225-275 μm) that included nitrated units. Both were obtained from uncontaminated cultures. Molecular weight loss by using SEC and SEM were used to validate the experiment. The degradation process lasted for duration of three months (Marqués-Calvo et al., 2006a). *A. niger* (CECT 2700), *P. pinophilum* (2912) isolated from Colección Española de Cultivos Tipo has degraded PET in the duration of 3 months which is confirmed by optical imaging profiler (OIP) (Marqués-Calvo et al., 2006b). *P. funiculosum* was obtained from a landfill and studied for a period of 84 days to assess its ability to degrade PET. Various doses of Bionolle were used to test the polymer. The polymer composition was characterized by the following weight ratios: 100/0, 90/10, 75/25, 50/50, and 0/100, with corresponding weight loss percentages of 0.08, 0.07, 0.21, 0.19, and 90.28, respectively. The deterioration was enhanced to a greater extent with the assistance of SEM, FTIR, and XPS techniques (Nowak, Pająk, et al., 2011). In a study conducted by (Nowak et al., 2011) PET, a type of a polyester was buried in waste coal, a forest and an extinct volcano crater over a period of 225 days. *A. awamori*, *M. subtilissima*, and *G. viride* were identified on the buried plastic film. The weight loss recorded in waste coal was 5.76%, 2.02% in forest and 17.03% in soil. The tensile strength revealed to be the most delicate among all the sites because of elongation at break of 98%. The findings were further supported by SEM and FTIR. *Thielavia terrestris* CAU709, isolated from soil, demonstrated the ability to hydrolyze PET when incubated with a low molecular mass cutinase for 24 hours (S. Yang et al., 2013). *Aspergillus sp.*, *Penicillium sp.*, and *Fusarium sp.* which were isolated from sewage, degraded PET flakes and foam in 70 days as confirmed by FTIR (Umamaheswari et al., 2014). Fungal strains displaying possibilities for converting PET nanoparticles were *A. oryzae* [CBMAI 2034] C361 (1.0 ± 0.1), *Trichoderma sp.* [CBMAI 1932] C65 (1.7 ± 0.3), *Trichoderma sp.* [CBMAI 2032] C68 (1.1 ± 0.2), *Trichoderma sp.* L1239 (7.1 ± 0.2), *M. arundinis* L43 (2.4 ± 0.4), *M. arundinis* L84 (4.1 ± 0.5), *Fusarium sp.* L1269 (1.4 ± 0.2) detected by fluorescence after 15 days. Other low-capacity degradable fungi found to be *R. miehei* C357 (0.3 ± 0.1), *P. brevicompactum* C360 (0.2 ± 0.1), *Aspergillus sp.* C362 (0.1 ± 0.0), *Aspergillus sp.* C363 (0.4 ± 0.1), *Trichoderma sp.* C64 (0.4 ± 0.1), *Trichoderma sp.* [CBMAI 2033] C70 (0.2 ± 0.0), *Neopestalotiopsis sp.* [CBMAI 2030] F053 (0.4 ± 0.1), and *E. sorghinum* F057 (0.5 ± 0.1). All the findings were confirmed with SEM analysis (Chaves et al., 2018). Freshwater isolates of *Microsphaeropsis arundinis* (2), *Mucor*, *Trichoderma*, *Westerdykella*, and *Pycnidophora sp.* have successfully degraded PET and further verified by high-performance liquid chromatography with UV detector (HPLC-UV), FTIR, SEM, and fluorescence examination (Malafatti-picca et al., 2019). The degradation of PET was attributed from the culture collected *Clitocybe sp.* and *L. laccata* for over a period of six months which was confirmed by SEM and EDX analysis (Janczak et al., 2020).

Pseudomonas sp. could degrade PET films 0.6% by weight within 100 days which was isolated from AS, FS and soil. The colour of PET film changed from shiny-brown to matte-white. The AFM and SEM analysis showed cavities and surface deterioration. FTIR analysis confirmed the degradation (Taghavi et al., 2021). Dry weight measurement, titration assay, and SEM analysis verified that *Moniliophthoralarori*, which was isolated from cacao pods, produced cutinase that broke PET by 43 % by weight in 21 days (Vázquez-Alcántara et

al., 2021). *A. tamarii* and *P. crustosum*, isolated from soil on the premises of Rajalakshmi Engineering College, India, degraded PET through cutinase activity in 30 days as confirmed through terephthalic acid (TPA), FTIR, and SEM analysis (Anbalagan et al., 2022). *Lecanicillium phanocladii* (IBPPM 542) and *F. oxysporum* (IBPPM 543) from the IBPPM Collection of Rhizospheric Microorganisms, originally isolated from oil-polluted samples, *T. harzianum* (IBPPM 664) from the Institute of Ecology and Evolution, Russian Academy of Sciences and *T. sayulitensis* (IBPPM 665), isolated from the rhizosphere of *Miscanthus* grown in Zn-polluted soil successfully degraded PET in 30 days and showed 11.6 ± 2.9 , 22.0 ± 2.2 , 17.2 ± 3.8 , 10.0 ± 3.3 percent weight loss respectively. Production of enzymes like cutinase, peroxidase and oxidase supported the degradation of PET (Pozdnyakova et al., 2023). *P. ostreatus* from the University of Ibadan, Nigeria and *P. pulmonarius*, provided by Zero Emissions Research Initiative (ZERI), Namibia, successfully degraded the PET flakes after 60 days. There was a color fading of the PET flakes due to increased carboxyl-terminated species because of enzymes secreted by the fungi. The biodegradation was studied with the help of FTIR and GC-MS analysis (Odigbo et al., 2023) (Table No. 5).

Poly(ϵ -caprolactone) (PCL)

Pochonialilacinus (formerly *Paecilomyces lilacinus*) isolated from soil and activated sludge, demonstrated the ability to degrade PCL by 10% in 10 days. It was further confirmed with HPLC (Oda et al., 1995). The culture of *A. fumigatus* was introduced to PCL for 49 days. After 14 days, PLC films showed weight reduction and change in tensile properties. The degradation was studied by DSC (Albertsson et al., 1998). In 45 days, PCL was breached apart by *P. simplicissimum* and *A. fumigatus*. SEC, DSC, FTIR, SEM, and ESCA were used to corroborate the observed 50–55% weight decrease (Renstad et al., 1998). In aerobic soil study, *Paecilomyces sp.*, *Thermomyces sp.*, were found at 30°C degrading PCL 30 days. It was confirmed by weight measurement and analysis of soil (Nishide et al., 1999). In 50 days, the SEM test verified that *Penicillium spp.* isolated from soil had effectively broken-down PCL (Kamiya et al., 2007). Seo et al. (2007) conducted a fascinating study where they broke down PCL utilizing a unique cutinolytic-ustilaginomycetous yeast, *Pseudozyma jejuensis* OL71, discovered on orange leaves. They confirmed the degradation by measuring the total organic carbon (TOC) concentration, which showed a fivefold increase in Yeast and Mold medium with 10 g/l PCL within a span of 12 days. It also showed the best growth on YM medium with 10 g/l cutin (Seo et al., 2007). mass loss and SEM analysis confirms that the soil-isolated *A. fumigatus*, *A. niger*, *A. versicolor*, *Aspergillus spp.*, *P. simplicissimum*, *Penicillium spp.*, and *C. cladosporioides* have effectively broken-down blend of PCL with cellulose acetate (CA) 25%, reduced the tensile strength by 38, 25, and 13% in the blends of 80/20, 60/40, and 40/60 in nine months respectively (Rosa et al., 2009). *P. oxalicum* strain DSYD05-1, isolated from soil, demonstrated the ability to degrade PCL within 6 days, confirmed through enzymatic assay and weight loss analysis (Li et al., 2012). *T. terrestris* CAU709, isolated from soil, demonstrated the ability to hydrolyze PCL when incubated with a low molecular mass cutinase enzyme for 24 hours (S. Yang et al., 2013). Enzymatic degradation and SEM confirm that in 7 days, *P. antarctica* JCM 10317,

707 *Ustilago maydis* MAFF 236374, 236375, 236376, 236377, 236378, and *S. cerevisiae*
 708 BY4741 from culture collections of Japan, NIAS General Bank Japan, and EUROSCARF,
 709 Germany, degraded PCL film (Shinozaki et al., 2013). *P. japonica* is a newly discovered yeast
 710 belonging to the ustilaginomycetous group. It was found on the *Hyoscyamus muticus* plant,
 711 often known as Egyptian henbane. This yeast could break down PCL in the form of film and
 712 foam. They revealed a significant weight reduction of 93.33% for PCL film and 43.2% for
 713 foam over a period of 15 and 30 days respectively (Abdel-Motaal et al., 2014). Agricultural
 714 soils collected from Chiang Mai and Lampang provinces in northern Thailand were screened
 715 for PCL degradation by the agar diffusion method. Among the several isolates,
 716 *Amycolatopsis* sp. Strain SCM_MK2-4 produced enzymes like protease, esterase and lipase
 717 and showed 0.023 U/mL activity in 30 days (Penkhrue et al., 2015). Soil of western and
 718 central parts of Spitsbergen, Svalbard Archipelago, *Trichoderma* sp. (16H) and *Clonostachys*
 719 *rosea* (16G) isolated and showed weight loss of 21.54 and 52.91% of PCL respectively. *C.*
 720 *rosea* also showed degradation of 34.5% at 20°C in liquid medium. The experiment was
 721 further validated by SEM (Urbanek et al., 2017). *A. fumigatus* and *T. lanuginosus* showed
 722 complete degradation of PCL when buried in compost and incubated at 50°C after 91 days.
 723 They also observed significant reduction in tensile strength within a 2 week at below 45°C.
 724 Further they recorded abundant growth of *A. fumigatus* at 25 and 37°C whereas
 725 *Neocosmospora* and *F. solani* and *A. fumigatus* revealed at 25°C in compost and *F. solani*
 726 alone in soil at same temperature (Al Hosni et al., 2019). A culture of *C. globosum* obtained
 727 from a collection was utilized for the degradation of PCL with significant reduction of 75%
 728 in mass over a period of 28 days and supported by SEM analysis (Vivi et al., 2019). Clear
 729 zone formation indicates that the Korean Agricultural Culture Collection (KACC)'s
 730 *Apiotrichum porosum* (83034BP), *P. samsonianum* (KNUF-20-PPH03), *T. pinophilus* (KACC
 731 83035BP), *P. lilacinum* (KNUF-20-PDG05), and *Fusicolla acetilerea* (KACC 83036BP)
 732 degraded PCL in 45 days (Lee et al., 2021). In just one month, PCL, was successfully
 733 degraded by consortium of *Geomyces* sp. (B10I), *Sclerotinia*, *Fusarium* sp. (B30M),
 734 *Mortierella*, and *Hansenula anomala* which were isolated from soil, as demonstrated by the
 735 establishment of a clear zone (Urbanek et al., 2021). Dry weight measurement, titration assay,
 736 and SEM analysis verified that *M. roreri*, which was isolated from cacao pods, produced
 737 cutinase that broke down PCL 43 % by weight in 21 days (Vázquez-Alcántara et al.,
 738 2021) (Table No. 5).

739 **Polyhydroxy Butyrate (PHB) and polyhydroxybutyrate co-hydroxyvalerate) (PHBV)**

740 *P. simplicissimum*, *Verticillium leptobactrum*, and *A. fumigatus* degraded PHB and
 741 PHBV in compost in 98 days. Weight loss and loss of mechanical properties verified the
 742 degradation (Mergaert et al., 1994). *P. lilacinus* isolated from soil and activated sludge,
 743 demonstrated the ability to degrade 100% of PHB in 10 days. It was further confirmed with
 744 HPLC (Oda et al., 1995). In aerobic soil study, *Mucor* sp. was found at 30°C degrading
 745 PHB/HV in 23 days. It was confirmed by weight measurement and analysis of soil (Nishide et
 746 al., 1999). From garden soil, *Penicillium*, *Cephalosporium*, *Paecilomyces* and *Trichoderma*
 747 has degraded PHB in 30 days, confirmed by mass loss and mechanical tests (Savenkova et al.,
 748 2000). *A. fumigatus* LAR 9, *P. farinosus* LAR 10 and *F. solani* LAR 11 were isolated from
 749 PHB buried in activated sludge for 25 days. It showed weight loss of $98.9 \pm 4.0\%$ at 37°C.

Whereas, *A. fumigatus* LAR 9, *Curvularia protuberata* LAR 12 and *P. simplicissimum* LAR 13 found on Sky-Green1 (SG) with $77.5 \pm 2.4\%$ at 28°C and *A. fumigatus* LAR 9 and *A. parasiticus* LAR 26 on Mater-Bi1 (MB) with $72.1 \pm 2.2\%$ at 60°C weight loss in 55 days. Further it was confirmed by SEM and Sturmtest (Kim et al., 2000). PHB has been broken down by the soil-isolated *Trichoderma* spp. in 50 days, as shown by FTIR (Răpă et al., 2014). *A. fumigatus* (KP724998.1) in soil whereas *A. fumigatus* (KR527135.1) in compost at 37°C , *F. solani* (KX929306.1) in compost at 25°C and *T. lanuginosus* (KT365229.1), *Sordaria* sp. (JN659492.1), *S. thermophilum* (AB085928.1) and *C. thermophilum* (AB746179.1) in compost at 50°C showed significant weight loss around 300 days (Al Hosni et al., 2019). *A. niger* (soil contaminated with oil wastes) obtained from the Department of Biotechnology, Ministry Science, degraded PHB on solid media with a 100% weight loss in 12 days whereas it took 14 days to consume in liquid medium (Iman et al., 2019). *P. oxalicum* strain SS2 has broken down PHB and PHBV from soil in emulsion and films within 36–48 hours at 30°C in a lab-built soil environment within a week, as confirmed by SEM, NMR, DSC, FTIR, Gel Filtration Chromatography (GFC), and Molecular Weight Determination (MWD) (Satti et al., 2020) (Table No. 5).

Polylactic Acid (PLA)

Enzymatic degradation and SEM confirm that in 7 days, *P. antarctica* JCM 10317, *U. maydis* MAFF 236374, 236375, 236376, 236377, 236378, and *S. cerevisiae* BY4741 from culture collections of Japan, NIAS General Bank Japan, and EUROSCARF, Germany, degraded PLA film (Shinozaki et al., 2013). Several isolates were collected from northern Thailand, *Amycolatopsis* sp. SCM_MK2-4 exhibited 36.7 % degradation of PLA film after seven days. They also reported protease, esterase and lipase enzymes, which were responsible for biodegradation (Penkhrue et al., 2015). *T. lanuginosus* was prominently identified in compost and soil under controlled conditions. PLA at 25°C and 37°C showed no significant weight reduction, whereas, after approximately 18 weeks, rapid weight loss was observed at 50°C in compost (Al Hosni et al., 2019). Clear zone formation indicates that the Korean Agricultural Culture Collection (KACC)'s *A. porosum* (83034BP), *P. samsonianum* (KNUF-20-PPH03), *T. pinophilus* (KACC 83035BP), *P. lilacinum* (KNUF-20-PDG05), and *F. acetilerea* (KACC 83036BP) degraded PLA in 45 days (Lee et al., 2021). *P. chrysosporium* (BKMF-1767, CCTCC, No. AF-96007) procured from China Center for Type Culture Collection, China, degraded 19.7% PLA by weight in 35 days. Additional confirmation was done with the help of FTIR, SEM (F. Wu et al., 2023) (Table No. 6).

Polybutylene Succinate (PBS)

In 50 days, the SEM test verified that *Penicillium* spp. isolated from soil had effectively broken-down PBS (Kamiya et al., 2007). *F. solani* isolated from farmland soil has degraded the polybutylene succinate in 14 days. It was demonstrated by measuring CO_2 evolution (Abe et al., 2010). Within ten days enzymatic activity and a SEM test have indicated that *Paraphomachrysanthemicola* (FJ426987), which was isolated from healthy leaves of wheat, barley, and rice grown in fields, successfully wiped out PBS film (Bionolle 1001 G) ($20\text{ }\mu\text{m}$) (Koitabashi et al., 2012). *T. terrestris* CAU709, isolated from soil, demonstrated the ability to hydrolyze PBS when incubated with a low molecular mass cutinase enzyme for 24

hours(S. Yang et al., 2013). Enzymatic degradation and SEM confirm that in 7 days, *P.antarctica* JCM 10317, *U. maydis* MAFF 236374, 236375, 236376, 236377, 236378, and *S. cerevisiae* BY4741 from culture collections of Japan, NIAS General Bank Japan, and EUROSCARF, Germany, degraded PBS film(Shinozaki et al., 2013). *Cryptococcus magma*, *C. magnus* JCM 9038 (CBS 140),*Filobasidiumfloriforme* JCM 10631 (CBS 6241), *P. antarctica* JCM 10317 procured from Japan Collection of Microorganisms of the Riken Bio-resource Center, Japan which were isolated from larval midgut of a stag beetle (*Aeguslaevicollis*) showed degradation of PBSin 4 days. The confirmation was done on the basis of enzyme production(Suzuki et al., 2013). Previously isolated *Paraphoma* sp. from barley, successfully degraded PBS films in 7 days as proved by the enzymatic degradation test(Koitabashi et al., 2016). *P. antarctica* (PaE) and *Paraphoma* sp. B47-9 (PCLE) have degraded PBS (Bionolle #1020)in 1-4 hrs, which was confirmed using LCMS(Sato et al., 2017). Enzymes synthesized by SCM_MK3-3 isolate and *A. thailandensis* CMUPLA07showed PBS degrading activity which further confirmed by SEM (Penkhrue et al., 2015).Al Hosni et al., (2019) incubated *T. pinophilus* (MF686817.1), *A. cellulolyticus* (AB474749.2), *P. pinophilum* (AB474749.2) and *A. fumigatus* (KF494830.1) in compost and soil. They recorded moderate degradation of PBS at 50°C in compost and 37°C in soil within 300 days. In just one month, PBS was successfully degraded by *Geomyces* sp. (B10I), *Sclerotinia*, *Fusarium* sp. (B30M), *Mortierella*, and *H.anomala* isolated from soil, as demonstrated by the establishment of a clear zone(Urbaneck et al., 2021)Table No. 6.

di-(2- ethylhexyl phthalate (DEHP)

*F. oxysporum*and *M. alpina*isolated from soil in central Manchester, UK, *P. pulmonarius*, two strains of *P. ostreatus* and *P. floridapro*cedured from the Chinese University of Hong Kong Collection, American Type Culture Collection and Universidad Autonoma de Tlaxcala collection respectively. In the DEHP-containing medium, *F. oxysporum*and *M. alpinapro*duced the utmost amounts of biomass, 200 and 82 mg/cm², respectively(Suárez-Segundo et al., 2013).*F.culmorum*, a culture from Research Centre for Biological Sciences (CICB) at Universidad Autónoma de Tlaxcala, Mexico degraded 99% of DEHP (1000 mg/L) after 144 h of incubation whereas at 500 mg/L, it showed 93% and nearly 98% degradation within 84 h and 144 h of incubation, respectively. The experiment was confirmed by GC-MS analysis(Ahuactzin-Pérez et al., 2016).*P. ostreatus*, *P.seryngii*, *Lentinula edodes*, and *A. bisporus*were procured from the market. The manganese peroxidase activity (MnP) confirmed the degradation of DEHP after 20 days(Hock et al., 2020).The soil of garbage dumps was investigated and isolated *A. niger* (MZ832174), *A. nidulans* (MT919276), and *R. nigricans*. After 20 days, the fungal species with the highest DEHP degradation rate in urine bags was *A. niger*, followed by *R. nigricans* and *A. nidulans*. The most DEHP-degrading fungus species in blood bags was *A. niger*, followed by *A. nidulans* and *R. nigricans*. SEM was employed to understand the deterioration of DEHP (E. A. M. Ali et al., 2023).*F. culmorum*was procured from the Research Centre for Biological Sciences culture collection at Universidad Autónoma deTlaxcala, Mexico. For the degradation of a high concentration of DEHP (3 g/L) as the only carbon and energy source, the fungus was grown in solid-state fermentation (SSF), where the biodegradation reached 96.9% in 312 hours. In cultures treated with DEHP, this fungus developed an esterase activity three times higher than in control

835 cultures (1288.9 and 443.2 U/L, respectively). Using zymography, nine bands exhibiting
836 esterase activity (24.6, 31.2, 34.2, 39.5, 42.8, 62.1, 74.5, 134.5, and 214.5 kDa) in DEHP-
837 supplemented cultures were detected. These bands differed from control cultures (Hernández-
838 Sánchez et al., 2024) (Table No. 6).

839 Linear Low-Density Polyethylene (LLDPE)

840 The mix culture of *A. niger*, *P. funiculosum*, *C. globosum*, *G. virens*, and *Pullularia*
841 *pullulans* demonstrated the ability to biodegrade LLDPE and maleated LLDPE with corn
842 starch blends (>30%) in 28 days. The recorded weight loss was 0.37% and 0.20% for LLDPE
843 and MA-g-LLDPE respectively. It was further confirmed by SEM, DSC, TGA,
844 FTIR (Chandra & Rustgi, 1997). *Aspergillus* and *Penicillium* have been shown to break down
845 LLDPE in three months, as demonstrated by DSC and FTIR tests (Ojeda et al., 2009).
846 *P. chrysosporium* ATCC 34541, procured from Deutsche Sammlung von Mikroorganismen
847 und Zellkulturen (DSMZ), demonstrated the ability to degrade oxo-biodegradable LLDPE
848 films (12 microns) designed for mulching applications over 180 days, confirmed through
849 FTIR, DSC, TGA, and GPC analysis (Corti et al., 2012). According to enzymatic activity,
850 *A. terreus*, *A. wentii*, and *Emericella nidulans* which were isolated from waste material soil,
851 decomposed LLDPE and LLDPE mixed with High Molecular Weight (HmHDPE) in three
852 months (Poonam et al., 2013). *T. hamatum* FR87271 decomposed LLDPE within seven days
853 after being extracted from plastic waste found in the soil. The weight reduction for untreated
854 virgin plastic and LLDPE treated with γ irradiation followed by 90°C temperature showed
855 $2.2 \pm 1.2\%$ and $3.9 \pm 0.5\%$, respectively. The test was supported by FTIR, TGA, GPC and SEM
856 (Malachová et al., 2020). Among the microbes tested, the most active plastic-consuming
857 fungus was *Debaryomyces hansenii* (MK394103.1), found in agricultural soil. Compared to
858 plastic film, it reduced LLDPE MPs by 2.5-5.5% in 30 days when it was in powder form.
859 Some other, as-yet-unidentified fungi also demonstrated plastic-consuming capabilities up to
860 some extent. FESEM validated it further (Salinas et al., 2023) (Table No. 6).

861 Poly (butylene succinate adipate) (PBSA)

862 In aerobic soil study, *Aspergillus sp.*, *Cunninghamella sp.* and *Thermomyces sp.* were
863 found at 30°C degrading PBSA in 25 days. It was confirmed by weight measurement and
864 analysis of soil (Nishide et al., 1999). In 50 days, the SEM test verified that *Penicillium spp.*
865 isolated from soil had effectively broken-down PBSA (Kamiya et al., 2007). Within ten days
866 enzymatic activity and a SEM test have indicated that *P. chrysanthemicola* (FJ426987), which
867 was isolated from healthy leaves of wheat, barley, and rice grown in fields, successfully
868 wiped out PBSA film (Bionolle 3001 G) (20 μ m) (Koitabashi et al., 2012). Enzymatic
869 degradation and SEM confirm that in 7 days, *P. antarctica* JCM 10317, *U. maydis* MAFF
870 236374, 236375, 236376, 236377, 236378, and *S. cerevisiae* BY4741 from culture
871 collections of Japan, NIAS General Bank Japan, and EUROSCARF, Germany, degraded
872 PBSA film (Shinozaki et al., 2013). *C. magma*, *C. s. magnus* JCM 9038 (CBS
873 140), *Filobasidium floriforme* JCM 10631 (CBS 6241), *P. antarctica* JCM 10317 procured
874 from Japan Collection of Microorganisms of the Riken Bio- resource Center, Japan which
875 were isolated from larval midgut of *A. laevis collis* showed degradation of PBSA in 4 days. The
876 confirmation was done on the basis of enzyme production (Suzuki et al., 2013). Previously

isolated *Paraphoma* sp. from barley, successfully degraded PBSA films in 7 days as proved by the enzymatic degradation test(Koitaishi et al., 2016). *Paraphoma* sp. Strain B47-9 degraded PBSA of 20µm in 8 hours by enzyme production. It was analysed and confirmed by gel electrophoresis(Sameshima-Yamashita et al., 2016). *P. antarctica* (PaE) and *Paraphoma* sp. B47-9 (PCLE) have degraded PBSA (Bionolle #3020) in 1-4 hrs, which was confirmed using LCMS(Sato et al., 2017). Previously isolated rice leaf-derived *P. antarctica* strain NRL-A and rice husk-derived *P. antarctica* strains GB-4(1) Wand GB11-W as well as *P. antarctica* JCM 10317 from the Japan Collection of Microorganisms (JCM) of the Riken Bio Resource Centre degraded PBSA film (20 mm) in three days, as confirmed by SEM(Kitamoto et al., 2018). In just one month, PCL, PBS, and PBSA were successfully degraded by *Geomyces* sp. (B10I), *Sclerotinia*, *Fusarium* sp. (B30M), *Mortierella*, and *H.anomala* isolated from soil, as demonstrated by the establishment of a clear zone(Urbanek et al., 2021).PBSA films were damaged in 28 days by *A. fumigatus* L30 and *A.terreus* HC (78 % weight loss) which were isolated from farming soil. This was verified by SEM, NMR and enzymatically(Chien et al., 2022). *Fusarium* sp. grown in *in-situ* soil degraded PBSA in 55 days. The production of CO₂ and enzymatic activity were used to verify the degradation(Tsuboi et al., 2024) (Table No. 6).

Other types of Plastic

P. ostreatus, *P.chrysosporium*, *T. versicolor* (ATCC11235), cultures from culture collection of the Institute of Forstbotanic of The Universitat Gottingen, 3400-Gottingen, Germany and *Gloeophyllumtrabeum*, *Phlebia radiata* from Collection of Bundesanstalt fur Materialforschungundprufung, Berlin, Germany, Lignin/styrene products 10.3 (LPS10), 32.2 (LPS32), and 50.4 (LPS50) wt% lignin and lignin/ methyl methacrylate (1 1 to 18 wt% lignin) in 68 days. The significant weight loss was recorded for LPS 50 and LPS 32 by 50.41 and 32.17, respectively. SEM analysis, UV-spectrometry, and synthesis of polymerizates served as degradation confirmation(Milstein et al., 1996).In 15 days,*Phanerochetechrysosporium* degraded PVA successfully. It was confirmed by GPC, FTIR, HPLC(Betty Lucy López et al., 1999). In 12 weeks, *Fusarium* L023 degraded polylactic co-glycolide (PLGA43/57)91.1% b weight, which was confirmed by DSC, SEM and change in viscosity tests(Cai et al., 2001). The biodegradation of E-P copolymers was conducted using *A. niger* obtained from the NCL, India. Weight losses of 10% for E-P (F 30R), and less than 15% for E-P (Q 30R) were observed after 6 months of being exposed to 100 hours of UV-irradiation in compost(Pandey & Singh, 2001).The process of decomposing polyamide-6 involved utilization by a lignolytic fungus,*P.chrysosporium*MZKI B223 which was procured from the Fungal Culture Collection of the National Institute of Chemistry. It exhibited a 50% reduction in weight after 5 months. The deterioration was further supported by DSC, relative viscosity and SEM analysis(Klun et al., 2003). GPC and SEM tests has confirmed that *Inonotus hispidus* has degraded ploysteramides and caprolactone in 32 to 90 days(Šašek et al., 2006).*A.clavatus* isolated from both dry and moist soil, completely metabolisedPES in 20 to several days, as shown by the SEM and enzyme production assays(Ishii et al., 2007).A pure culture of *A. niger*, degraded PS: PLA (30%) PS: PLA: OMMT (5%) by 4.9% and 6% reduction in tensile strength in 28 days respectively. The confirmatory tests were TGA, SEM, FTIR and XRD(Barkoula et al., 2008). Synthesized

copolymers of lactic acid, terephthalic acid, and ethylene glycol were degraded in 60 days by *A. niger*, *A. versicolor*, *A. clavatus*, *A. fumigatus*, *A. alternata*, *Mucor sp.*, *Penicillium sp.*, and *Rhizopus sp.* FTIR and SEM tests verified the change in condition (Soni et al., 2009). *A. niger* consumed ethylene-propylene copolymer (EP) in 6 months, as demonstrated by SEM, FTIR and viscosity variation (Alariqi & Singh, 2010). *A. niger* ATCC 9642, *P. pinophilum* ATCC 11, 797, *Chaetomium globosum* ATCC 6205, *G. virens* ATCC 9645, and *Aureobasium pullulans* ATCC 15, 233 were procured from Guangzhou institute of microbiology. Consortium of these fungal strains degraded starch-based elastomers, polyethylene-octene (POE), starch and grafted POE-g-MAH (acid anhydride) and starch copolymer blends in 28 days, which were confirmed by tensile strength and SEM (Z. Yang et al., 2010).

TGA and SEM tests have verified that in 45 days, thermoplastic grafted starch (TPGS) and ungrafted starch (TPS) was degraded by *A. niger* (Canché-Escamilla et al., 2011). Within 24 days *Fusarium sp.* DMT-5-3 and *Trichosporon sp.* DMI-5-1, which were isolated from mangrove sediments, have been shown to degrade dimethyl phthalate (DMP), dimethyl isophthalate (DMI), and dimethyl terephthalate (DMT) as per an enzymatic assay (Luo et al., 2012). *Fusarium sp.* isolated from garden soil and waste leachate degraded Polycarbonate (PC) in 15 days. The confirmatory tests were clear zone formation and AFM (Arefian et al., 2013). *Chaetomium sp.* isolated from agricultural soil, demonstrated the potential for breaking down biodegradable mulch films (BDM) used in agriculture, as indicated by clear zone formation and SEM analysis after 10 weeks (Bailes et al., 2013). *P. pulmonarius*, two strains of *P. ostreatus*, and *P. floridae* were obtained from the Chinese University of Hong Kong Collection, the American Type Culture Collection, and the Universidad Autonoma de Tlaxcala Collection, respectively. *F. oxysporum* and *M. alpina* were isolated from soil in central Manchester, UK. Media containing 500 mg per liter DBP showed the highest biomass production by *F. oxysporum* and *M. alpina*, with quantities of 160 and 65 mg/cm² in 7 days respectively (Suárez-Segundo et al., 2013). *T. versicolor* ATCC 42530, taken from the American Type Culture Collection and *L. tigrinus* CBS 577.79 procured from Central Bureau Voor Schimmel Cultures [Utrecht, NL], demonstrated the ability to degrade highly recalcitrant PAHs in industrially polluted soil within 60 days (Lladó et al., 2013). *Fusarium*, *Ulocladium*, *Chrysosporium*, and *Penicillium* were isolated from a PC-contaminated garden, and waste leachate exhibited a degradation of PC within a week. Further confirmation was done by a clear zone of amylase and lipase, and AFM (Arefian et al., 2013). *Candida guilliermondii* and *A. fumigatus* taken from Culture Collection of Basidiomycetes, Czech Republic, degraded Polyester amides in 6 weeks. Enzyme production (lipase and esterase) served as confirmation of degradation (Novotný et al., 2015). The label "70 TPF" refers to the combination of thermoplastic unripe banana flour and polyethylene in a 70:30 ratio. It remained buried in compost for 125 days. The fungus *M. elongata* was shown to thrive on plastic, leading to a decrease in its weight (45.23%) and tensile strength (Vieyra et al., 2015). *T. versicolor* procured from National Collection of Biology Laboratory, University of Tehran, Iran has degraded TPS, Cellulose Nanofibers (CNFs) in the duration of 2 months, which was confirmed by SEM and dynamical thermal analysis (DMA) (Babaei et al., 2015). *P. antarctica* (PaE) and *Paraphoma sp.* B47-9 (PCLE) have degraded poly(butylene adipate) (PBA) in 1-4 hrs, which was confirmed using LCMS (Sato et al., 2017). Through enzymatic degradation, *Coriopsis byrsina*, which was isolated from the Wonorejo Mangrove soil in

Indonesia, broke down synthetic plastic in six weeks, resulting in a 22.7% weight loss (Kuswytasari et al., 2019). The degradation of hexadecane, derived from municipal trash, was seen to occur within a period of 14 days by the action of *A. flavus* MH503926 with 52.92±8.81% weight loss. This deterioration was confirmed through the use of both GCMS and SEM (M. Perera et al., 2019). SEM and EDX analyses revealed that *Clitocybe sp.* and *Laccaria laccata*, exhibited the ability to degrade polylactide within a period of 6 months (Janczak et al., 2020). The PBAT-thermoplastic starch underwent effective degradation by the *Aspergillus sp.* and *Penicillium sp.* cultures in 30-day period, resulted in degradation rates of 1.04% and 2.32% respectively. The test confirmation was conducted using SEM and FTIR techniques (T. A. De Oliveira et al., 2020).

Dry weight measurement, titration assay, and SEM analysis verified that *M. roreri*, isolated from cacao pods, produced cutinase that broke down polyethylene succinate (PES) 59% by weight in 21 days (Vázquez-Alcántara et al., 2021). By producing enzymes, *P. sordida* YK-624, which was obtained from a culture, broke down Bisphenol F (BPF) in 14 days. Transcriptome analysis under ligninolytic conditions, was used to identify the ligninolytic enzymes (Wang et al., 2021). As demonstrated by increased esterase activity during liquid fermentation, *F. culmorum* and *F. oxysporum* degraded dibutyl phthalate (DBP) in 7 days (González-Márquez et al., 2021). *Myrothecium roridum* IM 6482, retrieved from a culture, eradicated Bisphenol A (BPA) in 72 hours, as demonstrated by cellular and subcellular enzyme production and LC-MS/MS analysis (Jasińska et al., 2021). *A. flavus* found in the field soil, degraded compostable microplastic films in a year, as demonstrated by ATR-FTIR analysis (Pedrini, 2022). A single species of fungus, specifically *Acremonium sp.*, was identified as capable of decomposing three PAHs, phenanthrene, anthracene, and pyrene within a 30-day period, which was found inside plastic fuel bottles. The deterioration was confirmed by ultra-high-performance chromatography (UHPLC) (Héctor et al., 2022). DBP was catabolized in 15 days by *A. flavus*, an isolate from the sanitary landfill soil. The GC-MS characterizations revealed the formation of intermediate metabolites such as benzyl-butyl phthalate, dimethyl-phthalate, di-iso-butyl-phthalate and phthalic acid (Puranik et al., 2023). *P. lilacinum* strain BA1S isolated from farmland soil degraded biodegradable PBAT 15% by weight in 30 days. It was confirmed by SEM, FTIR and LCMS (Tseng et al., 2023). *Phanerochaete sp.* H2, an endophytic fungus isolated from the leaves of *Handroanthus impetiginosus*, was used to remove BPA. Polyacrylonitrile nanofibrous membrane (PAN NFM) used as a scaffold to accomplish BPA degradation in just seven days. SEM was used to detect the deterioration (Conceição et al., 2023) (Table No. 7).

Conclusion

In this presented phase of our inquiry, we focused on the advantages, consequences, and environmental impacts of fungal plastic degradation. We find out its remarkable ability to substantially reduce plastic waste and conserve natural ecosystem. This review opens the doors for understanding the plastic as a problem as well as using fungi as its mitigation. We have also focused on the understanding of the dynamic and promising area of fungal plastic degradation and its crucial role with the hope of a better future.

1006 Considering an extensive review of the literature, we can confirm that fungi can be
1007 used to decompose plastic, which is one of the worst wastes of time. Also, we concluded that
1008 LDPE was the most common substance that degraded. Whereas, on the other hand PBS and
1009 PBSA appeared to be the fastest degrading polymer with the degrading time as low as 1-4
1010 hours. The most promising fungal strain is found to be the various species of *Aspergillus*
1011 primarily isolated from dumpsite and soil. The most convenient screening and confirming
1012 technique appeared to be weight loss and FTIR. It can also be said that fungi degrade faster
1013 when they are set together for work.

1014 However, in addition to its promise, we must also consider the difficulties and
1015 limitations associated with employing fungi for plastic degradation. These concerns include
1016 the ability to handle increased size or capacity, ensuring precision in targeting particular types
1017 of plastics, managing the rules that regulate the release of genetically modified fungi into the
1018 environment. As we look to the future, we understand how crucial it is to preserve a balance
1019 between progress and environmental conservation.

1021 Acknowledgements

1022 The authors are grateful to Dr. Aniket Gade for his valuable help in collection of
1023 data. We are thankful to MAHAJYOTI for their financial assistance. We sincerely thank the
1024 authorities of Homi Bhabha State University, The Institute of Science, Mumbai, and
1025 Elphinstone College for providing resources to carry out this work.

1030 Reference

- 1031 Abdel-Motaal, F. F., El-Sayed, M. A., El-Zayat, S. A., & Ito, S. ichi. (2014). Biodegradation
1032 of poly (ϵ -caprolactone) (PCL) film and foam plastic by *Pseudozyma japonica* sp. nov.,
1033 a novel cutinolytic ustilaginomycetous yeast species. *3 Biotech*, 4(5), 507–512.
1034 <https://doi.org/10.1007/s13205-013-0182-9>
- 1035 Abe, M., Kobayashi, K., Honma, N., & Nakasaki, K. (2010). Microbial degradation of
1036 poly(butylene succinate) by *Fusarium solani* in soil environments. *Polymer Degradation*
1037 *and Stability*, 95(2), 138–143. <https://doi.org/10.1016/j.polymdegradstab.2009.11.042>
- 1038 Ahuactzin-Pérez, M., Tlecuitl-Beristain, S., García-Dávila, J., González-Pérez, M., Gutiérrez-
1039 Ruíz, M. C., & Sánchez, C. (2016). Degradation of di(2-ethyl hexyl) phthalate by
1040 *Fusarium culmorum*: Kinetics, enzymatic activities and biodegradation pathway based
1041 on quantum chemical modeling pathway based on quantum chemical modeling. *Science*
1042 *of the Total Environment*, 566–567, 1186–1193.
1043 <https://doi.org/10.1016/j.scitotenv.2016.05.169>
- 1044 Al Hosni, A. S., Pittman, J. K., & Robson, G. D. (2019). Microbial degradation of four
1045 biodegradable polymers in soil and compost demonstrating polycaprolactone as an ideal
1046 compostable plastic. *Waste Management*, 97, 105–114.

- 1047 <https://doi.org/10.1016/j.wasman.2019.07.042>
- 1048 Alariqi, S. A. S., & Singh, R. P. (2010). Effect of γ -Dose rate on Biodegradation of γ -
- 1049 Sterilized Biomedical Polyolefins. *Journal of Polymers and the Environment*, 18(4),
- 1050 600–607. <https://doi.org/10.1007/s10924-010-0217-9>
- 1051 Albertsson, A. C., Renstad, R., Erlandsson, B., Eldsater, C., & Karlsson, S. (1998). Effect of
- 1052 processing additives on (bio)degradability of film-blown poly(ϵ -caprolactone). *Journal*
- 1053 *of Applied Polymer Science*, 70(1), 61–74. [https://doi.org/10.1002/\(sici\)1097-](https://doi.org/10.1002/(sici)1097-4628(19981003)70:1<61::aid-app8>3.3.co;2-f)
- 1054 4628(19981003)70:1<61::aid-app8>3.3.co;2-f
- 1055 Ali, E. A. M., Abdel-Rahman, T. M. A., Ali, D. M. I., & Gamal, A. S. H. (2023). Fungal
- 1056 Bioremediation of the Plasticizer Hazardous Compound di-2-Ethylhexyl Phthalate
- 1057 (DEHP) in Urine and Blood Bags. *Iranian Journal of Science*, 47(3), 673–682.
- 1058 <https://doi.org/10.1007/s40995-023-01466-y>
- 1059 Ali, M. I., Ahmed, S., Robson, G., Javed, I., Ali, N., Atiq, N., & Hameed, A. (2014).
- 1060 Isolation and molecular characterization of polyvinyl chloride (PVC) plastic degrading
- 1061 fungal isolates. *Journal of Basic Microbiology*, 54(1), 18–27.
- 1062 <https://doi.org/10.1002/jobm.201200496>
- 1063 Ali, M. I., Perveen, Q., Ahmad, B., Javed, I., Razi-Ul-Hussnain, R., Andleeb, S., Atique, N.,
- 1064 Ghumro, P. B., Ahmed, S., & Hameed, A. (2009). Studies on biodegradation of
- 1065 cellulose blended polyvinyl chloride films. *International Journal of Agriculture and*
- 1066 *Biology*, 11(5), 577–580.
- 1067 Anbalagan, S., Venkatakrisnan, H. R. R., Ravindran, J., Sathyamoorthy, J., Rangabashyam,
- 1068 K. A., Ragini, Y. P., Sathasivam, J., & Sureshababu, K. (2022). Hydrolytic degradation of
- 1069 polyethylene terephthalate by cutinase enzyme derived from fungal biomass– molecular
- 1070 characterization. *Biointerface Research in Applied Chemistry*, 12(1), 653–667.
- 1071 <https://doi.org/10.33263/BRIAC121.653667>
- 1072 Arefian, M., Zia, M., Tahmourespour, A., & Bayat, M. (2013). Polycarbonate biodegradation
- 1073 by isolated molds using clear-zone and atomic force microscopic methods. *International*
- 1074 *Journal of Environmental Science and Technology*, 10(6), 1319–1324.
- 1075 <https://doi.org/10.1007/s13762-013-0359-0>
- 1076 Awasthi, S., Srivastava, N., Singh, T., Tiwary, D., & Mishra, P. K. (2017). Biodegradation of
- 1077 thermally treated low density polyethylene by fungus *Rhizopus oryzae* NS 5. *3 Biotech*,
- 1078 7(1), 1–8. <https://doi.org/10.1007/s13205-017-0699-4>
- 1079 Babae, M., Jonoobi, M., Hamzeh, Y., & Ashori, A. (2015). Biodegradability and mechanical
- 1080 properties of reinforced starch nanocomposites using cellulose nanofibers. *Carbohydrate*
- 1081 *Polymers*, 132, 1–8. <https://doi.org/10.1016/j.carbpol.2015.06.043>
- 1082 Bailes, G., Lind, M., Ely, A., Powell, M., Moore-Kucera, J., Miles, C., Inglis, D., &
- 1083 Brodhagen, M. (2013). Isolation of native soil microorganisms with potential for
- 1084 breaking down biodegradable plastic mulch films used in agriculture. *Journal of*
- 1085 *Visualized Experiments*, 75, 1–11. <https://doi.org/10.3791/50373>
- 1086 Balasubramanian, V., Natarajan, K., Rajeshkannan, V., & Perumal, P. (2014). Enhancement
- 1087 of in vitro high-density polyethylene (HDPE) degradation by physical, chemical, and
- 1088 biological treatments. *Environmental Science and Pollution Research*, 21(21), 12549–
- 1089 12562. <https://doi.org/10.1007/s11356-014-3191-2>
- 1090 Barkoula, N. M., Alcock, B., Cabrera, N. O., & Peijs, T. (2008). Flame-Retardancy

- 1091 Properties of Intumescent Ammonium Poly(Phosphate) and Mineral Filler Magnesium
1092 Hydroxide in Combination with Graphene. *Polymers and Polymer Composites*, 16(2),
1093 101–113. <https://doi.org/10.1002/pc>
- 1094 Barratt, S. R., Ennos, A. R., Greenhalgh, M., Robson, G. D., & Handley, P. S. (2003). Fungi
1095 are the predominant micro-organisms responsible for degradation of soil-buried
1096 polyester polyurethane over a range of soil water holding capacities. *Journal of Applied*
1097 *Microbiology*, 95(1), 78–85. <https://doi.org/10.1046/j.1365-2672.2003.01961.x>
- 1098 Beg, M. D. H., Kormin, S., Bijarimi, M., & Zaman, H. U. (2015). Environmentally
1099 degradable sago starch filled low-density polyethylene. *Journal of Polymer Engineering*,
1100 35(6), 551–563. <https://doi.org/10.1515/polyeng-2014-0293>
- 1101 Bernat, P., Jasińska, A., Niedziałkowska, K., Słaba, M., Różalska, S., Paraszkiwicz, K., Sas-
1102 Paszt, L., & Heipieper, H. J. (2023). Adaptation of the metolachlor-degrading fungus
1103 *Trichoderma harzianum* to the simultaneous presence of low-density polyethylene
1104 (LDPE) microplastics. *Ecotoxicology and Environmental Safety*, 267(October).
1105 <https://doi.org/10.1016/j.ecoenv.2023.115656>
- 1106 Betty Lucy López, O., Amanda Inés Mejía, G., & Ligia Sierra, G. (1999). Biodegradability of
1107 poly(vinyl alcohol). *Polymer Engineering and Science*, 39(8), 1346–1352.
1108 <https://doi.org/10.1002/pen.11523>
- 1109 Bhavsar, P., Bhawe, M., & Webb, H. K. (2024). Effective multi-stage biodegradation of
1110 commercial bulk polyurethane by *Clonostachys* and *Purpureocillium* spp. *Science of the*
1111 *Total Environment*, 908(October 2023), 168329.
1112 <https://doi.org/10.1016/j.scitotenv.2023.168329>
- 1113 Bong, S., Lii, W., Wong, C., Al-Obaidi, J. R., Rahmad, N., Mujahid, A., & Müller, M.
1114 (2017). Malaysian Journal of Microbiology Ability of endophytic fungi isolated from
1115 *Nepenthes ampullaria* to degrade polyurethane. *Malaysian Journal of Microbiology*,
1116 13(3), 172–179.
1117 https://pdfs.semanticscholar.org/49f1/975aecffd27b4f9c013033410ea80e4845ef.pdf?_ga=2.113004036.1202168521.1560519827-2109118846.1559721676
- 1119 Brunner, I., Fischer, M., Rüthi, J., Stierli, B., & Frey, B. (2018). Ability of fungi isolated
1120 from plastic debris floating in the shoreline of a lake to degrade plastics. *PLoS ONE*,
1121 13(8), 1–14. <https://doi.org/10.1371/journal.pone.0202047>
- 1122 Butnaru, E., Darie-Niță, R. N., Zaharescu, T., Balaeș, T., Tănase, C., Hitruc, G., Doroftei, F.,
1123 & Vasile, C. (2016). Gamma irradiation assisted fungal degradation of the
1124 polypropylene/biomass composites. *Radiation Physics and Chemistry*, 125, 134–144.
1125 <https://doi.org/10.1016/j.radphyschem.2016.04.003>
- 1126 Cai, Q., Bei, J., Luo, A., & Wang, S. (2001). Biodegradation behaviour of poly(lactide-co-
1127 glycolide) induced by microorganisms. *Polymer Degradation and Stability*, 71(2), 243–
1128 251. [https://doi.org/10.1016/S0141-3910\(00\)00153-1](https://doi.org/10.1016/S0141-3910(00)00153-1)
- 1129 Canché-Escamilla, G., Canché-Canché, M., Duarte-Aranda, S., Cáceres-Farfán, M., &
1130 Borges-Argáez, R. (2011). Mechanical properties and biodegradation of thermoplastic
1131 starches obtained from grafted starches with acrylics. *Carbohydrate Polymers*, 86(4),
1132 1501–1508. <https://doi.org/10.1016/j.carbpol.2011.06.052>
- 1133 Catto, A. L., Montagna, L. S., Almeida, S. H., Silveira, R. M. B., & Santana, R. M. C.
1134 (2016). Wood plastic composites weathering: Effects of compatibilization on

- biodegradation in soil and fungal decay. *International Biodeterioration and Biodegradation*, 109, 11–22. <https://doi.org/10.1016/j.ibiod.2015.12.026>
- Chandra, R., & Rustgi, R. (1997). Biodegradation of maleated linear low-density polyethylene and starch blends. *Polymer Degradation and Stability*, 56(2), 185–202. [https://doi.org/10.1016/S0141-3910\(96\)00212-1](https://doi.org/10.1016/S0141-3910(96)00212-1)
- Chaudhary, A. K., Chaitanya, K., Dalmia, R., & Vijayakumar, R. P. (2021). Synergistic effect of UV, thermal, and chemical treatment on biological degradation of low-density polyethylene (LDPE) by *Thermomyces lanuginosus*. *Environmental Monitoring and Assessment*, 193(8), 1–11. <https://doi.org/10.1007/s10661-021-09296-4>
- Chaudhary, A. K., Chittriv, S. P., & Vijayakumar, R. P. (2022). Influence of nitric acid on biodegradation of polystyrene and low-density polyethylene by *Cephalosporium* species. *Archives of Microbiology*, 204(8), 1–10. <https://doi.org/10.1007/s00203-022-03089-0>
- Chaves, M. R. B., Lima, M. L. S. O., Malafatti-Picca, L., De Angelis, D. A., De Castro, A. M., Valoni, É., & Marsaioli, A. J. (2018). A practical fluorescence-based screening protocol for polyethylene terephthalate degrading microorganisms. *Journal of the Brazilian Chemical Society*, 29(6), 1278–1285. <https://doi.org/10.21577/0103-5053.20170224>
- Chien, H. L., Tsai, Y. T., Tseng, W. S., Wu, J. A., Kuo, S. L., Chang, S. L., Huang, S. J., & Liu, C. Te. (2022). Biodegradation of PBSA Films by Elite *Aspergillus* Isolates and Farmland Soil. *Polymers*, 14(7). <https://doi.org/10.3390/polym14071320>
- Conceição, J. C. S., Alvarega, A. D., Mercante, L. A., Correa, D. S., & Silva, E. O. (2023). Endophytic fungus from *Handroanthus impetiginosus* immobilized on electrospun nanofibrous membrane for bioremoval of bisphenol A. *World Journal of Microbiology and Biotechnology*, 39(10). <https://doi.org/10.1007/s11274-023-03715-z>
- Corti, A., Sudhakar, M., & Chiellini, E. (2012). Assessment of the Whole Environmental Degradation of Oxo-Biodegradable Linear Low Density Polyethylene (LLDPE) Films Designed for Mulching Applications. *Journal of Polymers and the Environment*, 20(4), 1007–1018. <https://doi.org/10.1007/s10924-012-0493-7>
- Cosgrove, L., McGeechan, P. L., Robson, G. D., & Handley, P. S. (2007). Fungal communities associated with degradation of polyester polyurethane in soil. *Applied and Environmental Microbiology*, 73(18), 5817–5824. <https://doi.org/10.1128/AEM.01083-07>
- Da Luz, J. M. R., Paes, S. A., Bazzolli, D. M. S., Tótola, M. R., Demuner, A. J., & Kasuya, M. C. M. (2014). Abiotic and biotic degradation of oxo-biodegradable plastic bags by *Pleurotus ostreatus*. *PLoS ONE*, 9(11). <https://doi.org/10.1371/journal.pone.0107438>
- da Luz, J. M. R., Paes, S. A., Nunes, M. D., da Silva, M. de C. S., & Kasuya, M. C. M. (2013). Degradation of Oxo-Biodegradable Plastic by *Pleurotus ostreatus*. *PLoS ONE*, 8(8), 1–8. <https://doi.org/10.1371/journal.pone.0069386>
- Da Luz, J. M. R., Paes, S. A., Ribeiro, K. V. G., Mendes, I. R., & Kasuya, M. C. M. (2015). Degradation of green polyethylene by *Pleurotus ostreatus*. *PLoS ONE*, 10(6). <https://doi.org/10.1371/journal.pone.0126047>
- Das, M. P., & Kumar, S. (2014). Microbial deterioration of low density polyethylene by *Aspergillus* and *Fusarium* sp. *International Journal of ChemTech Research*, 6(1), 299–305.

- 1179 Das, M. P., Kumar, S., & Das, J. (2018). Fungal-mediated deterioration and biodegradation
1180 study of low-density polyethylene (LDPE) isolated from municipal dump yard in
1181 Chennai, India. *Energy, Ecology and Environment*, 3(4), 229–236.
1182 <https://doi.org/10.1007/s40974-018-0085-z>
- 1183 El-Dash, H. A., Yousef, N. E., Aboelazm, A. A., Awan, Z. A., Yahya, G., & El-Ganiny, A.
1184 M. (2023). Optimizing Eco-Friendly Degradation of Polyvinyl Chloride (PVC) Plastic
1185 Using Environmental Strains of *Malassezia* Species and *Aspergillus fumigatus*.
1186 *International Journal of Molecular Sciences*, 24(20).
1187 <https://doi.org/10.3390/ijms242015452>
- 1188 El-Morsy, E., Hassan, H., & Ahmed, E. (2017). Biodegradative activities of fungal isolates
1189 from plastic contaminated soils. *Mycosphere*, 8(8), 1071–1086.
1190 <https://doi.org/10.5943/mycosphere/8/8/13>
- 1191 El-Sayed, M. T., Rabie, G. H., & Hamed, E. A. (2021). Biodegradation of low-density
1192 polyethylene (LDPE) using the mixed culture of *Aspergillus carbonarius* and A.
1193 *fumigatus*. *Environment, Development and Sustainability*, 23(10), 14556–14584.
1194 <https://doi.org/10.1007/s10668-021-01258-7>
- 1195 Elsamahy, T., Sun, J., Elsilk, S. E., & Ali, S. S. (2023). Biodegradation of low-density
1196 polyethylene plastic waste by a constructed tri-culture yeast consortium from wood-
1197 feeding termite: Degradation mechanism and pathway. *Journal of Hazardous Materials*,
1198 448(November 2022), 130944. <https://doi.org/10.1016/j.jhazmat.2023.130944>
- 1199 Emmanuel-Akerele, H. A., & Akinyemi, P. O. (2022). Physico-Chemical and
1200 Microbiological Assessment of Soils from Dumpsites for Plastic Degrading
1201 Microorganisms. *Pollution*, 8(2), 501–512.
1202 <https://doi.org/10.22059/POLL.2021.330648.1186>
- 1203 Esmaeili, A., Pourbabaee, A. A., Alikhani, H. A., Shabani, F., & Kumar, L. (2014).
1204 Colonization and biodegradation of photo-oxidized low-density polyethylene (LDPE) by
1205 new strains of *Aspergillus* sp. and *Lysinibacillus* sp. *Bioremediation Journal*, 18(3),
1206 213–226. <https://doi.org/10.1080/10889868.2014.917269>
- 1207 Ferreira, F. G. D., de Andrade Lima, M. A. G., de Almeida, Y. M. B., & Vinhas, G. M.
1208 (2010). Biodegradation of LDPE/Modified starch blends sterilized with gamma
1209 radiation. *Journal of Polymers and the Environment*, 18(3), 196–201.
1210 <https://doi.org/10.1007/s10924-010-0202-3>
- 1211 Gajendiran, A., Krishnamoorthy, S., & Abraham, J. (2016). Microbial degradation of low-
1212 density polyethylene (LDPE) by *Aspergillus clavatus* strain JASK1 isolated from
1213 landfill soil. *3 Biotech*, 6(1), 1–6. <https://doi.org/10.1007/s13205-016-0394-x>
- 1214 Gao, R., Liu, R., & Sun, C. (2022). A marine fungus *Alternaria alternata* FB1 efficiently
1215 degrades polyethylene. *Journal of Hazardous Materials*, 431(January), 128617.
1216 <https://doi.org/10.1016/j.jhazmat.2022.128617>
- 1217 Ghosh, S. K., & Pal, S. (2021). De-polymerization of LDPE plastic by *Penicillium*
1218 *simplicissimum* isolated from municipality garbage plastic and identified by ITSs locus
1219 of rDNA. *Vegetos*, 34(1), 57–67. <https://doi.org/10.1007/s42535-020-00176-9>
- 1220 Gómez-Méndez, L. D., Moreno-Bayona, D. A., Poutou-Piñales, R. A., Salcedo-Reyes, J. C.,
1221 Pedroza-Rodríguez, A. M., Vargas, A., & Bogoya, J. M. (2018). Biodeterioration of
1222 plasma pretreated LDPE sheets by *Pleurotus ostreatus*. *PLoS ONE*, 13(9), 1–28.

- 1223 <https://doi.org/10.1371/journal.pone.0203786>
- 1224 Gong, Z., Jin, L., Yu, X., Wang, B., Hu, S., Ruan, H., Sung, Y. J., Lee, H. G., & Jin, F.
- 1225 (2023). Biodegradation of Low Density Polyethylene by the Fungus *Cladosporium* sp.
- 1226 Recovered from a Landfill Site. *Journal of Fungi*, 9(6).
- 1227 <https://doi.org/10.3390/jof9060605>
- 1228 González-Márquez, A., Volke-Sepulveda, T., Díaz, R., & Sánchez, C. (2021). Enhanced
- 1229 esterase activity during the degradation of dibutyl phthalate by *Fusarium* species in
- 1230 liquid fermentation. *Journal of Industrial Microbiology and Biotechnology*, 48(9–10),
- 1231 1–7. <https://doi.org/10.1093/jimb/kuab062>
- 1232 Gunawan, N. R., Tessman, M., Schreiman, A. C., Simkovsky, R., Samoylov, A. A.,
- 1233 Neelakantan, N. K., Bemis, T. A., Burkart, M. D., Pomeroy, R. S., & Mayfield, S. P.
- 1234 (2020). Rapid biodegradation of renewable polyurethane foams with identification of
- 1235 associated microorganisms and decomposition products. *Bioresource Technology*
- 1236 *Reports*, 11(July), 100513. <https://doi.org/10.1016/j.biteb.2020.100513>
- 1237 Gunawan, N. R., Tessman, M., Zhen, D., Johnson, L., Evans, P., Clements, S. M., Pomeroy,
- 1238 R. S., Burkart, M. D., Simkovsky, R., & Mayfield, S. P. (2022). Biodegradation of
- 1239 renewable polyurethane foams in marine environments occurs through depolymerization
- 1240 by marine microorganisms. *Science of the Total Environment*, 850(September).
- 1241 <https://doi.org/10.1016/j.scitotenv.2022.158761>
- 1242 Hakkarainen, M., Karlsson, S., & Albertsson, A. C. (2000). Rapid (bio)degradation of
- 1243 polylactide by mixed culture of compost microorganisms - Low molecular weight
- 1244 products and matrix changes. *Polymer*, 41(7), 2331–2338.
- 1245 [https://doi.org/10.1016/S0032-3861\(99\)00393-6](https://doi.org/10.1016/S0032-3861(99)00393-6)
- 1246 Hanifi, S., Oromiehie, A., Ahmadi, S., & Farhadnejad, H. (2014). Corn Starch and
- 1247 Montmorillonite Nanocomposite)-Reinforced Polypropylene: Preparation, properties,
- 1248 and biodegradability. *Journal of Vinyl and Additive Technology*, 20(1), 16–23.
- 1249 <https://doi.org/10.1002/vnl.21333>
- 1250 Héctor Mario HERAS-MARTÍNEZ, Laila Nayzzel MUÑOZ-CASTELLANOS, Alejandro
- 1251 BUGARIN, Víctor Hugo RAMOS-SÁNCHEZ, I. S. O. and D. C.-F. (2022).
- 1252 BIODEGRADATION OF POLYCYCLIC AROMATIC HYDROCARBONS BY
- 1253 *Acremonium* sp. ACTIVITY. *Rev. Int. Contam. Ambie.*, 38, 261–269.
- 1254 Hernández-Sánchez, B., Santacruz-Juárez, E., Figueroa-Martínez, F., Castañeda-Antonio, D.,
- 1255 Portillo-Reyes, R., Viniegra-González, G., & Sánchez, C. (2024). A novel and efficient
- 1256 strategy for the biodegradation of di(2-ethylhexyl) phthalate by *Fusarium culmorum*.
- 1257 *Applied Microbiology and Biotechnology*, 108(1), 1–13. [https://doi.org/10.1007/s00253-](https://doi.org/10.1007/s00253-023-12961-y)
- 1258 [023-12961-y](https://doi.org/10.1007/s00253-023-12961-y)
- 1259 Hock, O. G., De Qin, D., Lum, H. W., Hee, C. W., & Shing, W. L. (2020). Evaluation of the
- 1260 plastic degradation ability of edible mushroom species based on their growth and
- 1261 manganese peroxidase activity. *Current Topics in Toxicology*, 16, 65–72.
- 1262 Hung, C. S., Barlow, D. E., Varaljay, V. A., Drake, C. A., Crouch, A. L., Russell, J. N.,
- 1263 Nadeau, L. J., Crookes-Goodson, W. J., & Biffinger, J. C. (2019). The biodegradation of
- 1264 polyester and polyester polyurethane coatings using *Papiliotrema laurentii*. *International*
- 1265 *Biodeterioration and Biodegradation*, 139(November 2018), 34–43.
- 1266 <https://doi.org/10.1016/j.ibiod.2019.02.002>

- 1267 Ibrahim, I. N., Maraqa, A., Hameed, K. M., Saadoun, I. M., & Maswadeh, H. M. (2011).
1268 Assessment of potential plastic-degrading fungi in Jordanian habitats. *Turkish Journal of*
1269 *Biology*, 35(5), 551–557. <https://doi.org/10.3906/biy-0901-9>
1270 Iiyoshi, Y., Tsutsumi, Y., & Nishida, T. (1998). Polyethylene degradation by lignin-
1271 degrading fungi and manganese peroxidase. *Journal of Wood Science*, 44(3), 222–229.
1272 <https://doi.org/10.1007/BF00521967>
1273 Iman, G., Saad, K., Nadhem, H., Hadeel, F., Inaam, A., & Isam, A. (2019). Biodegradability
1274 of microbial synthesized poly- β -hydroxy-butyrate produced from pseudomonas
1275 aeruginosa Dw7 local isolate. *Research Journal of Biotechnology*, 14(Special Issue I),
1276 165–171.
1277 Ishii, N., Inoue, Y., Shimada, K. ichiro, Tezuka, Y., Mitomo, H., & Kasuya, K. ichi. (2007).
1278 Fungal degradation of poly(ethylene succinate). *Polymer Degradation and Stability*,
1279 92(1), 44–52. <https://doi.org/10.1016/j.polymdegradstab.2006.09.014>
1280 Janczak, K., Dąbrowska, G. B., Raszkowska-Kaczor, A., Kaczor, D., Hryniewicz, K., &
1281 Richert, A. (2020). Biodegradation of the plastics PLA and PET in cultivated soil with
1282 the participation of microorganisms and plants. *International Biodeterioration and*
1283 *Biodegradation*, 155(August). <https://doi.org/10.1016/j.ibiod.2020.105087>
1284 Jasińska, A., Soboń, A., Różalska, S., & Średnicka, P. (2021). Bisphenol a removal by the
1285 fungus myrothecium roridum IM 6482—Analysis of the cellular and subcellular level.
1286 *International Journal of Molecular Sciences*, 22(19).
1287 <https://doi.org/10.3390/ijms221910676>
1288 Jayaprakash, V., & Palempalli, U. M. D. (2018). Effect of palmitic acid in the acceleration of
1289 polyethylene biodegradation by Aspergillus oryzae. *Journal of Pure and Applied*
1290 *Microbiology*, 12(4), 2259–2268. <https://doi.org/10.22207/JPAM.12.4.66>
1291 Johnnie, D. A., Issac, R., & Prabha, M. L. (2021). Bio efficacy assay of laccase isolated and
1292 characterized from trichoderma viride in biodegradation of low density polyethylene
1293 (LDPE) and textile industrial effluent dyes. *Journal of Pure and Applied Microbiology*,
1294 15(1), 410–420. <https://doi.org/10.22207/JPAM.15.1.38>
1295 Kamiya, M., Asakawa, S., & Kimura, M. (2007). Molecular analysis of fungal communities
1296 of biodegradable plastics in two Japanese soils. *Soil Science and Plant Nutrition*, 53(5),
1297 568–574. <https://doi.org/10.1111/j.1747-0765.2007.00169.x>
1298 Kang, B. R., Kim, S. Bin, Song, H. A., & Lee, T. K. (2019). Accelerating the biodegradation
1299 of high-density polyethylene (Hdpe) using bjerkandera adusta tbb-03 and lignocellulose
1300 substrates. *Microorganisms*, 7(9). <https://doi.org/10.3390/microorganisms7090304>
1301 Kannahi, M., & Rubini, K. (2012). Biodegradation of polythene bag by Aspergillus oryzae.
1302 *Biosciences Biotechnology Research Asia*, 9(1), 423–426.
1303 <https://doi.org/10.13005/bbra/1018>
1304 Kathiresan, K. (2003). Polythene and Plastics-degrading microbes from the mangrove soil.
1305 *Revista de Biología Tropical*, 51, 3–4.
1306 Khan, S., Ali, S. A., & Ali, A. S. (2023). Biodegradation of low density polyethylene (LDPE)
1307 by mesophilic fungus ‘Penicillium citrinum’ isolated from soils of plastic waste dump
1308 yard, Bhopal, India. *Environmental Technology (United Kingdom)*, 44(15), 2300–2314.
1309 <https://doi.org/10.1080/09593330.2022.2027025>
1310 Khatoon, N., Jamal, A., & Ali, M. I. (2019). Lignin peroxidase isoenzyme: a novel approach

- 1311 to biodegrade the toxic synthetic polymer waste. *Environmental Technology (United*
- 1312 *Kingdom)*, 40(11), 1366–1375. <https://doi.org/10.1080/09593330.2017.1422550>
- 1313 Khruengsaï, S., Sripahco, T., & Pripdeevech, P. (2021). Low-density polyethylene film
- 1314 biodegradation potential by fungal species from thailand. *Journal of Fungi*, 7(8).
- 1315 <https://doi.org/10.3390/jof7080594>
- 1316 Khruengsaï, S., Sripahco, T., & Pripdeevech, P. (2022). Biodegradation of Polyester
- 1317 Polyurethane by *Embarria clematidis*. *Frontiers in Microbiology*, 13(June), 1–12.
- 1318 <https://doi.org/10.3389/fmicb.2022.874842>
- 1319 Kim, M., Lee, A., Yoon, J., & Chin, I. (2000). and Mater-Bi 1 by fungi isolated from soils.
- 1320 *Most*, 36.
- 1321 Kitamoto, H., Yoshida, S., Koitabashi, M., Yamamoto-Tamura, K., Ueda, H., Yarimizu, T.,
- 1322 & Sameshima-Yamashita, Y. (2018). Enzymatic degradation of poly-butylene succinate-
- 1323 co-adipate film in rice husks by yeast *Pseudozyma antarctica* in indoor conditions.
- 1324 *Journal of Bioscience and Bioengineering*, 125(2), 199–204.
- 1325 <https://doi.org/10.1016/j.jbiosc.2017.08.017>
- 1326 Klun, U., Friedrich, J., & Kržan, A. (2003). Polyamide-6 fibre degradation by a lignolytic
- 1327 fungus. *Polymer Degradation and Stability*, 79(1), 99–104.
- 1328 [https://doi.org/10.1016/S0141-3910\(02\)00260-4](https://doi.org/10.1016/S0141-3910(02)00260-4)
- 1329 Koitabashi, M., Noguchi, M. T., Sameshima-Yamashita, Y., Syuntaro, H., Suzuki, K.,
- 1330 Yoshida, S., Watanabe, T., Shinozaki, Y., Tsushima, S., & Kitamoto, H. K. (2012).
- 1331 Degradation of biodegradable plastic mulch films in soil environment by phylloplane
- 1332 fungi isolated from gramineous plants. *AMB Express*, 2(1), 1–10.
- 1333 <https://doi.org/10.1186/2191-0855-2-40>
- 1334 Koitabashi, M., Sameshima-Yamashita, Y., Koike, H., Sato, T., Moriwaki, J., Morita, T.,
- 1335 Watanabe, T., Yoshida, S., & Kitamoto, H. (2016). Biodegradable plastic-degrading
- 1336 activity of various species of *Paraphoma*. *Journal of Oleo Science*, 65(7), 621–627.
- 1337 <https://doi.org/10.5650/jos.ess16067>
- 1338 Kučić Grgić, D., Miloloža, M., Ocelić Bulatović, V., Ukić, Š., Slouf, M., & Gajdosova, V.
- 1339 (2023). Screening the Efficacy of a Microbial Consortium of Bacteria and Fungi Isolated
- 1340 from Different Environmental Samples for the Degradation of LDPE/TPS Films.
- 1341 *Separations*, 10(2). <https://doi.org/10.3390/separations10020079>
- 1342 Kumar, S., Das, M. P., Jeyanthi Rebecca, L., & Sharmila, S. (2013). Isolation and
- 1343 identification of LDPE degrading fungi from municipal solid waste. *Journal of*
- 1344 *Chemical and Pharmaceutical Research*, 5(3), 78–81.
- 1345 Kuswytasari, N. D., Kurniawati, A. R., Alami, N. H., Zulaika, E., Shovitri, M., Oh, K. M.,
- 1346 Puspaningsih, N. N. T., & Ni'Matuzahroh. (2019). Plastic degradation by coriolopsis
- 1347 Byrsina, an identified white-rot, soil-borne mangrove fungal isolate from Surabaya, east
- 1348 java, Indonesia. *Biodiversitas*, 20(3), 867–871. <https://doi.org/10.13057/biodiv/d200334>
- 1349 Łabuzek, S., Nowak, B., & Pająk, J. (2004). The susceptibility of polyethylene modified with
- 1350 bionolle to biodegradation by filamentous fungi. *Polish Journal of Environmental*
- 1351 *Studies*, 13(1), 59–68.
- 1352 Lakshmi, J. P., & Selvi, V. K. (2021). In vitro biodegradation of low-density polyethylene by
- 1353 soil microorganisms. *Research Journal of Chemistry and Environment*, 25(12), 44–52.
- 1354 <https://doi.org/10.25303/2512rjce4452>

- 1355 Lee, S. Y., Ten, L. N., Das, K., You, Y. H., & Jung, H. Y. (2021). Biodegradative Activities
1356 of Fungal Strains Isolated from Terrestrial Environments in Korea. *Mycobiology*, 49(3),
1357 285–293. <https://doi.org/10.1080/12298093.2021.1903131>
- 1358 Li, F., Yu, D., Lin, X., Liu, D., Xia, H., & Chen, S. (2012). Biodegradation of poly(ϵ -
1359 caprolactone) (PCL) by a new *Penicillium oxalicum* strain DSYD05-1. *World Journal of*
1360 *Microbiology and Biotechnology*, 28(10), 2929–2935. [https://doi.org/10.1007/s11274-](https://doi.org/10.1007/s11274-012-1103-5)
1361 012-1103-5
- 1362 Lin, Z., Jin, T., Xu, X., Yin, X., Zhang, D., Geng, M., Pang, C., Luo, G., Xiong, L., Peng, J.,
1363 & Fei, J. (2024). Screening and degradation characteristics of plastic-degrading
1364 microorganisms in film-mulched vegetable soil. *International Biodeterioration and*
1365 *Biodegradation*, 186(October 2023), 105686.
1366 <https://doi.org/10.1016/j.ibiod.2023.105686>
- 1367 Liu, J., Zeng, Q., Lei, H., Xin, K., Xu, A., Wei, R., Li, D., Zhou, J., Dong, W., & Jiang, M.
1368 (2023). Biodegradation of polyester polyurethane by *Cladosporium* sp. P7: Evaluating
1369 its degradation capacity and metabolic pathways. *Journal of Hazardous Materials*,
1370 448(November 2022), 130776. <https://doi.org/10.1016/j.jhazmat.2023.130776>
- 1371 Liu, X., Yu, L., Xie, F., Petinakis, E., Sangwan, P., Shen, S., Dean, K., Ammala, A., &
1372 Wong-Holmes, S. (2013). New evidences of accelerating degradation of polyethylene by
1373 starch. *Journal of Applied Polymer Science*, 130(4), 2282–2287.
1374 <https://doi.org/10.1002/app.39421>
- 1375 Lladó, S., Covino, S., Solanas, A. M., Viñas, M., Petruccioli, M., & D'annibale, A. (2013).
1376 Comparative assessment of bioremediation approaches to highly recalcitrant PAH
1377 degradation in a real industrial polluted soil. *Journal of Hazardous Materials*, 248–
1378 249(1), 407–414. <https://doi.org/10.1016/j.jhazmat.2013.01.020>
- 1379 Luo, Z. H., Pang, K. L., Wu, Y. R., Gu, J. D., Chow, R. K. K., & Vrijmoed, L. L. P. (2012).
1380 Degradation of Phthalate Esters by *Fusarium* sp. DMT-5-3 and *Trichosporon* sp. DMI-5-
1381 1 Isolated from Mangrove Sediments. *Progress in Molecular and Subcellular Biology*,
1382 53, 299–328. https://doi.org/10.1007/978-3-642-23342-5_15
- 1383 Malachová, K., Novotný, Č., Adamus, G., Lotti, N., Rybková, Z., Soccio, M., Šlosarčíková,
1384 P., Verney, V., & Fava, F. (2020). Ability of *Trichoderma hamatum* isolated from
1385 plastics-polluted environments to attack petroleum-based, synthetic polymer films.
1386 *Processes*, 8(4). <https://doi.org/10.3390/PR8040467>
- 1387 Malafatti-picca, L., Ricardo, M., Chaves, D. B., Castro, A. M. De, Valoni, É., Oliveira, V. M.
1388 de, Marsaioli, A. J., Angelis, D. de F. de, & Attili-Angelis, D. (2019). Hydrocarbon-
1389 associated substrates reveal promising fungi for Poly (ethylene terephthalate) (PET)
1390 depolymerization. *Brazilian Journal of Microbiology*, 2050, 1–28.
- 1391 Manzur, A., Limón-González, M., & Favela-Torres, E. (2004). Biodegradation of
1392 Physicochemically Treated LDPE by a Consortium of Filamentous Fungi. *Journal of*
1393 *Applied Polymer Science*, 92(1), 265–271. <https://doi.org/10.1002/app.13644>
- 1394 Marqués-Calvo, M. S., Cerdà-Cuellar, M., Kint, D. P. R., Bou, J. J., & Muñoz-Guerra, S.
1395 (2006). Enzymatic and microbial biodegradability of poly(ethylene terephthalate)
1396 copolymers containing nitrated units. *Polymer Degradation and Stability*, 91(4), 663–
1397 671. <https://doi.org/10.1016/j.polymdegradstab.2005.05.014>
- 1398 Mathur, G., Mathur, A., & Prasad, R. (2011). Colonization and degradation of thermally

- 1399 oxidized high-density polyethylene by aspergillus niger (ITCC No. 6052) isolated from
1400 plastic waste dumpsite. *Bioremediation Journal*, 15(2), 69–76.
1401 <https://doi.org/10.1080/10889868.2011.570281>
- 1402 Mergaert, J., Anderson, C., Wouters, A., & Swings, J. (1994). Microbial degradation of
1403 poly(3-hydroxybutyrate) and poly(3-hydroxybutyrate-co-3-hydroxyvalerate) in compost.
1404 *Journal of Environmental Polymer Degradation*, 2(3), 177–183.
1405 <https://doi.org/10.1007/BF02067443>
- 1406 Mikulášová, M., & Košíková, B. (1999). Biodegradability of lignin-polypropylene composite
1407 films. *Folia Microbiologica*, 44(6), 669–672. <https://doi.org/10.1007/BF02825659>
- 1408 Milstein, O., Gersonde, R., Huttermann, A., Chen, M. J., & Meister, J. J. (1996). Fungal
1409 biodegradation of lignin graft copolymers from ethene monomers. *Journal of*
1410 *Macromolecular Science - Pure and Applied Chemistry*, 33(5), 685–702.
1411 <https://doi.org/10.1080/10601329608010887>
- 1412 Mohan K. R. Konduri, G. Koteswarareddy, D. B. Rohini Kumar, B. V. R., & Narasu, M. L.
1413 (2011). Effect of Pro-Oxidants on Biodegradation of Polyethylene (LDPE) by
1414 Indigenous Fungal Isolate, *Aspergillus oryzae*. *Journal Of Applied Polymer Science*, 120,
1415 3536–3545.
- 1416 Muhonja, C. N., Makonde, H., Magoma, G., & Imbuga, M. (2018). Biodegradability of
1417 polyethylene by bacteria and fungi from Dandora dumpsite Nairobi-Kenya. *PLoS ONE*,
1418 13(7), 1–17. <https://doi.org/10.1371/journal.pone.0198446>
- 1419 Muthumani, S., & Anbuselvi, S. (2014). Waste management and environment protection – A
1420 study with isolation and characterisation of low density polyethylene degrading
1421 microbes. *International Journal of ChemTech Research*, 7(6), 2841–2845.
- 1422 Nakamura, Y., Sawada, T., Kobayashi, F., Kuwahara, M., & Ito, H. (1997).
1423 Nakamura1997.Pdf. In *Journal Of Cemical Engineering Of Japan* (Vol. 30, Issue 1, pp.
1424 1–6). doi.org/10.1252/jcej.30.1
- 1425 Nakei, M. D., Misinzo, G., Tindwa, H., & Semu, E. (2022). Degradation of polyethylene
1426 plastic bags and bottles using microorganisms isolated from soils of Morogoro,
1427 Tanzania. *Frontiers in Microbiology*, 13(December), 1–15.
1428 <https://doi.org/10.3389/fmicb.2022.1077588>
- 1429 Napoli, M. Di, Silvestri, B., Castagliuolo, G., Carpentieri, A., Luciani, G., Di Maro, A.,
1430 Sorbo, S., Pezzella, A., Zanfardino, A., & Varcamonti, M. (2023). High density
1431 polyethylene (HDPE) biodegradation by the fungus *Cladosporium halotolerans*. *FEMS*
1432 *Microbiology Ecology*, 99(2), 1–9. <https://doi.org/10.1093/femsec/fiac148>
- 1433 Nishide, H., Toyota, K., & Kimura, M. (1999). Effects of soil temperature and anaerobiosis
1434 on degradation of biodegradable plastics in soil and their degrading microorganisms.
1435 *Soil Science and Plant Nutrition*, 45(4), 963–972.
1436 <https://doi.org/10.1080/00380768.1999.10414346>
- 1437 Novotný, Č., Erbanová, P., Sezimová, H., Malachová, K., Rybková, Z., Malinová, L.,
1438 Prokopová, I., & Brožek, J. (2015). Biodegradation of aromatic-aliphatic copolyesters
1439 and polyesteramides by esterase activity-producing microorganisms. *International*
1440 *Biodeterioration and Biodegradation*, 97, 25–30.
1441 <https://doi.org/10.1016/j.ibiod.2014.10.010>
- 1442 Nowak, B., Pajak, J., Drozd-Bratkowicz, M., & Rymarz, G. (2011). Microorganisms

- 1443 participating in the biodegradation of modified polyethylene films in different soils
- 1444 under laboratory conditions. *International Biodeterioration and Biodegradation*, 65(6),
- 1445 757–767. <https://doi.org/10.1016/j.ibiod.2011.04.007>
- 1446 Nowak, B., Pająk, J., Labuzek, S., Rymarz, G., & Talik, E. (2011). Biodegradation of
- 1447 poly(ethylene terephthalate) modified with polyester “Bionolle®” by *Penicillium*
- 1448 *funiculosum*. *Polimery/Polymers*, 56(1), 35–44.
- 1449 <https://doi.org/10.14314/polimery.2011.035>
- 1450 Oda, Y., Asari, H., Urakami, T., & Tonomura, K. (1995). Microbial degradation of poly(3-
- 1451 hydroxybutyrate) and polycaprolactone by filamentous fungi. *Journal of Fermentation*
- 1452 *and Bioengineering*, 80(3), 265–269. [https://doi.org/10.1016/0922-338X\(95\)90827-M](https://doi.org/10.1016/0922-338X(95)90827-M)
- 1453 Odigbo, C., Adenipekun, C., Oladosu, I., & Ogunjobi, A. (2023). Polyethylene terephthalate
- 1454 (PET) biodegradation by *Pleurotus ostreatus* and *Pleurotus pulmonarius*. *Environmental*
- 1455 *Monitoring and Assessment*, 195(5). <https://doi.org/10.1007/s10661-023-11153-5>
- 1456 Ojeda, T. F. M., Dalmolin, E., Forte, M. M. C., Jacques, R. J. S., Bento, F. M., & Camargo,
- 1457 F. A. O. (2009). Abiotic and biotic degradation of oxo-biodegradable polyethylenes.
- 1458 *Polymer Degradation and Stability*, 94(6), 965–970.
- 1459 <https://doi.org/10.1016/j.polymdegradstab.2009.03.011>
- 1460 Ojha, N., Pradhan, N., Singh, S., Barla, A., Shrivastava, A., Khatua, P., Rai, V., & Bose, S.
- 1461 (2017). Evaluation of HDPE and LDPE degradation by fungus, implemented by
- 1462 statistical optimization. *Scientific Reports*, 7(January), 1–13.
- 1463 <https://doi.org/10.1038/srep39515>
- 1464 Oliveira, T. A. De, Barbosa, R., Mesquita, A. B. S., Ferreira, J. H. L., Carvalho, L. H. De, &
- 1465 Alves, T. S. (2020). Fungal degradation of reprocessed PP/PBAT/thermoplastic starch
- 1466 blends. *Journal of Materials Research and Technology*, 9(2), 2338–2349.
- 1467 <https://doi.org/10.1016/j.jmrt.2019.12.065>
- 1468 Oliveira, M. M., Proenca, A. M., Moreira-Silva, E., dos Santos, F. M., Marconatto, L., de
- 1469 Castro, A. M., & Medina-Silva, R. (2022). Biochemical features and early adhesion of
- 1470 marine *Candida parapsilosis* strains on high-density polyethylene. *Journal of Applied*
- 1471 *Microbiology*, 132(3), 1954–1966. <https://doi.org/10.1111/jam.15369>
- 1472 Oliya, P., Singh, S., Goel, N., Singh, U. P., & Srivastava, A. K. R. (2020). Polypropylene
- 1473 degradation potential of microbes isolated from solid waste dumping site. *Pollution*
- 1474 *Research*, 39(2), 268–277.
- 1475 Oprea, S. (2010). Dependence of fungal biodegradation of PEG/castor oil-based polyurethane
- 1476 elastomers on the hard-segment structure. *Polymer Degradation and Stability*, 95(12),
- 1477 2396–2404. <https://doi.org/10.1016/j.polymdegradstab.2010.08.013>
- 1478 Osman, M., Satti, S. M., Luqman, A., Hasan, F., Shah, Z., & Shah, A. A. (2018). Degradation
- 1479 of Polyester Polyurethane by *Aspergillus* sp. Strain S45 Isolated from Soil. *Journal of*
- 1480 *Polymers and the Environment*, 26(1), 301–310. [https://doi.org/10.1007/s10924-017-](https://doi.org/10.1007/s10924-017-0954-0)
- 1481 [0954-0](https://doi.org/10.1007/s10924-017-0954-0)
- 1482 Paço, A., Duarte, K., da Costa, J. P., Santos, P. S. M., Pereira, R., Pereira, M. E., Freitas, A.
- 1483 C., Duarte, A. C., & Rocha-Santos, T. A. P. (2017). Biodegradation of polyethylene
- 1484 microplastics by the marine fungus *Zalerion maritimum*. *Science of the Total*
- 1485 *Environment*, 586, 10–15. <https://doi.org/10.1016/j.scitotenv.2017.02.017>
- 1486 Padmanabhan, L., Varghese, S., Patil, R. K., Rajath, H. M., Krishnasree, R. K., & Shareef,

- 1487 M. I. (2019). Ecofriendly Degradation of Polyethylene Plastics Using Oil Degrading
1488 Microbes. *Recent Innovations in Chemical Engineering (Formerly Recent Patents on*
1489 *Chemical Engineering)*, 13(1), 29–40.
1490 <https://doi.org/10.2174/2405520412666190725114137>
- 1491 Pandey, J. K., & Singh, R. P. (2001). Uv-irradiated biodegradability of ethylene-propylene
1492 copolymers, LDPE, and I-PP in composting and culture environments.
1493 *Biomacromolecules*, 2(3), 880–885. <https://doi.org/10.1021/bm010047s>
- 1494 Parit, A. A., Jadhav, A. S., & Raut, P. D. (2023). Screening and Isolation of Polypropylene
1495 Degrading Fungi from Waste Dumping Site, Kolhapur, India. *Nature Environment and*
1496 *Pollution Technology*, 22(3), 1599–1605.
1497 <https://doi.org/10.46488/NEPT.2023.v22i03.046>
- 1498 Pedrini, G. (2022). *Alma Mater Studiorum Università di Bologna Archivio istituzionale della*
1499 *ricerca Rights / License : The terms and conditions for the reuse of this version of the*
1500 *manuscript are specified in the.* 3(April 2024), 109–114.
- 1501 Penkhrue, W., Khanongnuch, C., Masaki, K., Pathom-aree, W., Punyodom, W., & Lumyong,
1502 S. (2015). Isolation and screening of biopolymer-degrading microorganisms from
1503 northern Thailand. *World Journal of Microbiology and Biotechnology*, 31(9), 1431–
1504 1442. <https://doi.org/10.1007/s11274-015-1895-1>
- 1505 Perera, M., Wijayarathna, D., Wijesundera, S., Chinthaka, M., Seneviratne, G., & Jayasena,
1506 S. (2019). Biofilm mediated synergistic degradation of hexadecane by a naturally
1507 formed community comprising *Aspergillus flavus* complex and *Bacillus cereus* group.
1508 *BMC Microbiology*, 19(1), 1–9. <https://doi.org/10.1186/s12866-019-1460-4>
- 1509 Perera, P., Herath, H., Paranagama, P. A., Wijesinghe, P., & Attanayake, R. N. (2023). Wood
1510 decay fungi show enhanced biodeterioration of low-density polyethylene in the absence
1511 of wood in culture media. *PLoS ONE*, 18(7 July), 1–25.
1512 <https://doi.org/10.1371/journal.pone.0288133>
- 1513 Poonam, K., Rajababu, V., Yogeshwari, J., & Patel, H. (2013). Diversity of plastic degrading
1514 microorganisms and their appraisal on biodegradable plastic. *Applied Ecology and*
1515 *Environmental Research*, 11(3), 441–449. https://doi.org/10.15666/aeer/1103_441449
- 1516 Porter, R., Černoša, A., Fernández-Sanmartín, P., Cortizas, A. M., Aranda, E., Luo, Y., Zalar,
1517 P., Podlogar, M., Gunde-Cimerman, N., & Gostinčar, C. (2023). Degradation of
1518 polypropylene by fungi *Coniochaeta hoffmannii* and *Pleurostoma richardsiae*.
1519 *Microbiological Research*, 277. <https://doi.org/10.1016/j.micres.2023.127507>
- 1520 Pozdnyakova, N. N., Burov, A. M., Antonov, E. A., Aleksandrova, A. V., & Turkovskaya, O.
1521 V. (2023). The Ability of Ascomycetes to Transform Polyethylene Terephthalate.
1522 *Applied Biochemistry and Microbiology*, 59(9), 1192–1200.
1523 <https://doi.org/10.1134/S0003683823090077>
- 1524 Puliga, F., Zuffi, V., Baldo, D., Cavatorta, D., Zambonelli, A., Francioso, O., & Sanchez-
1525 Cortes, S. (2023). *Cladosporium cladosporioides* (strain Clc/1): a candidate for low-
1526 density polyethylene degradation. *Chemical and Biological Technologies in Agriculture*,
1527 10(1), 1–11. <https://doi.org/10.1186/s40538-023-00419-2>
- 1528 Puranik, S., Shukla, L., Kundu, A., Kamil, D., Paul, S., Venkadasamy, G., Salim, R., Singh,
1529 S. K., Kumar, D., & Kumar, A. (2023). Exploring Potent Fungal Isolates from Sanitary
1530 Landfill Soil for In Vitro Degradation of Dibutyl Phthalate. *Journal of Fungi*, 9(1).

- 1531 <https://doi.org/10.3390/jof9010125>
- 1532 Raghavan, D., & Torma, A. E. (1992). DSC and FTIR characterization of biodegradation of
- 1533 polyethylene. *Polymer Engineering & Science*, 32(6), 438–442.
- 1534 <https://doi.org/10.1002/pen.760320609>
- 1535 Rani, A., Singh, P., & Kumar, R. (2020). Microbial deterioration of high-density
- 1536 polyethylene by selected microorganisms. *Journal of Applied Biology and*
- 1537 *Biotechnology*, 8(6), 64–66. <https://doi.org/10.7324/JABB.2020.80611>
- 1538 Râpă, M., Popa, M. E., Cornea, P. C., Popa, V. I., Grosu, E., Geicu-Cristea, M., Stoica, P., &
- 1539 Tănase, E. E. (2014). Degradation study by trichoderma spp. of poly (3-
- 1540 hydroxybutyrate) and wood fibers composites. *Romanian Biotechnological Letters*,
- 1541 19(3), 9390–9399.
- 1542 Ratna Kumari, V., & Kulkarni, S. D. (2018). An effective study on rapid degradation of
- 1543 polythene bags and plastic waste by microbial species. *Research Journal of Pharmacy*
- 1544 *and Technology*, 11(10), 4421–4425. <https://doi.org/10.5958/0974-360X.2018.00809.0>
- 1545 Renstad, R., Karlsson, S., Sandgren, Å., & Albertsson, A. C. (1998). Influence of processing
- 1546 additives on the degradation of melt-pressed films of poly(ε-caprolactone) and
- 1547 poly(lactic acid). *Journal of Environmental Polymer Degradation*, 6(4), 209–221.
- 1548 Riabi, H. R. A., Mohammadzadeh, A., Mirzahosseini, S. A. H., Chahak, A. F., & Imani, J.
- 1549 (2023). Isolation of the Gut Microbiome of Galleria mellonella Sp. (Lepidoptera:
- 1550 Pyralidae) Larvae and Its Role in the Digestion of Polyethylene Plastic. *Water, Air, and*
- 1551 *Soil Pollution*, 234(8), 1–12. <https://doi.org/10.1007/s11270-023-06515-1>
- 1552 Rosa, D. S., Bardi, M. A. G., Guedes, C. G. F., & Angelis, D. A. (2009). Role of
- 1553 polyethylene-graft-glycidyl methacrylate compatibilizer on the biodegradation of poly(ε-
- 1554 caprolactone)/cellulose acetate blends. *Polymers for Advanced Technologies*, 20(12),
- 1555 863–870. <https://doi.org/10.1002/pat.1302>
- 1556 Ruan, Y., Hu, F., Zhao, J., Li, Y., Ling, J., Cao, J., & Zhang, L. (2023). Degradation of
- 1557 polyethylene particles by Trichoderma harzianum and recombinant laccase cloned from
- 1558 the strain. *Journal of Applied Polymer Science*, 140(43).
- 1559 <https://doi.org/10.1002/app.54599>
- 1560 Russell, J. R., Huang, J., Anand, P., Kucera, K., Sandoval, A. G., Dantzler, K. W., Hickman,
- 1561 D. S., Jee, J., Kimovec, F. M., Koppstein, D., Marks, D. H., Mittermiller, P. A., Núñez,
- 1562 S. J., Santiago, M., Townes, M. A., Vishnevetsky, M., Williams, N. E., Vargas, M. P.
- 1563 N., Boulanger, L. A., ... Strobel, S. A. (2011). Biodegradation of polyester polyurethane
- 1564 by endophytic fungi. *Applied and Environmental Microbiology*, 77(17), 6076–6084.
- 1565 <https://doi.org/10.1128/AEM.00521-11>
- 1566 Saeed, S., Iqbal, A., & Deeba, F. (2022). Biodegradation study of Polyethylene and PVC
- 1567 using naturally occurring plastic degrading microbes. *Archives of Microbiology*, 204(8),
- 1568 1–14. <https://doi.org/10.1007/s00203-022-03081-8>
- 1569 Sáenz, M., Borodulina, T., Diaz, L., & Banchon, C. (2019). Minimal conditions to degrade
- 1570 low density polyethylene by Aspergillus terreus and niger. *Journal of Ecological*
- 1571 *Engineering*, 20(6), 44–51. <https://doi.org/10.12911/22998993/108699>
- 1572 Salinas, J., Carpena, V., Martínez-Gallardo, M. R., Segado, M., Estrella-González, M. J.,
- 1573 Toribio, A. J., Jurado, M. M., López-González, J. A., Suárez-Estrella, F., & López, M. J.
- 1574 (2023). Development of plastic-degrading microbial consortia by induced selection in

- 1575 microcosms. *Frontiers in Microbiology*, 14(April), 1–10.
- 1576 <https://doi.org/10.3389/fmicb.2023.1143769>
- 1577 Sameshima-Yamashita, Y., Koitabashi, M., Tsuchiya, W., Suzuki, K., Watanabe, T.,
- 1578 Shinozaki, Y., Yamamoto-Tamura, K., Yamazaki, T., & Kitamoto, H. (2016).
- 1579 Enhancement of biodegradable plastic-degrading enzyme production from paraphoma-
- 1580 like fungus, strain B47-9. *Journal of Oleo Science*, 65(3), 257–262.
- 1581 <https://doi.org/10.5650/jos.ess15207>
- 1582 Sangale, M. K., Shah Nawaz, M., & Ade, A. B. (2019). Potential of fungi isolated from the
- 1583 dumping sites mangrove rhizosphere soil to degrade polythene. *Scientific Reports*, 9(1),
- 1584 1–11. <https://doi.org/10.1038/s41598-019-41448-y>
- 1585 Sangeetha Devi, R., Rajesh Kannan, V., Nivas, D., Kannan, K., Chandru, S., & Robert
- 1586 Antony, A. (2015). Biodegradation of HDPE by *Aspergillus* spp. from marine
- 1587 ecosystem of Gulf of Mannar, India. *Marine Pollution Bulletin*, 96(1–2), 32–40.
- 1588 <https://doi.org/10.1016/j.marpolbul.2015.05.050>
- 1589 Sarkhel, R., Sengupta, S., Das, P., & Bhowal, A. (2020). Comparative biodegradation study
- 1590 of polymer from plastic bottle waste using novel isolated bacteria and fungi from marine
- 1591 source. *Journal of Polymer Research*, 27(1). <https://doi.org/10.1007/s10965-019-1973-4>
- 1592 Šašek, V., Vitásek, J., Chromcová, D., Prokopová, I., Brožek, J., & Náhlík, J. (2006).
- 1593 Biodegradation of synthetic polymers by composting and fungal treatment. *Folia*
- 1594 *Microbiologica*, 51(5), 425–430. <https://doi.org/10.1007/BF02931586>
- 1595 Sato, S., Saika, A., Shinozaki, Y., Watanabe, T., Suzuki, K., Sameshima-Yamashita, Y.,
- 1596 Fukuoka, T., Habe, H., Morita, T., & Kitamoto, H. (2017). Degradation profiles of
- 1597 biodegradable plastic films by biodegradable plastic-degrading enzymes from the yeast
- 1598 *Pseudozyma antarctica* and the fungus *Paraphoma* sp. B47-9. *Polymer Degradation and*
- 1599 *Stability*, 141, 26–32. <https://doi.org/10.1016/j.polymdegradstab.2017.05.007>
- 1600 Satti, S. M., Shah, Z., Luqman, A., Hasan, F., Osman, M., & Shah, A. A. (2020).
- 1601 Biodegradation of Poly(3-hydroxybutyrate) and Poly(3-hydroxybutyrate-co-3-
- 1602 hydroxyvalerate) by Newly Isolated *Penicillium oxalicum* SS2 in Soil Microcosms and
- 1603 Partial Characterization of Extracellular Depolymerase. *Current Microbiology*, 77(8),
- 1604 1622–1636. <https://doi.org/10.1007/s00284-020-01968-7>
- 1605 Savenkova, L., Gercberga, Z., Nikolaeva, V., Dzene, A., Bibers, I., & Kalnin, M. (2000).
- 1606 Mechanical properties and biodegradation characteristics of PHB-based films. *Process*
- 1607 *Biochemistry*, 35(6), 573–579. [https://doi.org/10.1016/S0032-9592\(99\)00107-7](https://doi.org/10.1016/S0032-9592(99)00107-7)
- 1608 Saxena, A., Jain, S., & Pareek, A. (2022). Estimation of possible Biodegradation of Polythene
- 1609 by Fungal Isolates Growing on Polythene Debris. *Pollution*, 8(2), 567–577.
- 1610 <https://doi.org/10.22059/POLL.2021.331370.1195>
- 1611 Seenivasagan, R., Karthika, A., & Poonkuzhali, K. (2022). In Vitro and In Silico Study of the
- 1612 Efficacy of Fungi in Low-Density Polyethylene Degradation in a Disposal Paper Cup.
- 1613 *Water, Air, and Soil Pollution*, 233(3). <https://doi.org/10.1007/s11270-022-05534-8>
- 1614 Seo, H. S., Um, H. J., Min, J., Rhee, S. K., Cho, T. J., Kim, Y. H., & Lee, J. (2007).
- 1615 *Pseudozyma jejuensis* sp. nov., a novel cutinolytic ustilaginomycetous yeast species that
- 1616 is able to degrade plastic waste. *FEMS Yeast Research*, 7(6), 1035–1045.
- 1617 <https://doi.org/10.1111/j.1567-1364.2007.00251.x>
- 1618 Shah, A. A., Hasan, F., Hameed, A., & Ahmed, S. (2008). Biological degradation of plastics:

- 1619 A comprehensive review. *Biotechnology Advances*, 26(3), 246–265.
- 1620 <https://doi.org/10.1016/j.biotechadv.2007.12.005>
- 1621 Sharma, S., Mathur, N., Singh, A., & Agarwal, M. (2019). Synergistic effects of thermal and
- 1622 fungal degradation on low and high density polyethylene films. *International Journal of*
- 1623 *Scientific and Technology Research*, 8(10), 3212–3219.
- 1624 Sheik, S., Chandrashekar, K. R., Swaroop, K., & Somashekarappa, H. M. (2015).
- 1625 Biodegradation of gamma irradiated low density polyethylene and polypropylene by
- 1626 endophytic fungi. *International Biodeterioration and Biodegradation*, 105, 21–29.
- 1627 <https://doi.org/10.1016/j.ibiod.2015.08.006>
- 1628 Shinozaki, Y., Morita, T., Cao, X. H., Yoshida, S., Koitabashi, M., Watanabe, T., Suzuki, K.,
- 1629 Sameshima-Yamashita, Y., Nakajima-Kambe, T., Fujii, T., & Kitamoto, H. K. (2013).
- 1630 Biodegradable plastic-degrading enzyme from *Pseudozyma antarctica*: Cloning,
- 1631 sequencing, and characterization. *Applied Microbiology and Biotechnology*, 97(7),
- 1632 2951–2959. <https://doi.org/10.1007/s00253-012-4188-8>
- 1633 Soni, R. K., Soam, S., & Dutt, K. (2009). Studies on biodegradability of copolymers of lactic
- 1634 acid, terephthalic acid and ethylene glycol. *Polymer Degradation and Stability*, 94(3),
- 1635 432–437. <https://doi.org/10.1016/j.polymdegradstab.2008.11.014>
- 1636 Sowmya, H. V., Ramalingappa, B., Nayanashree, G., Thippeswamy, B., & Krishnappa, M.
- 1637 (2015). Polyethylene degradation by fungal consortium. *International Journal of*
- 1638 *Environmental Research*, 9(3), 823–830.
- 1639 Sowmya, H. V., Ramalingappa, Krishnappa, M., & Thippeswamy, B. (2014). Degradation of
- 1640 polyethylene by *Trichoderma harzianum*—SEM, FTIR, and NMR analyses.
- 1641 *Environmental Monitoring and Assessment*, 186(10), 6577–6586.
- 1642 <https://doi.org/10.1007/s10661-014-3875-6>
- 1643 Sowmya, H. V., Ramalingappa, Krishnappa, M., & Thippeswamy, B. (2015). Degradation of
- 1644 polyethylene by *Penicillium simplicissimum* isolated from local dumpsite of
- 1645 Shivamogga district. *Environment, Development and Sustainability*, 17(4), 731–745.
- 1646 <https://doi.org/10.1007/s10668-014-9571-4>
- 1647 Spina, F., Tummino, M. L., Poli, A., Prigione, V., Ilieva, V., Cocconcelli, P., Puglisi, E.,
- 1648 Bracco, P., Zanetti, M., & Varese, G. C. (2021). Low density polyethylene degradation
- 1649 by filamentous fungi. *Environmental Pollution*, 274, 116548.
- 1650 <https://doi.org/10.1016/j.envpol.2021.116548>
- 1651 Suárez-Segundo, J. L., Vázquez-López, D., Torres-García, J. L., Ahuactzin-Pérez, M.,
- 1652 Montiel-Martínez, N., Tlecuitl-Beristain, S., & Sánchez, C. (2013). Growth of colonies
- 1653 and hyphal ultrastructure of filamentous fungi grown on dibutyl phthalate and di (2-
- 1654 ethylhexyl) phthalate. *Revista Mexicana de Ingeniera Quimica*, 12(3), 499–504.
- 1655 Sugana Rani, K., & Prasada Rao, P. V. V. (2012). Evaluation of biodegradation of plastics
- 1656 and polythene bags from various soils. *Journal of Pure and Applied Microbiology*, 6(1),
- 1657 281–287.
- 1658 Sumathi, T., Viswanath, B., Sri Lakshmi, A., & Saigopal, D. V. R. (2016). Production of
- 1659 Laccase by *Cochliobolus* sp. Isolated from Plastic Dumped Soils and Their Ability to
- 1660 Degrade Low Molecular Weight PVC. *Biochemistry Research International*, 2016.
- 1661 <https://doi.org/10.1155/2016/9519527>
- 1662 Suzuki, K., Sakamoto, H., Shinozaki, Y., Tabata, J., Watanabe, T., Mochizuki, A.,

- 1663 Koitabashi, M., Fujii, T., Tsushima, S., & Kitamoto, H. K. (2013). Affinity purification
1664 and characterization of a biodegradable plastic-degrading enzyme from a yeast isolated
1665 from the larval midgut of a stag beetle, *Aegus laevicollis*. *Applied Microbiology and*
1666 *Biotechnology*, 97(17), 7679–7688. <https://doi.org/10.1007/s00253-012-4595-x>
- 1667 Taghavi, N., Singhal, N., Zhuang, W. Q., & Baroutian, S. (2021). Degradation of plastic
1668 waste using stimulated and naturally occurring microbial strains. *Chemosphere*, 263,
1669 127975. <https://doi.org/10.1016/j.chemosphere.2020.127975>
- 1670 Tian, L., Kolvenbach, B., Corvini, N., Wang, S., Tavanaie, N., Wang, L., Ma, Y., Scheu, S.,
1671 Corvini, P. F. X., & Ji, R. (2017). Mineralisation of ¹⁴C-labelled polystyrene plastics by
1672 *Penicillium variabile* after ozonation pre-treatment. *New Biotechnology*, 38, 101–105.
1673 <https://doi.org/10.1016/j.nbt.2016.07.008>
- 1674 Tseng, W. S., Lee, M. J., Wu, J. A., Kuo, S. L., Chang, S. L., Huang, S. J., & Liu, C. Te.
1675 (2023). Poly(butylene adipate-co-terephthalate) biodegradation by *Purpureocillium*
1676 *lilacinum* strain BA1S. *Applied Microbiology and Biotechnology*, 107(19), 6057–6070.
1677 <https://doi.org/10.1007/s00253-023-12704-z>
- 1678 Tsuboi, S., Hoshino, Y. T., Yamamoto-Tamura, K., Uenishi, H., Omae, N., Morita, T.,
1679 Sameshima-Yamashita, Y., Kitamoto, H., & Kishimoto-Mo, A. W. (2024). Enhanced
1680 biodegradable polyester film degradation in soil by sequential cooperation of yeast-
1681 derived esterase and microbial community. *Environmental Science and Pollution*
1682 *Research*, 31(9), 13941–13953. <https://doi.org/10.1007/s11356-024-31994-y>
- 1683 Umamaheswari, S., Murali, M., & Thiyagarajan, R. (2014). Role of fungi inhabiting soil, cow
1684 dung and sewage in degrading polyethylene terephthalate and polystyrene foam. *Journal*
1685 *of Pure and Applied Microbiology*, 8(3), 2465–2471.
- 1686 Urbanek, A. K., Rymowicz, W., Strzelecki, M. C., Kociuba, W., Franczak, Ł., & Mirończuk,
1687 A. M. (2017). Isolation and characterization of Arctic microorganisms decomposing
1688 bioplastics. *AMB Express*, 7(1). <https://doi.org/10.1186/s13568-017-0448-4>
- 1689 Urbanek, A. K., Strzelecki, M. C., & Mirończuk, A. M. (2021). The potential of cold-adapted
1690 microorganisms for biodegradation of bioplastics. *Waste Management*, 119, 72–81.
1691 <https://doi.org/10.1016/j.wasman.2020.09.031>
- 1692 Urzo, M. L. R., Cuevas, V. C., & Opuencia, R. B. (2017). Screening and identification of
1693 polyester polyurethane-degrading fungi. *Philippine Agricultural Scientist*, 100(July
1694 2017), S72–S80.
- 1695 Vázquez-Alcántara, L., Oliart-Ros, R. M., García-Bórquez, A., & Peña-Montes, C. (2021).
1696 Expression of a Cutinase of *Moniliophthora roreri* with Polyester and PET-Plastic
1697 Residues Degradation Activity. *Microbiology Spectrum*, 9(3).
1698 <https://doi.org/10.1128/spectrum.00976-21>
- 1699 Verma, N., & Gupta, S. (2019). Assessment of LDPE degrading potential *Aspergillus* species
1700 isolated from municipal landfill sites of Agra. *SN Applied Sciences*, 1(7), 1–10.
1701 <https://doi.org/10.1007/s42452-019-0746-3>
- 1702 Vieyra, H., San Martín-Martínez, E., Juárez, E., Figueroa-López, U., & Aguilar-Méndez, M.
1703 A. (2015). Biodegradation process of a blend of thermoplastic unripe banana flour -
1704 Polyethylene under composting: Identification of the biodegrading agent. *Journal of*
1705 *Applied Polymer Science*, 132(29), 1–10. <https://doi.org/10.1002/app.42258>
- 1706 Vimal Kumar, R., Kanna, G. R., & Elumalai, S. (2017). Biodegradation of Polyethylene by

- 1707 Green Photosynthetic Microalgae. *Journal of Bioremediation & Biodegradation*, 08(01),
1708 1–8. <https://doi.org/10.4172/2155-6199.1000381>
- 1709 Vivi, V. K., Martins-Franchetti, S. M., & Attili-Angelis, D. (2019). Biodegradation of PCL
1710 and PVC: *Chaetomium globosum* (ATCC 16021) activity. *Folia Microbiologica*, 64(1),
1711 1–7. <https://doi.org/10.1007/s12223-018-0621-4>
- 1712 Volke-Seplveda, T., Saucedo-Castaeda, G., Gutierrez-Rojas, M., Manzur, A., & Favela-
1713 Torres, E. (2002). Thermally treated low density polyethylene biodegradation by
1714 *Penicillium pinophilum* and *Aspergillus niger*. *Journal of Applied Polymer Science*,
1715 83(2), 305–314. <https://doi.org/10.1002/app.2245>
- 1716 Wang, J., Yin, R., Zhang, X., Wang, N., Xiao, P., Hirai, H., & Xiao, T. (2021).
1717 Transcriptomic analysis reveals ligninolytic enzymes of white-rot fungus *Phanerochaete*
1718 *sordida* YK-624 participating in bisphenol F biodegradation under ligninolytic
1719 conditions. *Environmental Science and Pollution Research*, 28(44), 62390–62397.
1720 <https://doi.org/10.1007/s11356-021-15012-z>
- 1721 Wróbel, M., Szymańska, S., Kowalkowski, T., & Hryniewicz, K. (2023). Selection of
1722 microorganisms capable of polyethylene (PE) and polypropylene (PP) degradation.
1723 *Microbiological Research*, 267(October 2022).
1724 <https://doi.org/10.1016/j.micres.2022.127251>
- 1725 Wu, F., Guo, Z., Cui, K., Dong, D., Yang, X., Li, J., Wu, Z., Li, L., Dai, Y., & Pan, T.
1726 (2023). Insights into characteristics of white rot fungus during environmental plastics
1727 adhesion and degradation mechanism of plastics. *Journal of Hazardous Materials*,
1728 448(193), 130878. <https://doi.org/10.1016/j.jhazmat.2023.130878>
- 1729 Wu, K. Y., Yang, T. X., Yang, M., Wu, J. Q., Li, X., Chen, X. D., Tang, L., & Yang, X. Y.
1730 (2023). Preliminary identification of soil fungi for the degradation of polyurethane film.
1731 *Archives of Microbiology*, 205(4), 1–7. <https://doi.org/10.1007/s00203-023-03491-2>
- 1732 Xu, R. F., Tibpromma, S., Karunarathna, S. C., Hyde, K. D., Phukhamsakda, C., Okal, E. J.,
1733 Dai, D. Q., Chukeatirote, E., Khan, S., Elgorban, A. M., & Mortimer, P. E. (2024).
1734 Morphology, phylogeny, and polyurethane degrading ability of *Lasiodiplodia iraniensis*
1735 and *Mortierella alpina*. *New Zealand Journal of Botany*, 1–18.
1736 <https://doi.org/10.1080/0028825X.2023.2298926>
- 1737 Yang, S., Xu, H., Yan, Q., Liu, Y., Zhou, P., & Jiang, Z. (2013). A low molecular mass
1738 cutinase of *Thielavia terrestris* efficiently hydrolyzes poly(esters). *Journal of Industrial*
1739 *Microbiology and Biotechnology*, 40(2), 217–226. [https://doi.org/10.1007/s10295-012-](https://doi.org/10.1007/s10295-012-1222-x)
1740 [1222-x](https://doi.org/10.1007/s10295-012-1222-x)
- 1741 Yang, Z., Peng, H., Wang, W., & Liu, T. (2010). Crystallization behavior of poly(ϵ -
1742 caprolactone)/layered double hydroxide nanocomposites. *Journal of Applied Polymer*
1743 *Science*, 116(5), 2658–2667. <https://doi.org/10.1002/app>
- 1744 Zahra, S., Abbas, S. S., Mahsa, M. T., & Mohsen, N. (2010). Biodegradation of low-density
1745 polyethylene (LDPE) by isolated fungi in solid waste medium. *Waste Management*,
1746 30(3), 396–401. <https://doi.org/10.1016/j.wasman.2009.09.027>
- 1747 Zeghal, E., Vaksmaa, A., Vielfaure, H., Boekhout, T., & Niemann, H. (2021). The Potential
1748 Role of Marine Fungi in Plastic Degradation – A Review. *Frontiers in Marine Science*,
1749 8(November). <https://doi.org/10.3389/fmars.2021.738877>
- 1750 Zhang, J., Gao, D., Li, Q., Zhao, Y., Li, L., Lin, H., Bi, Q., & Zhao, Y. (2020).

1751 Biodegradation of polyethylene microplastic particles by the fungus *Aspergillus flavus*
1752 from the guts of wax moth *Galleria mellonella*. *Science of the Total Environment*, 704.
1753 <https://doi.org/10.1016/j.scitotenv.2019.135931>
1754
1755
1756
1757
1758
1759
1760
1761
1762
1763
1764
1765
1766
1767
1768

1769 Glossary

- 1770 • Microplastics (MPs)
- 1771 • Polyaromatic hydrocarbons (PAHs)
- 1772 • Polyethylene (PE)
- 5 1773 • Differential Scanning Calorimetry (DSC)
- 1774 • Fourier Transform Infrared Spectroscopy (FTIR)
- 1775 • Mangrove soil (M)
- 1776 • Petroleum soil (P)
- 1777 • Molasses soil (MS)
- 1778 • Lab (L)
- 7 1779 • X-Ray Diffraction (XRD)
- 1780 • Scanning Electron Microscopy (SEM)
- 1781 • Nuclear Magnetic Resonance (NMR)
- 4 1782 • Attenuated Total Reflectance-Fourier Transform Infrared (ATR-FTIR)
- 1783 • Grams per Square Meter (GSM)
- 7 1784 • Gel Permeation Chromatography (GPC)
- 1785 • Gas Chromatography-Mass Spectroscopy (GC-MS)
- 1786 • Mineral Salt Media (MSM)
- 1787 • Atomic Force Microscopy (AFM)

- 1788 • Low Density Polyethylene (LDPE)
- 1789 • National Chemical Laboratory (NCL)
- 19 1790 • Wide angle X-ray scattering (WAXS)
- 1791 • Gas Chromatography (GC)
- 1792 • High-Temperature Gel-Permeation Chromatography (HT-GPC)
- 55 1793 • Manganese Stearate (MnS)
- 1794 • Titanium Stearate (TiS)
- 1795 • Iron Stearate (FeS)
- 1796 • Cobalt Stearate (CoS)
- 1797 • Field Emission Scanning Electron Microscopy (FESEM)
- 1798 • Potato Dextrose Broth (PDB)
- 1799 • Czapek Dextrose Broth (CDB)
- 1800 • Thermogravimetric Analysis (TGA)
- 1801 • Untreated LDPE (U-LDPE)
- 1802 • Thermal pretreatment (T-LDPE)
- 1803 • Environmental Scanning Electron Microscopy (ESEM)
- 1804 • Thermoplastic Starch (TPS)
- 1805 • Styrene-ethylene-styrene degradation (SEBS).
- 1806 • Residual Mulch Film (RMF)
- 1807 • High Density Polyethylene (HDPE)
- 1808 • Polyester Polyurethane (PS-PU)
- 1809 • Polyethylene succinate (PES)
- 1810 • Polyethylene adipate (PEA)
- 1811 • Polystyrene (PS)
- 1812 • Polyurethane (PU)
- 113 1813 • LiquidChromatography-Mass Spectroscopy (LC-MS)
- 1814 • X-ray Photoelectron Spectroscopy (XPS)
- 171 1815 • Malt Extract Agar (MEA)
- 1816 • Chloramphenicol Malt Extract Agar (CMEA)
- 1817 • Polyvinyl Chloride (PVC)
- 1818 • Polypropylene (PP)
- 4 1819 • Isotactic Polypropylene (i-PP)
- 1820 • Ethylene-(vinyl acetate) (EVA)
- 7 1821 • Small Angle X-ray Scattering (SAXS)
- 1822 • Transmission Electron Microscopy (TEM)
- 1823 • Coupling Agent (CA)
- 1824 • Static Contact Angles (SCA)
- 1825 • Polyethylene Terephthalate (PET)
- 1826 • Optical Imaging Profiler (OIP)
- 118 1827 • High-Performance Liquid Chromatography with UVdetector (HPLC-UV)
- 1828 • Energy Dispersive X-ray analysis (EDX)
- 1829 • Zero Emissions Research Initiative (ZERI)
- 1830 • Poly(ϵ -caprolactone) (PCL)
- 1831 • Total Organic Carbon (TOC)
- 1832 • Polyhydroxy Butyrate (PHB)
- 1833 • Polyhydroxybutyrate co-hydroxyvalerate) (PHBV)
- 1834 • Gel Filtration Chromatography (GFC)

- 1835 • Molecular Weight Determination (MWD)
- 1836 • Polylactic Acid (PLA)
- 1837 • Polybutylene succinate (PBS)
- 1838 • Di-(2- ethylhexyl phthalate (DEHP)
- 1839 • Linear Low-Density Polyethylene (LLDPE)
- 1840 • Poly (butylene succinate adipate (PBSA)
- 1841 • Polylactic co-glycolide (PLGA)
- 1842 • Polyethylene-octene (POE)
- 1843 • Thermoplastic grafted starch (TPGS)
- 1844 • Dimethyl phthalate (DMP)
- 1845 • Dimethyl isophthalate (DMI)
- 1846 • Dimethyl terephthalate (DMT)
- 1847 • Polycarbonate (PC)
- 1848 • Biodegradable Mulch (BDM)
- 1849 • Cellulose Nanofibers (CNFs)
- 1850 • Dynamical Thermal Analysis (DMA)
- 1851 • Poly(butylene adipate) (PBA)
- 1852 • Bisphenol F (BPF)
- 1853 • Dibutyl phthalate (DBP)
- 1854 • Ultra-High-Performance Chromatography (UHPLC)

1855

1856

1857

1858

1859

1860 Supplementary Data

1861 **Table No.1: Biodegradation studies on PE using fungi**

Sr. No.	Name of Fungus species	Collection Site	Type of plastic	Incubation Time	TS (%)	WL (%)	CO ₂ (g/L)	Other Plastic degradation test	Reference
1	<i>A. niger</i>	Adapted strain	PE (10.16 μ m)	140 days	-	-	-	DSC, FTIR	Raghavan and Torma, 1992
2	IZU-154	Kobe Steel	PE	12 days	73	-	-	Manganese peroxidase activity	Iiyoshi et al., 1998
3	<i>A. glaucus</i>	Mangrove soil	PE bags	1 month	-	28.8	-	-	Kathiresan, 2003
			Plastic cups			7.26			
4	<i>A. oryzae</i>	Soil	polythene bags 0.5 to	30 days	-	-	-	Weight loss	Kannahi & Rubini,

			5cm						2012	
5	<i>A. niger</i>	Soil from mangrove (M), petroleum (P) and molasses (MS)	plastic cups	9 months	-	L: 13.25	-	SEM	Sugana Rani & Prasada Rao, 2012	
						M: 15.5				
						P:4.62				
						MS:3.37				
	<i>A. glaucus</i>		polythene bags			L: 14.75				
						M: 10.75				
						P: 6.75				
						MS: 3.25				
			plastic cups			L: 17.25				
						M: 12				
						P: 3.5				
						MS:2.25				
		polythene bags	L: 16							
			M: 11							
			P: 6.37							
			MS: 2.25							
6	<i>P.ostreatu s</i>	Laborator y of Mycorrhiz al Associatio ns/DMB/B IOAGRO/ UFV	Oxo- biodegrad able plastic bags	45 days	-	-	-	XRD, SEM, FTIR, Enzymatic assay	da Luz et al., 2013	
7	<i>P. ostreatus</i>	fungal collection of the Departme nt of Microbiol ogy of Universida de Federal de Vicos a	Oxo- biodegrad able ployethyle ne	90 days	-	-	-	SEM, FTIR, mechanical properties, CO ₂ measurement	Da Luz et al., 2014	
8	<i>C. lunata</i>	Dumpsite	PE	3 months	-	1.2	-	FTIR, SEM	Sowmya et	

	<i>A. alternata</i>					0.8			al., 2015a
	<i>A. glaucus</i>					7.7			
	<i>Fusarium sp.</i>					0.7			
	Consortium of all fungi					27			
9	<i>P. simplicissimum</i>	Dumpsite	PE: autoclaved	3 months	-	16	-	FTIR, SEM, NMR	Sowmya et al., 2015b
			PE: surface-sterilized			7.7			
			PE: UV-treated			38			
10	<i>Z. maritimum</i>	Marine water and soil	PE microplastic pellets	28 days	-	-	-	FTIR-ATR, NMR	Paço et al., 2017
11	<i>Aspergillus sp.</i>	Landfill soil	polythene bag (40 GSM)	2 months	-	0.6	-	FTIR	Ratna Kumari & Kulkarni, 2018
	<i>Candida sp.</i>		polythene bag (20 GSM)			2.33			
12	<i>A. terreus</i>	Dumping sites, mangrove rhizosphere	PE	60 days	-	58.51 ± 8.14	-	SEM, FTIR	Sangale et al., 2019
	<i>A. sydowii</i>				94.44 ± 2.40				
13	<i>A. niger</i>	Cooking oil, grease and petroleum products	PE: black and white polythene	70 days	-	B: 38, W: 26	-	SEM	Padmanabhan et al., 2019
	<i>A. flavus</i>					B: 27, W: 16			
	Unidentified sp.					B: 64, W: 45			
27 14	<i>Aspergillus sp.</i>	Marine waters	Plastic bottles	6 weeks	-	22	-	FTIR, SEM, XRD	Sarkhel et al., 2020
15	<i>A. niger</i>	Soil of the plastic waste environment	PE	4 weeks	-	L: 40 ± 3.3 S: 12 ± 3	-	FTIR, SEM	Saeed et al., 2022
	<i>A. glaucus</i>					L: 25 ± 3.3 S: 15 ± 3			
27 16	<i>A. alternata</i>	Marine sediment	Commercial PE bags	120 days	-	-	-	FTIR, XRD, GPC, GC-MS, SEM	Gao et al., 2022

17	<i>A. terreus</i> (F4)	Soil	PE powder of PE bags and bottles	13 days	-	-	-	Clear zone formation	Nakei et al., 2022
	<i>A. terreus</i> (F5)								
	<i>T. islandicus</i> (F6)								
	<i>A. terreus</i> (F8)								
	<i>Aspergillus</i> sp. (F7)								
	<i>Phoma</i> sp. (F2)								
	<i>E. rubidurum</i> (F1)								
	<i>N. fischeri</i> (F3)								
18	<i>A. flavus</i>	Gut of <i>Galleria mellonella</i>	PE	40 days	-	-	-	AFM, SEM	Riabi et al., 2023
19	<i>T. harzianum</i>	Soil contaminated with plastic	PE film (60 µm thick)	30 days	-	3.39 ± 0.3	-	SEM, FTIR, GC-MS	Ruan et al., 2023
			PE particles (355 µm and 160 µm in diameter)			-			
20	<i>F. solani</i>	Municipal waste disposal site	PE	90 days	-	-	-	SEM, FTIR	Wróbel et al., 2023
	<i>F. oxysporum</i>								
	<i>L. araneicola</i>								
	<i>T. lixii</i>								

1862

1863 **Table No.2: Biodegradation studies on LDPE using fungi**

1864

Sr. No.	Name of Fungal species	Collection Site	Type of plastic	Incubation Time	TS (%)	WL (%)	CO ₂ (g/L)	OtherPlastic degradation test	Reference
LDPE									
1	<i>A. niger</i>	Biochemistry	Untreated LDPE	6 months	-	<15	-	Variation in Viscosity,	Pandey & Singh, 2001

		Division, National Chemical Laborator y, Pune,	100 hours UV irradiated LDPE			22		Chain Scission, FTIR, SEM	
2	<i>P. pinophilum, A. niger</i>	Culture	Thermally oxidized LDPE	31 months	-	-	-	DSC, XRD, SEM, FTIR	Volke- Seplveda et al., 2002
3	<i>A. niger, G.virens, P. pinophilum, P. chrysosporiu m</i>	Culture	LDPE	9 months	-	-	-	DSC, WAXS, FTIR, GC, SEM	Manzur et al., 2004
4	<i>A. niger P. funiculosum</i>	Waste	LDPE film modified with 60% (wt/wt) Bionolle	90 days	17.9 ± 0.6 MPa	7.53 100	-	SEM, FTIR	Łabuzek et al., 2004
19 5	<i>A. fumigatus A. terreus F. solani</i>	Solid waste	LDPE film (15 µm)	100 days	-	-	-	FTIR, SEM, HT-GPC	Zahra et al., 2010
6	<i>P. chrysosporiu m T. wortmannii</i>	culture collection at the Federal Universit y, Brazil soil of the Muribeca Landfill	LDPE/mod ified starch	90 days	-	-	-	XRD, SEM, FTIR	Ferreira et al., 2010
55 7	<i>A. oryzae</i>	HDPE film (buried in soil for 3 months)	Untreated LDPE MnS LDPE TiS LDPE FeS LDPE CoS LDPE UV LDPE	3 months	26 51 45 40 39 21	5 47.2 41.6 36.1 34 18	-	Elongation percentage, SEM, F TIR	Konduri et al., 2011
108 8	<i>A. awamori M. subtilissima G. viride</i>	Waste coal Forest	F0: LDPE F1: Modified with Bionolle (70:30)	225 days	F0: 13.7 F1: 6.7 F0: 13.7 F1: 6.9	F0: 0.26 F1: 0.25 F0: 0.13 F1: 0.52	-	FTIR, SEM	Nowak et al., 2011

		Extinct volcano crater			F0: 13.2 F1: 7.3	F0: 0.28 F1: 0.26			
9	<i>A. niger</i> , <i>Aspergillus</i> sp. (5), <i>Fusarium</i> sp. (2)	Municipal solid waste	LDPE	7 days	-	-	-	Growth	Kumar et al., 2013
24 10	<i>T.harzianum</i>	Soil sample of dumpsite	UV- treated PE autoclaved surface-sterilized PE	15 days	-	40 23 13	-	SEM, FTIR, NMR	Sowmya et al., 2014
11	<i>Aspergillus</i> sp., <i>Lysinibacillus</i> sp.	Soil from municipal landfill	(25 days UV pre-treated) LDPE films (20 µm)	56 days	-	-	-	SEM, FTIR, XRD	Esmacili et al., 2014
12	<i>Saccharomyc</i> <i>A. niger</i> <i>A. flavus</i> <i>Streptomyces</i>	PE dumped garbage	LDPE	30 days	-	43 72 11 40	- 4.2 - -	-	Muthumani & Anbuselvi, 2014
13	FSM-3 <i>Aspergillus</i> FSM-5 FSM-6 FSM-8 FSM-10	Municipal solid waste	LDPE	60 days	-	8 5 7 7 9	20.2 6 18.4 17.9 17.8 19.3	Change in pH, SEM, FTIR	Das & Kumar, 2014
14	<i>A. niger</i>	Culture	LDPE sago starch filled LDPE (70/30)	30 days	-	0.09 6.52	-	SEM	Beg et al., 2015
15	<i>L. theobromae</i> <i>Aspergillus</i> sp., <i>P. lilacinus</i>	<i>Psychotri aflavida</i> <i>Humboldtia brunonis</i>	LDPE (20 µm)	90 days	-	-	-	FTIR, DSC, SEM, changes in viscosity	Sheik et al., 2015
16	<i>P. ostreatus</i>	collection of the Department of Microbiology of the Federal University of Viçosa	LDPE with 50% green polymers	100 days	-	-	-	Tensile strength, CO ₂ evolution, SEM, FTIR	Da Luz et al., 2015

17	<i>A. nomius</i> ,	Waste dumping site	LDPE	90 days	-	4.9	2.85	AFM, FTIR, GC-MS	Gajendiran et al., 2016a
	<i>Streptomyces</i> sp.					5.2	4.27		
18	<i>A. clavatus</i>	Landfill soil	LDPE	90 days	-	35	2.32	SEM, AFM, FTIR	Gajendiran et al., 2016b
19	<i>C. viridis</i>	Dumping site soil	LDPE	90 days	-	14.8	4.46	SEM, AFM, FTIR	Gajendiran et al., 2016c
20	<i>R. oryzae</i>	Culture	LDPE	1 month	60	8.4 ± 3	-	SEM, FTIR, AFM	Awasthi et al., 2017
21	<i>P. oxalicum</i>	Plastic dumping ground	LDPE	90 days	-	36.60	-	FESEM, AFM, FTIR	Ojha et al., 2017
	<i>P. chrysogenum</i>					34.35			
22	<i>A. oryzae</i>	Dumpsite	LDPE sheets	16 weeks	-	36.4±5.53	-	FTIR, GC-MS	Muhonja et al., 2018
23	<i>A. oryzae</i>	PE bags buried in the soil for six months	Surface sterilized green LDPE 1% Palmitic acid	90 days	-	PDB: 25 CDB: 32.5 PDB: 30 CDB: 40	-	FTIR, SEM	Jayaprakash & Palempalli, 2018
24	<i>P. ostreatus</i>	Culture	LDPE	150 days	-	-	-	colonization percentage, AFM, SEM, FTIR	Gómez-Méndez et al., 2018
25	<i>A. flavus</i>	Municipal dump yard	LDPE	60 days	-	17	20.8	FESEM, FTIR	Das et al., 2018
	<i>A. versicolor</i>					19	20.9		
	<i>F. solani</i>					13	19.2		
26	<i>M. circinelloids</i>	Culture	LDPE (19μ)(untreated)	45 days	-	1.328±0.27	-	FTIR	Sharma et al., 2019
			(thermally treated)			0.77			
27	<i>Aspergillus</i> sp.	Landfill soil	polythene bag (40	2 months	-	0.6	-	FTIR	Sáenz et al., 2019a
	<i>Candida</i> sp.		polythene bag (20			2.33			
28	<i>A. flavus</i>	Soil	LDPE	4 months in media, 9 months in soil	-	M: 14.3, S: 30.6	-	SEM, FTIR	Verma & Gupta, 2019
	<i>A.s terreus</i>					M: 13.1, S: 11.4			
29	<i>A. terreus</i>	Ecuadoria	LDPE	77 days	-	35.3	-	SEM	Sáenz et al.,

	<i>A. niger</i>	n mangrove				22.14			2019b
30	<i>T. hamatum</i>	Plastics from Soil	LDPE (40 µm)	7 days	-	0.5 ± 0.4	-	FTIR, TGA, GPC, SEM	Malachová, 2020
			UV/ T60:			1.3 ± 0.4			
			γT150			0.9 ± 0.1			
31	<i>A. fumigatus</i>	Landfills	Black LDPE	16 weeks	-	3.8	-	SEM, FTIR, XRD, GC-MS	El-Sayed et al., 2021
	<i>A. carbonarius</i>					2.267			
	Consortium		Untreated			5.01			
			T-LDPE			39.1			
			C-LDPE			17.76			
			γ-LDPE			5.79			
81 32	<i>D. italiana</i>	Culture collection of the Institute of Excellence in Fungal Research	LDPE (0.12 mm)	90 days	1.56,	43.90	0.45 -1.45	SEM, FTIR, GC-MS	Khruengsai et al., 2021
	<i>T. jaczewskii</i>				1.78,	46.34	0.36 -1.22		
	<i>C. fruticola</i>				0.43,	48.78	0.45 -1.45		
	<i>S. citrulli</i>				1.86,	45.12	0.33 -1.26		
	<i>A. niger</i>				3.34	28.78	0.37 -1.27		
33	<i>Pencilliumsp</i> <i>s</i>	Soil from disposal site	LDPE	40 days	-	19.17± 0.02	-	SEM-EDAX and FTIR	Lakshmi & Selvi, 2021
	<i>Fusarium sps</i>					7.08±0 .05			
	<i>A.fumigatus</i>					21.88 ±0.03			
34	<i>T. viride</i>	Culture collection	LDPE	5 days	-	-	-	Enzymatic degradation	Johnnie et al., 2021
95 35	<i>T. lanuginosus</i>	NCIM, NCL	LDPE (8 µm)	30 days	-	9.21 ± 0.84	-	SEM, FTIR	Chaudhary et al., 2021
104 36	<i>P. chrysogenum</i> <i>F. oxysporum</i> <i>T. brevicompactum</i> <i>P. lilacinum</i> <i>F. falciforme</i>	Abandoned dumpsite in northern Italy	LDPE (400 µm)	30 days	-	-	-	SEM, ATR-FTIR	Spina et al., 2021
42 37	<i>P. simplicissimum</i> strains F1 and F2	Municipality garbage plastic	Untreated LDPE	40 days	-	-	F1: 20 ± 3.45 F2: 05 ± 1.67	SEM, FTIR	Ghosh & Pal, 2021

				150 days		F1: 58.0±4 .04 F2: 24.78 ± 3.94	-		
			Ethanol treated			F1: 60.1 ± 3.56 F2: 25.58 ± 2.72	-		
38	<i>Fusarium sp.</i>	Waste disposal site	LDPE	40 days	-	7.08	-	Plate assay method, Zone method, SEM- EDAX, FT-IR	Lakshmi & Selvi, 2021
	<i>Pencillium sp.</i>					19.17			
	<i>A. fumigatus</i>					21.88			
39	<i>Cephalospori um sp.</i>	NCIM, NCL	LDPE	56 days	-	12.22± 0.82	-	FTIR, TGA, SEM, XRD	Chaudhary et al., 2022
40	<i>R. oryzae</i>	Plastic dumping site	LDPE	60 days	-	60	-	FTIR, SEM	Seenivasagan et al., 2022
33 41	<i>P. chrysogenum</i>	Polythene debris	LDPE andbiodegr adable plastic	30 days	-	P:8 BP: 23	-	SEM	Saxena et al., 2022
	<i>R. nigricans</i>					P: 6 BP: 14			
	<i>C. murorum</i>					P: 2 BP: 5			
	<i>M. echinata</i>					P: 3 BP: 8			
	<i>A. fumigatus</i>					P: 7 BP: 15			
	<i>S. chartarum</i>					P: 2 BP: 7			
	<i>A. niger</i>					P: 9 BP: 28			
	<i>C. globosum</i>					P:5 BP:10			
	<i>A. flavus</i>					P:7 BP:18			
	<i>F. oxysporum</i>					P: 3 BP: 8			

42	<i>T.harzianum</i>	IAFB	LDPE microplastics	9 days	-	-	-	Enzymatic activity	Bernat et al., 2023
43	<i>P. flavidoalba</i>	Decaying hardwoods of Neem	LDPE	45 days	-	46.79 ± 0.67	0.00307	FTIR, SEM	Perera et al., 2023
44	<i>Cladosporium</i> sp.	Soil	untreated LDPE	30 days	-	0.30 ± 0.06	-	ESEM, FTIR	Gong et al., 2023
			heat treated			0.70 ± 0.06			
45	<i>S. halophilus</i>	Gut of wood-feeding termites	LDPE (25 µm)	45 days	-	43.6	18.6	-	Elsamahy et al., 2023
	<i>M. guilliermondii</i>					19.2	11.1		
	<i>M. caribbica</i>					32.0	13.3		
	consortium					63.4	33.2		
46	<i>C. cladosporioides</i>	Agricultural fields	LDPE film (6 µm)	90 days	-	-	-	ATR-FTIR, Raman and SERS spectroscopy, SEM	Puliga et al., 2023
47	<i>Penicillium citrinum</i>	Soils of plastic waste dump yard	LDPE (51 µm)	90 days	-	38.82 ± 1.08	-	FE-SEM, FTIR, TGA	Khan et al., 2023
			Nitric acid treated LDPE			47.22 ± 2.04			
6 6 48	<i>Aspergillus</i> sp. 1, <i>Aspergillus</i> sp. 2, <i>Trichoderma</i> sp., <i>Rhizopus</i> sp., <i>Penicillium</i> sp., <i>Alternaria</i> sp., <i>C. parapsilosis</i>	E1: activated sludge and river sediment, E2: compost	A: LDPE with 20 % thermoplastic starch (TPS) B: LDPE + TPS C: LDPE + TPS + styrene-ethylene-styrene degradation (SEBS)	56 days	-	A: 3.3184 B: 14.1152 C: 16.0062 A: 3.9625 B: 20.4520 C: 21.9277	-	SEM, FTIR	Kučić Grgić et al., 2023
49	<i>G. candidum</i>	Soil	LDPE (10 µm)	90 days	-	1.5809	-	SEM, FTIR	Lin et al., 2024
	<i>F. oxysporum</i>					1.7823			
	<i>Trichoderma</i> sp.					1.8398			

1865

1866 **Table No. 3 Plastic biodegradation studies on HDPE, PS-PU, PS and PU with fungi**

1867

Sr. No.	Name of Fungal species	Collection Site	Type of plastic	Incubation Time	TS (%)	WL (%)	CO ₂ (g/L)	Other Plastic degradation test	Reference
HDPE									
1	<i>Aspergillus, Penicillium</i>	Compost	HDPE	3 months	-	-	-	DSC, FTIR	Ojeda et al., 2009
2	<i>A. niger</i>	Culture	HDPE	6 months	-	-	-	SEM, FTIR, Variation in Viscosity	Alariqi& Singh, 2010
3	<i>A. niger</i>	Waste dumpsite	HDPE (20μ)	1 month	61	3.44	-	SEM, FTIR	Mathur et al., 2011
4	<i>A.terreus</i>	dump yard	HDPE (40 μm)	30 days	-	9.4±0.1	-	FTIR, SEM, GC-MS	Balasubramanian et al., 2014
5	Consortium	Compost	HDPE 80/starch 20	200 days	-	-	-	Synchrotron-FTIR microscope (SFTIR-M), SEM, FTIR, Tensile testing	X. Liu et al., 2013
6	<i>A. tubingensis</i>	Plastic waste dump site in Gulf of Mannar, India	HDPE (40 μm)	30 days	-	6.02 ± 0.2	-	FTIR	Sangeetha Devi et al., 2015
	<i>A. flavus</i>					8.51 ± 0.1			
7	<i>P. oxalicum</i>	Plastic dumping ground	HDPE	90 days	-	55.34	-	FE-SEM, AFM, FTIR	Ojha et al., 2017
	<i>P. chrysogenum</i>					58.59			
8	<i>A. oryzae</i>	PE bags buried in the soil for six months	Surface sterilized black HDPE	90 days	-	PDB: 22.6	-	FTIR, SEM	Jayaprakash & Palempalli, 2018
			1% Palmitic acid			CDB: 28			
						PDB: 24			
						CDB: 33			
9	<i>B. adusta</i>	Ohgap Mountains, South Korea	HDPE (0.05 mm thick)	90 days	-	-	-	SEM,Raman Spectroscopy	Kang et al., 2019

10	<i>M. circinelloides</i>	Culture	HDPE (10 μ)	45 days	-	1.428 ± 0.51	-	FTIR	Sharma et al., 2019
			thermal pretreated			1.13			
			HDPE (38 μ)			0.709 ±0.14			
			thermal pretreated			0.61			
10	<i>A. Flavus</i>	Gut contents of wax	HDPE microplastic	28 days	-	-	-	FTIR	Zhang et al., 2020
11	<i>A. fumigatus</i>	Soil dump	HDPE	90 days	-	T:2.12	-	SEM	Rani et al., 2020
						UT: 1.43			
	<i>A. flavus</i>					T: 1.38			
						UT: 1.31			
	<i>F. solani</i>					T: 2.58			
						UT: 1.84			
12	<i>A. flavus</i>	Farm sludge (FS), soil, wax and meal worms' excreta	HDPE sample 1	100 days	-	5.5	-	SEM, FTIR	Taghavi et al., 2021
			Sample 2			2.5			
13	<i>C. parapsilosis</i>	Deep marine sediment	HDPE	96 hours	-	-	-	SEM, AFM, FTIR and Crystal Violet Assay	M. M. Oliveira et al., 2022
14	<i>Cephalosporium</i> strain	NCIM, NCL	HDPE films	56 days	-	-	-	Changes in pH, TDS, conductivity of MSM, FTIR, TGA, SEM	Chaudhary et al., 2022
15	<i>C. halotolerans</i>	Digestive tract of <i>G. mellonella</i> larvae	HDPE microparticles	15 days	-	-	-	SEM, FTIR, enzyme and protein analysis	Napoli et al., 2023
PS-PU									
1	<i>N. gliocladioides</i>	Soil	PS-PU	44 days	60	-	-	SEM	Barratt et al., 2003

	<i>P. ochrochloron</i>								
	<i>G. pannorum</i>								
2	<i>G. pannorum</i> , <i>Phoma sp.</i>	Soil	PS-PU	5 months	up to 95	-	-	Soil analysis, Fungal community analysis	Cosgrove et al., 2007
3	<i>F. solani</i> ,	Soil, wall paints, plastic debris	PS-PU sheets	3 weeks	-	-	L:100 P:72.5	Clear zone test	Ibrahim et al., 2011
	<i>A. solani</i>						L:71.8 P:63.6		
	<i>A. terreus</i>						L:26.1 P:58		
	<i>A. fumigatus</i>						L:43.5 P:39.5		
	<i>A. flavus</i>						L:40.5 P:94.8		
	<i>Spicaria sp</i>						L:12.7 P:22.9		
4	<i>P. microspora</i>	Woody plants of various families	PS-PU	2 weeks	-	-	-	Zone clearance, enzyme activity, FTIR	Russell et al., 2011
5	<i>L. theobromae</i> , <i>P. janthinellum</i> , <i>F. verticilloides</i> , <i>P. puntonii</i>	Forest soil	PS-PU	15 days	-	-	-	Biomass determination, Clear zone formation	Urzo et al., 2017
6	<i>P. laurentii</i>	Aircraft	PES	8 days	-	-	1.2 ± 0.2 mol%	IR microscopy	Hung et al., 2019
			PEA				-		
			Thermocet PS-PU				-		
			Irogran				-		
7	<i>E. clematidis</i>	Culture collection of the Institute of Excellence in Fungal Research	PS-PU	2 weeks	-	-	0.85	FTIR spectroscopy, GC-MS, Enzymatic Activity Assay	Khruengsai et al., 2022
PS									

1	<i>P. variabile</i>	Culture	PS	16 weeks	-	-	-	SEM, FTIR, GPC	Tian et al., 2017
2	<i>T. hamatum</i>	Plastics from Soil along highway	PS	7 days	-	0.9 ± 0.4	-	FTIR, TGA, GPC, SEM	Malachová et al., 2020
3	<i>P. glaucoroseum</i>	Soil, activated sludge, farm sludge	PS (2 mm)	100 days	-	1.8	-	SEM, FTIR, AFM	Taghavi et al., 2021
4	<i>Cephalosporium</i> sp.	Culture	PS	56 days	-	13.15 ± 0.44	-	FTIR, SEM, TGA, XRD	Chaudhary et al., 2022
5	<i>P. chrysosporium</i>	China Center for Type Culture Collection	PS	35 days	-	19.7	-	FTIR, SEM, GC-MS	F. Wu et al., 2023
PU									
1	<i>P. chrysosporium</i>	Culture	PU foam	10 days	-	-	-	Lignin Peroxidase production	Nakamura et al., 1997
2	<i>C. globosum</i>	Department of Microbiology of the Biological Research Institute,	PU	130 days	-	-	-	FTIR, SEM, Weight loss	Oprea, 2010
3	At 37°C, <i>A. flavum</i> , <i>C. rugosa</i> , <i>A. kalrae</i> At 45°C, <i>Aspergillus</i> sp., community of <i>Lichtheimia</i> sp., <i>A. fumigatus</i> , <i>M. cinnamomea</i>	Compost	PU	28 days	>70	-	-	Loss in tensile strength and percentage elongation at break	Zafar et al., 2014
4	<i>M. ruber</i> <i>M. sanguineus</i> <i>Monascus</i> sp.	Dumping site soil	PU	5 days	-	-	-	enzyme production, SEM, Zeta analysis	El-Morsy et al., 2017
5	<i>Pestalotiopsis</i> sp.	<i>Nepenthes ampullari</i>	PU	3 weeks	-	-	-	Enzyme essay	Bong et al., 2017

41 6	C. cladosporioi	Plastic debris of the shoreline of Lake Zurich	PU	6 days	-	-	-	GC-MS	Brunner et al., 2018
	X.graminea,								
	P. griseofulvum								
	Leptosphaeri asp.								
	A.bisporus	Fungal collection		14 days					
	M. oreades								
7	A. fumigatus	Solid waste dumping site soil	PU film (~0.2 mm)	4 weeks	-	15-20	10.05	FTIR, DSC, SEM, Esterase Activity Assay	Osman et al., 2018
8	Uncultured, Arthrographis, Apiotrichum, Aspergillus, Thermomyces	Soil	PU cubes	12 weeks		71 % mass loss		SEM, GC-MS, LC-MS	Gunawan et al., 2020a
	Uncultured, Arthrographis, Thermomyces, Apiotrichum, Mortierella	Compost				30 % mass loss			
9	Cladosporium	PU rich site in an ocean	PU	15/30 weeks	-	-	-	SEM, FTIR, GC-MS	Gunawan et al., 2022b
	P. chrysogenum								
10	R. oryzae	Soil	PU film (0.1 mm)	2 months	-	2.7	-	SEM, Enzymatic analysis	K. Y. Wu et al., 2023
	A. alternata					3.3			
11	Cladosporium sp.	Activated sludge	PBA-PU film	28 days		MSM: 32.42 PDB: 78.8	-	SEM, FTIR	Liu et al., 2023
			PU foam	14 days		MSM: 15.3 PDB: 83.8			
12	Clonostachy PB54	Landfill	PU	90 days	-	L: 38 S: 45	-	FTIR, XPS, LC-MS	Bhavsar et al., 2024
	Clonostachy PB62					L: 36			
	Purpureocillium spp. PB57					L: 33 S: 42			

	PB49					S: 39			
13	<i>L. iraniensis</i>	PU foam	PU films	4 months	-	MEA: 13.55	-	SEM	Xu et al., 2024
	<i>M. alpina</i>					CME A: 26.30			

1868

1869

1870 **Table No. 4 Investigations on degradation of PVC and PP types of plastic using fungi**

Sr. No.	Name of Fungal species	Collection Site	Type of Plastic	Incubation Time	TS (%)	WL (%)	CO ₂ (g/L)	Other Plastic degradation test	Reference
PVC									
1	<i>P. chrysosporium</i>	soil mixed with municipal sewage sludge	PVC films and cellulose (1:1)	3 months	-	-	-	FTIR	M. I. Ali et al., 2009
2	<i>P. chrysosporium</i>	Soil	PVC film	10 months	-	-	7.31 (after 4 weeks)	SEM, GPC, NMR, FTIR	M. I. Ali et al., 2014
	<i>L. tigrinus</i>						-		
	<i>A. niger</i>						6.02 (after 4 weeks)		
	<i>A.s sydowii</i>						-		
3	<i>Cochliobolus sp.</i>	Soil from plastic industry	PVC	7 days	-	-	-	FTIR, GC-MS, SEM	Sumathi et al., 2016
4	<i>C. globosum</i>	Culture collection	PVC films (40–50 µm)	28 days	-	75	-	SEM	Vivi et al., 2019
5	<i>P. chrysosporium</i>	waste plastic and wood	PVC films	2 months	-	31	-	FTIR, SEM	Khattoon et al., 2019
6	<i>T. hamatum</i>	Plastics from Soil	PVC	2 months	-	20.0±0.5	-	FTIR, TGA, GPC, SEM	Malachová et al., 2020
	<i>T. abietinum</i>					17.5±0.7			

	<i>B. nivea</i> FK1					18.4± 0.7			
	<i>B. nivea</i> JM5					15.5± 0.9			
7	<i>A. niger</i> <i>A. glaucus</i>	Soil of the plastic waste	PVC	28 days	-	10±3.3 32±3.3	-	FTIR, SEM	Saeed et al., 2022
8	<i>P. glandicola</i> <i>A. flavus</i> <i>A. fumigatus</i> <i>P. chrysogenum</i> <i>A. niger</i> <i>Fusarium sp.</i> <i>T. viridae</i>	Dumping site	PVC	6 weeks	-	6 12 6 2 10 6 10	-	-	Emmanuel-Akerele and Akinyemi, 2022
9	<i>A. fumigatus-3</i> <i>A. fumigatus-2</i> <i>Malassezia sp.</i> <i>A. fumigatus-1</i>	Landfill	PVC Strips	30 days	-	2.15 ± 0.42 1.92±0 .51 1.46±0 .7 0.718± 0.1	-	SEM, Enzymatic activity	El-Dash et al., 2023
PP									
1	<i>P. chrysosporium</i>	Culture	PP with lignin	30 days	-	-	-	elongation at break, UV-Spectrometry of enzyme	Mikulášová & Košíková, 1999
2	<i>A. niger</i>	Biochemistry Division,	PP	6 months	-	22	-	SEM, FTIR	Pandey & Singh, 2001
3	<i>A. niger</i>	Culture	i-PP	6 months	-	-	-	SEM, FTIR, Variation in Viscosity	Alariqi & Singh, 2010
4	<i>Trichoderma</i>	culture	PP/TPSwit h 6 wt% of EVA	3 weeks	-	90/10: 1.0 70/30: 10.9 50/50: 28.8	-	SAXS, TEM, TGA, SEM, FTIR	Hanifi et al., 2014
5	<i>L. theobromae</i> <i>Aspergillus sp.</i> , <i>P. lilacinus</i>	<i>Psychotri aflavida</i> <i>Humboldtia brunonis</i>	PP (20 µm)	90 days	-	-	-	FTIR, DSC, SEM, changes in viscosity	Sheik et al., 2015

6	<i>T. villosa, T. versicolor, P. sanguineus</i>	Soil/culture	PP and EVA copolymer, wood flour of <i>Eucalyptus grandis</i> and <i>Pinus elliotii</i>	12 weeks	-	-	-	SEM, CO ₂ production	Catto et al., 2016
	<i>F. ferrea</i>								
7	<i>B. adusta</i>	RECOSOL	Polypropylene (PP) PP/ <i>Eucalyptus globulus</i> (PP/EG), PP/Pinecones (PP/PC), PP/ <i>Brassica rapa</i> (PP/BR)	49 days	-	-	-	SEM, FTIR, AFM, static contact angles (SCA)	Butnaru et al., 2016
8	<i>Aspergillus sp.</i> and <i>Penicillium sp.</i>	Culture	PP 1 cycle	30 days	-	-0.262 ±	-	SEM, FTIR	T. A. De Oliveira et al., 2020
			PP 7 cycle			-0.620 ± 0.053			
9	<i>A. fumigatus</i>	Solid waste dumping site	PP cups	6 months	-	-	-	SEM, FTIR	Oliya et al., 2020
10	<i>C. hoffmannii</i> <i>P. richardsiae</i>	Hydrocarbon-contaminated environment	PP	2 months	-	-	-	SEM, Raman spectroscopy, FTIR—ATR, Enzymatic Activity	Porter et al., 2023
11	<i>C. halotolerans</i>	Soil of solid waste dumping site	sunlight-exposed PP	8 months	-	8.6	-	FTIR	Parit et al., 2023
			UV-exposed			6.1			
			un-treated			4.2			
12	<i>A. flavus</i>	Municipal waste landfill site	PP	90 days	-	-	-	SEM, FTIR	Wróbel et al., 2023
	<i>A. fumigatus</i>								
	<i>F. oxysporum</i>								
	<i>P. granulatum</i>								

1871

1872

1873 **Table No. 5 Investigations on degradation of PET, PCL and PHB types of plastics with**
 1874 **fungi**

Sr. No.	Name of Fungal species	Collection Site	Type of Plastic	Incubation Time	TS (%)	WL (%)	CO ₂ (g/L)	Other Plastic degradation test	Reference
PET									
1	<i>P. fluorescens</i>	Culture	PET (225-275 µm)	3 months	-	-	-	SEC, SEM	Marqués-Calvo et al., 2006a
	<i>A. niger</i>								
	<i>P. pinophilum</i>								
2	<i>A. niger</i>	Colección Española de Cultivos Tipo	PET	3 months	-	-	-	optical imaging profiler (OIP)	Marqués-Calvo et al., 2006b
	<i>P. pinophilum</i>								
3	<i>P. funiculosum</i>	Landfill	PET 0/100	84 days	-	0.08	-	SEM, FTIR, XSP	F, PajaK, et al., 2011
			90/10			0.07			
			75/25			0.21			
			50/50			0.19			
			100/0			90.28			
4	<i>A. awamori</i> , <i>M. subtilissima</i> , <i>G. viride</i>	Waste	PET (pbsa)	225 days	98	5.76	-	SEM, FTIR	Nowak et al., 2011
		Forest				2.02			
		Extinct volcano crater				17.03			
5	<i>T. terrestris</i>	Soil	PET	24 hrs	-	-	-	Cutinase production	Yang et al., 2013
6	<i>Aspergillus</i> sp., <i>Penicillium</i> sp., <i>Fusarium</i> sp.	Sewage	PET flakes	70 days	-	-	-	SEM	Umamaheswari et al., 2014
7	<i>A. oryzae</i>	Culture	PET nanoparticles	15 days	-	1.0 ± 0.1	-	SEM	Chaves et al., 2018
	<i>Trichoderma</i> sp. C65					1.7 ± 0.3			
	<i>Trichoderma</i> sp. C68					1.1 ± 0.2			
	<i>Trichoderma</i> sp. L1239					7.1 ± 0.2			
	<i>M. arundinis</i> L43					2.4 ± 0.4			
	<i>M. arundinis</i> L84					4.1 ± 0.5			

	<i>Fusarium sp.</i>					1.4 ± 0.2			
	<i>R. miehei</i>					0.3 ± 0.1			
	<i>P. brevicompactum</i>					0.2 ± 0.1			
	<i>Aspergillus sp. C362</i>					0.1 ± 0.0			
	<i>Aspergillus sp. C363</i>					0.4 ± 0.1			
	<i>Trichoderma sp. C64</i>					0.4 ± 0.1			
	<i>Trichoderma sp. C70</i>					0.2 ± 0.0			
	<i>Neopestalotiopsis sp.</i>					0.4 ± 0.1			
	<i>E. sorghinum</i>					0.5 ± 0.1			
8	<i>Microsphaeropsis</i> , <i>Mucor</i> , <i>Trichoderma</i> , <i>Westerdykella</i> , <i>Pycnidophora</i> sp., <i>Microsphaeropsis arundinis</i>	Fresh water	PET	15 days	-	-	-	HPLC-UV, FTIR, SEM, Fluorescence analysis	Malafattipicca et al., 2019
9	<i>Clitocybe sp.</i>	Culture collection	PET	6 months	-	-	-	SEM, EDX	Janczak et al., 2020
	<i>L. laccata</i>								
10	<i>Pseudomonas sp.</i>	AS, FS and soil	PET film	100 days	-	0.6	-	SEM, FTIR, AFM	Taghavi et al., 2021
11	<i>Moniliophthoraria</i>	Cacao pods	PET	21 days	-	31	-	Dry weight measurement, Titration assay, SEM	Vázquez-Alcántara et al., 2021
12	<i>A. tamarii</i> , <i>Penicillium crustosum</i>	Soil from college premises	PET	30 days	-	-	-	terephthalic acid release (TPA) release, FTIR and SEM	Anbalagan et al., 2022
13	<i>L. aphanocladii</i>	IBPPM Collection of Rhizospheric Microorganisms	PET	30 days	-	11.6 ± 2.9	-	Enzyme production	Pozdnyakova et al., 2023
	<i>F. oxysporum</i>					22.0 ± 2.2			

	<i>T. harzianum</i>	Institute of Ecology and Evolution , Russian Academy of Sciences				17.2 ± 3.8			
	<i>T. sayulitensis</i>	Rhizosphere of <i>Miscanthus</i> grown in Zn-polluted soil				10.0 ± 3.3			
14	<i>P. ostreatus</i>	University of Ibadan, Nigeria, ZERI, Namibia	PET flakes	60 days	-	-	-	FTIR GC-MS	Odigbo et al., 2023
	<i>P. pulmonarius</i>								
PCL									
1	<i>P. lilacinus</i>	soil and activated sludge	PCL	10 days	-	10	-	HPLC	Oda et al., 1995
2	<i>A. fumigatus</i>	Culture	PCL	14 days	-	-	-	DSC, weight reduction and reduction in tensile strength	Albertsson et al., 1998
3	<i>A. fumigatus</i> , <i>P. simplicissimum</i>	Culture	PCL	45 days	-	50-55	-	SEC, DSC, FTIR, SEM, ESCA (Electron Spectroscopy for Chemical Analysis)	Renstad et al., 1998
4	<i>Paecilomyces</i> sp., <i>Thermomyces</i> sp.	Soil	PCL	30 days	-	-	-	Weight measurement, Soil analysis	Nishide et al., 1999

5	<i>Penicillium sp.</i>	Soil	PCL	50 days	-	56	-	SEM	Kamiya et al., 2007
6	<i>P. jejuensis</i>	Orange leaves	PCL	12 days	-	-	-	Cutinase activity, TOC	Seo et al., 2007
7	<i>A. fumigatus</i> , <i>A. niger</i> , <i>A. versicolor</i> , <i>Aspergillus sp.</i> , <i>P. simplicissimum</i> , <i>Penicillium spp.</i> and <i>C. cladosporioides</i>	Soil	PCL	9 months	80/20: 38 60/40: 25 40/60: 13	-	-	SEM	Rosa et al., 2009
8	<i>P. oxalicum</i> strain DSYD05-1	Soil	PCL	6 days	-	-	-	Enzymatic assay, weight loss	Li et al., 2012
9	<i>T. terrestris</i> CAU709	Soil	PCL	24 hrs	-	-	-	Cutinase production	Yang et al., 2013
10	<i>P. antarctica</i> JCM 10317	Culture collection , Japan	PCL	7 days	-	-	-	SEM, Enzymatic degradation	Shinozaki et al., 2013
	<i>Ustilago maydis</i> MAFF 236374, 236375, 236376, 236377, 236378	NIAS Gene Bank, Japan							
	<i>S. cerevisiae</i> BY4741	EUROSC ARF, Germany							
11	<i>P. japonica</i>	<i>Hyoscyamus muticus</i> plant	PCL film	15 days	-	93.33	-	-	Abdel-Motaal et al., 2014
			PCL foam	30 days		43.2			
12	<i>Amycolatopsis sp.</i>	Agricultural soils	PCL	30 days	-	-	-	protease, esterase and lipase production	Penkhrue et al., 2015
13	<i>Trichoderma sp.</i> (16H)	Soil of western and central parts of Spitsbergen,	PCL	1 month	-	21.54	-	SEM	Urbanek et al., 2017
	<i>C. rosea</i> (16G)					52.91			
						34.50 (liq. 20°C)			

		Svalbard Archipelago							
14	<i>A. fumigatus</i>	Compost 37°C	PCL	91 days	-	100	-	Tensile strength	Al Hosni et al., 2019
		Soil 37°C							
	<i>T. lanuginosus</i>	Compost 50°C							
	<i>N.ramose, F. solani, A. fumigatus</i>	Compost 25°C							
	<i>F. solani</i>	Soil 25°C							
15	<i>C. globosum</i>	Culture collection	PCL	28 days	-	75	-	SEM	Vivi et al., 2019
16	<i>A. porosum, P. samsonianum, T. pinophilus, P. lilacinum, F. acetilerea</i>	KACC	PCL	45 days	-	-	-	Clear zone formation	Lee et al., 2021
16	<i>Geomycesp, Sclerotinia, Fusarium sp, Mortierella, H. anomala</i>	Soil	PCL	1 month				Clear zone formation	Urbanek et al., 2021
17	<i>M. roreri</i>	Cacao pods	PCL	21 days	-	43	-	Dry weight measurement, Titration assay, SEM	Vázquez-Alcántara et al., 2021
PHB									
1	<i>P. simplicissimum, V. leptobactrum, A. fitmigatus</i>	Compost	PHB, PHBHV	98 days	-	-	-	weight loss and loss of mechanical properties	Mergaert et al., 1994
2	<i>P.lilacinus</i>	soil and activated sludge	PHB	10 days	-	100	-	HPLC	Oda et al., 1995
3	<i>Mucor sp.</i>	Soil	PHB/ HV	23 days				Weight measurement, Soil analysis	Nishide et al., 1999

4	<i>Penicillium</i> , <i>Cephalosporium</i> , <i>Paecilomyces</i> ,	garden soil	PHB	30 days	-	-	-	Mass loss, mechanical test	Savenkova et al., 2000
5	<i>Trichoderma sp.</i>	Soil	PHB	50 days	-	-	-	FTIR	Răpă et al., 2014
6	<i>A. fumigatus</i> , <i>P. farinosus</i> , <i>F. solani</i>	Buried in an activated sludge	PHB	25 days	-	98.9±4.0 at 37°C	-	SEM, Sturm test	Kim et al., 2000
	<i>A. fumigatus</i> , <i>C. protuberata</i> , <i>P. simplicissimum</i>		Sky-Green1 (SG)	55 days		77.5±2.4 at 28°C			
	<i>A. fumigatus</i> , <i>A. parasiticus</i>		Mater-Bi1 (MB)			72.1±2.2 at 60°C			
9	7	<i>A. fumigatus</i>	Soil (37°C)	PHB	300 days	-	-	-	Al Hosni et al., 2019
		<i>A. fumigatus</i>	Compost (37°C)						
		<i>F. solani</i>	Compost (25°C)						
		<i>T. lanuginosus</i> , <i>Sordariales sp.</i> , <i>S. thermophilum</i> , <i>C. thermophilum</i>	Compost (50°C)						
84	8	<i>A. niger</i>	Department of Biotechnology /Ministry of Science, a local isolate from soil contaminated with oil wastes	PHB in solid medium	12 days	-	100	-	Iman et al., 2019
				PHB in liquid medium	14 days				

5	9	<i>P. oxalicum</i>	Soil of dumping site	PHB	emulsion and films form within 36–48 h at 30 °C in lab-built soil environment within 1 week	-	-	-	SEM, NMR, DSC, FTIR, Gel Filtration Chromatography, Molecular Weight Determination	Satti et al., 2020
---	---	--------------------	----------------------	-----	---	---	---	---	--	--------------------

1875

1876

1877

1878

1879

1880

1881

1882

1883 **Table No. 6Biodegradation of PLA, PBS, DEHP, LLDPE and PBSA types of plastics by**

1884 **fungi**

Sr. No.	Name of Fungus species	Collection Site	Type of plastic	Incubation Time	TS (%)	WL (%)	CO ₂ (g/L)	Other Plastic degradation test	Reference
PLA									
1	<i>P. antarctica</i>	Culture collection, Japan	PLA	7 days	-	-	-	SEM, Enzymatic degradation	Shinozaki et al., 2013
	<i>U. maydis</i> MAFF 236374, 236375, 236376, 236377, 236378	NIAS Gene Bank, Japan							
	<i>S. cerevisiae</i>	EUROSC ARF, Germany							
2	<i>Amycolatopsis ssp.</i>	Northern Thailand	PLA film	7 days	-	36.7	-	Enzyme production	Penkhrue et al., 2015

3	Two strains of <i>T. lanuginosus</i> and <i>Sordarialess p.</i>	Compost (50°C)	PLA	300 days	-	-	-	-	Al Hosni et al., 2019
4	<i>A. porosum</i> , <i>P. samsonianum</i> , <i>T. pinophilus</i> , <i>P. lilacinum</i> , <i>F. acetilerea</i>	Korean Agricultural Culture Collection (KACC)	PLA	45 days	-	-	-	Clear zone formation	Lee et al., 2021
5	<i>P. chrysosporium</i>	China Center for Type Culture Collection, China	PLA	35 days	-	19.7	-	FTIR, SEM	F. Wu et al., 2023
PBS									
1	<i>Penicillium sp.</i>	Soil	PBS	34 days	-	46	-	SEM	Kamiya et al., 2007
2	<i>F. solani</i>	Farmland soil	PBS	14 days	-	-	-	CO ₂ evolution	Abe et al., 2010
3	<i>P. chrysanthemi cola</i>	Healthy leaves of wheat, barley, rice, grown in fields	PBS film (Bionolle 1001G) (20 µm)	10 days	-	-	-	Enzymatic activity, SEM	Koitaabashi et al., 2012
4	<i>T. terrestris</i> CAU709	Soil	PBS	24 hrs	-	-	-	Cutinase production	Yang et al., 2013
5	<i>P. antarctica</i>	Culture collection, Japan	PBS film	7 days	-	-	-	SEM, Enzymatic degradation	Shinozaki et al., 2013
	<i>U. maydis</i> MAFF 236374, 236375, 236376, 236377, 236378	NIAS Gene Bank, Japan							
	<i>S. cerevisiae</i>	EUROSC ARF, Germany							

2			larval midgut of a stag beetle, <i>Aeguslaev icollis</i>							
2	6	<i>C. magnus</i>	Japan Collection of Microorganisms of the Riken Bio-resource Center, Japan	PBS	4 days	-	-	-	Enzyme production	Suzuki et al., 2013
		<i>C. magnus</i> , <i>F. floriforme</i> , <i>P. antarctica</i>								
	7	<i>A. thailandensis</i>	Soil	PBS	14 days	-	-	-	Enzyme production, SEM	Penkhrue et al., 2015
	8	<i>Paraphoma sp.</i>	Culture, isolated from barley	PBS film	7 days	-	-	-	Enzymatic degradation	Koitabashi et al., 2016
	9	<i>P. Antarctica</i> , <i>Paraphoma sp.</i>	culture	PBS (Bionolle #1020)	1- 4 hrs	-	-	-	LCMS, SEC	Sato et al., 2017
	10	<i>T. pinophilus</i> , <i>A. cellulolyticus</i> , <i>P. pinophilum</i>	Compost (50°C)	PBS	300 days	-	< 50	-	-	Al Hosni et al., 2019
		<i>A. fumigatus</i>	Soil (37°C)			-	< 75			
	11	<i>Geomyces sp.</i> , <i>Sclerotinia</i> , <i>Fusarium sp.</i> , <i>Mortierella</i> , <i>Hansenulaanomala</i>	Soil	PBS	1 month	-	-	-	Clear zone formation	Urbanek et al., 2021
DEHP										
1		<i>F. oxysporum</i> ,	Soil in central	DEHP	7 days	-	-	-	Biomass production	Suárez-Segundo et al.,

35	<i>M. alpina</i>	Manchester UK							2013
	<i>P. pulmonarius</i>	Chinese University of Hong Kong Collection							
	two strains of <i>P. ostreatus</i>	American Type Culture Collection							
	<i>P. florida</i>	Universidad Autónoma de Tlaxcala collection							
74 2	<i>F. culmorum</i>	CICB at Universidad Autónoma de Tlaxcala, Mexico	DEHP (1000 mg/L)	144 h		99		GC-MS	Ahuactzin-Pérez et al., 2016
			DEHP (500 mg/L)	84 h	-	93	-		
				144 h		98			
3	<i>P. ostreatus</i>	Local market	DEHP	20 days	-	-	-	Enzyme production	Hock et al., 2020
	<i>P. seryngii</i>								
	<i>L. edodes</i>								
	<i>A. bisporus</i>								
4	<i>A. niger</i>	Dumping ground soil	DEHP (urine bag, blood bag)	20 days	-	-	-	SEM	E. A. M. Ali et al., 2023
	<i>A. nidulans</i>								
	<i>R. nigricans</i>								
5	<i>F. culmorum</i>	Research Centre for Biological Sciences at Universidad Autónoma de Tlaxcala, Mexico	DEHP	312 hours	-	-	-	96.9 % biodegradation, Enzyme production	Hernández-Sánchez et al., 2024
LLDPE									

1	<i>A. niger, P. funiculosum, C. globosum, G. virens, P. pullulans</i>	Culture	LLDP E	28 days	-	0.37	-	SEM, DSC, TGA, FTIR	Chandra & Rustgi, 1997
			MA-g-LLDP E			0.2			
2	<i>Aspergillus, Penicillium</i>	Compost	LLDP E	3 months	-	-	-	DSC, FTIR	Ojeda et al., 2009
3	<i>P. chrysosporium</i>	DSMZ	LLDP E (12 micron)	180 days	-	-	-	FTIR, DSC, TGA, GPC	Corti et al., 2012
4	<i>A. terreus, A. wentii, E. nidulans</i>	Waste material soil	LLDP E, LLDP E + High Molecular weight (HmH DPE)	3 months	-	-	-	Enzymatic activity	Poonam et al., 2013
5	<i>T. hamatum</i>	Plastic waste soil	LLDP E- γ irradiation	7 days	-	2.2 \pm 1.2	-	FTIR, TGA, GPC, SEM	Malachová et al., 2020
			90°C			3.9 \pm 0.5			
6	<i>D. hansenii</i>	Agricultural soil	LLDP E MPs	30 days	-	2.5-5.5	-	FESEM	Salinas et al., 2023
PBSA									
1	<i>Aspergillus sp., Cunninghamella sp., Thermomyces sp.</i>	Soil	PBSA	25 days	-	-	-	Weight measurement, Soil analysis	Nishide et al., 1999
2	<i>Penicillium sp.</i>	Soil	PBSA	20 days at 25°C	-	60	-	LC-MS/MS, Enzyme production	Kamiya et al., 2007
				50 days on university soil		50			
3	<i>P. chrysanthemi</i>	Healthy leaves of wheat, barley,	PBSA film (Bionolle)	10 days	-	-	-	Enzymatic activity, SEM	Koitaishi et al., 2012

		rice, grown in fields	3001 G)						
4	<i>P. antarctica</i>	Culture collection , Japan	PBSA	7 days	-	-	-	SEM, Enzymatic degradation	Shinozaki et al., 2013
	<i>U. maydis</i> MAFF 236374, 236375, 236376, 236377, 236378	NIAS Gene Bank, Japan							
	<i>S. cerevisiae</i>	EUROSC ARF, Germany							
5	<i>C. magnus</i>	larval midgut of a stag beetle	PBSA	4 days	-	-	-	Enzyme production	Suzuki et al., 2013
	<i>C. magnus</i> , <i>F. floriforme</i> , <i>P. antarctica</i>	Japan Collection of Microorg anisms of the Riken Bio- resource Center							
6	<i>Paraphoma</i> <i>sp.</i>	Culture, isolated from barley	PBSA	7 days	-	-	-	Enzymatic degradation	Koitabashi et al., 2016
7	<i>Paraphoma</i> - like Fungus	Culture	PBSA 20µm	8 hours	-	-	-	Gel electrophores is	Sameshima- Yamashita et al., 2016
8	<i>P. antarctica</i> , <i>Paraphoma</i> <i>sp.</i>	culture	PBSA (Biono lle #3020)	1- 4 hrs	-	-	-	LCMS	Sato et al., 2017
9	<i>P. antarctica</i>	culture collection (JCM)	PBSA film (20 mm)	3 days	-	-	-	SEM	Kitamoto et al., 2018
10	<i>Geomyces</i> <i>sp.</i> , <i>Sclerotinia</i> , <i>Fusarium</i> <i>sp.</i> , <i>Mortierel</i> <i>la</i> , <i>H.</i> <i>anomala</i>	Soil	PBSA	1 month	-	-	-	Clear zone formation	Urbanek et al., 2021
11	<i>A. fumigatus</i>	Farmland soil	PBSA Films	28 days	-	-	-	SEM, NMR, Enzymatic	Chien et al., 2022
	<i>A. terreus</i>								

			(soil burial experiment)					activity	
12	<i>Fusarium sp.</i>	In situ soil	PBSA	55 days	-	-	-	CO ₂ production, enzymatic activity	Tsuboi et al., 2024

1885

1886

1887 **Table No. 7 Investigations on biodegradation of different types plastics by fungi**

Other types of plastic									
Sr. No.	Name of Fungus species	Collection Site	Type of plastic	Incubation Time	TS (%)	WL (%)	CO ₂ (g/L)	Other Plastic degradation test	Reference
1	<i>P. ostreatus</i> , <i>P. chrysosporium</i> , <i>T. versicolor</i> , <i>G. trabeum</i> , <i>P. radiata</i>	Culture collection of the Institute of Forstbotanic of The University	Lignin/styrene products 10.3 (LPS10), 32.2 (LPS3)	68 days	-	LPS 50 and LPS 32 by 50.41 and 32.17	-	SEM, UV-spectrometry, Synthesis of Polymerizates, Mass Reduction	Milstein et al., 1996
	<i>P. ostreatus</i> , <i>T. versicolor</i> , <i>P. radiata</i>	Collection of Bundesanstalt für Materialforschung und -prüfung, Berlin	lignin/methyl methacrylate (11 to 18 wt% lignin)						
2	<i>P. chrysosporium</i>	Culture	PVA	15 days	-	-	-	gel permeation chromatography (GPC), FTIR, HPLC	Betty Lucy López et al., 1999
3	<i>Fusarium</i>	Culture	PLGA 43/57	12 weeks	-	91.1	-	DSC, SEM, Change in viscosity	Cai et al., 2001
4	<i>A. niger</i>	NCL, India	EPF 30R (~100 µm) in compost	6 months	-	Unirradiated: 10 100 hr UV irradiated: > 75	-	Variation in Viscosity, Chain Scission, FTIR, SEM	Pandey & Singh, 2001

			EPQ 30R (~100 µm) in compo st			Unirra diated: <15 100 hr UV irradia			
5	<i>P. chrysosporium</i>	Fungal Culture Collection of the National	Polyamide-6	5 months	-	50	-	SEM	Klun et al., 2003
6	<i>I. hispidus</i>	Culture Collection of	poly(ester-amide)	32 to 90 days	-	-	-	GPC, SEM	Šašek et al., 2006
7	<i>A. clavatus</i>	Dry and wet soil	poly(ethylene succinate) (PESu)	20 to several days	-	-	-	SEM, Enzyme production	Ishii et al., 2007
	<i>P. funiculosum</i>	Culture							
8	<i>A. niger</i>	Culture	PS: PLA (30%)	28 days	4.9	-	-	TGA, SEM, FTIR, XRD	Barkoula et al., 2008
			PS: PLA: OMM T (5%)						
9	<i>A. niger</i>	Culture	copolymers of lactic acid, terephthalic acid and ethylene glycol	60 days	-	W:65	Y:70	FTIR, SEM	Soni et al., 2009
	<i>A. versicolor</i>					59	62		
	<i>A. clavatus</i>					55	60		
	<i>A. fumigatus</i>					53	65		
	<i>A. alternata</i>					68	81		
	<i>Mucor sp.</i>					48	64		
	<i>Penicillium sp.</i>					45	68		
	<i>Rhizopus sp.</i>					51	55		
10	<i>A. niger</i>	Culture	EP	6 months	-	-	-	SEM, FTIR, Variation in Viscosity	Alariqi & Singh, 2010
11	<i>A. niger, P.</i>	Guangzho	POE-	28 days	-	-	-	SEM, tensile	Z. Yang et

	<i>pinophilum</i> A <i>C. globsum</i> , <i>G. virens</i> , <i>A.</i> <i>pullulans</i>	u Institute of Microbiol ogy	g- MAH					strength	al., 2010
12	<i>Aspergillus niger</i>	Culture	TPGS, TPS	45 days	-	-	-	TGA, SEM	Canché- Escamilla et al., 2011
13	<i>Fusarium sp.</i> , <i>Trichospo ron sp.</i>	Mangrove Sediments	Dimet hyl phthal ate (DMP , dimeth yl isopht baleto	24 days	-	-	-	Enzymatic assay	Luo et al., 2012
14	<i>Fusarium sp.</i>	garden soil and waste leachate	Polycar bonate e (PC)	15 days	-	-	-	Clear zone, AFM	Arefian et al., 2013
15	<i>Chaetomium sp.</i>	Agricultur al soil	Biode gradab le mulch (BDM) films	10 weeks	-	-	-	Clear zone formation, SEM	Bailes et al., 2013
16	<i>P. pulmonarius</i>	ATCC Chinese Universit y of Hong Kong Collection	DBP & DEP	7 days	-	-	-	Radial growth rate and biomass Differentiation zone of grown	Suarez- Segundo et al., 2013
	<i>P. ostreatus</i> (<i>Po 37</i> and <i>Po</i>	American Type Culture							
	<i>P. florida</i>	Universid ad Autonom a ´de							
	<i>F.oxysporum</i>	Soil of the suburbs, park							
	<i>M. alpina</i>								
17	<i>T. versicolor</i>	American Type Culture Collection	PAH	60 days	-	-	-	Enzyme activity	Lladó et al., 2013

	<i>L. tigrinus</i>	Central bureau voor Schimmeltcultures							
18	<i>Fusarium</i>	PC contaminated garden and waste leachate	PC	7 days	-	-	-	clear zone of amylase and lipase, and AFM	Arefian et al., 2013
	<i>Ulocladium</i>								
	<i>Chrysosporium</i>								
	<i>Penicillium</i>								
19	<i>C. guilliermondii</i> , <i>A. fumigatus</i>	Culture Collection of Basidiomycetes, Czech Republic	Polyesteramides (PEA)	6 weeks	-	-	-	Enzyme production (lipase and esterase)	Novotný et al., 2015
20	<i>M. elongata</i>	Compost	70 TPF	125 days	-	45.23	-	tensile strength	Vieyra et al., 2015
21	<i>Trametes versicolor</i>	National Collection of Biology Laboratory, University of Tehran, Iran	TPS, CNFs	2 months	-	-	-	SEM, DMA	Babaei et al., 2015
22	<i>P. antarctica</i> , <i>Paraphoma sp.</i>	Culture	PBSA (Bionolle #3020), PBS (Bionolle #1020) PBA	1- 4 hrs	-	-	-	LCMS	Sato et al., 2017
23	<i>C. byrsina</i>	Wonorejo Mangrove soil, Indonesia	Plastic	6 weeks	-	22.7	-	enzymatic degradation	Kuswiyatari et al., 2019

24	<i>A. flavus</i>	Municipal waste	Hexadecane	14 days	-	52.92±8.81	-	GCMS, SEM	M. Perera et al., 2019
25	<i>Clitocybe sp.</i>	Culture	polylactide	6 months	-	-	-	SEM-EDX	Janczak et al, 2020
	<i>L. laccata</i>								
26	<i>Aspergillus sp.</i> and <i>Penicillium sp.</i>	Culture	PBAT - thermoplastic	30 days	-	1.04 ± 0.080	-	SEM, FTIR	T. A. De Oliveira et al., 2020
27	<i>M. roreri</i>	Cacao pods	polyethylene succinate (PES)	21 days	-	59	-	Dry weight measurement, Titration assay, SEM	Vázquez-Alcántara et al., 2021
28	<i>P. sordida</i>	Culture	Bisphenol F (BPF)	14 days	-	-	-	Enzymatic degradation	Wang et al., 2021
29	<i>Fusarium culmorum</i> and <i>F. oxysporum</i>	Culture collection	DBP	7 days	-	-	-	Esterase Activity	González-Márquez et al., 2021
30	<i>M. roridum</i>	Culture	BPA	72 hrs	-	-	-	LC-MS/MS, Enzyme production	Jasińska et al., 2021
31	<i>A. flavus</i>	Field soil	compostable film microplastics (CFMPs)	12 months	-	-	-	ATR-FTIR	Pedrini, 2022
32	<i>Acremonium sp.</i>	Inside plastic fuel bottles	PAHs	30 days	-	-	-	UHPLC	Héctor et al, 2022
33	<i>A. flavus</i>	Sanitary landfill soil	DBP	15 days	-	-	-	GC-MS	Puranik et al., 2023
34	<i>P. lilacinum</i>	Farmland soil	biodegradable	30 days	-	15	-	SEM, FTIR, LCMS	Tseng et al., 2023
35	<i>Phanerochaete sp.</i>	Leaves of <i>Handroanthus impetiginosus</i>	BPA	7 days	-	-	-	SEM	Conceição et al., 2023

1888

1889