

Design of a measuring device for the implementation of a method for simultaneous determination of conductivity and diffusivity of building materials

by Jana Publication & Research

Submission date: 01-Nov-2025 07:50AM (UTC+0200)

Submission ID: 2769513695

File name: IJAR-54581.pdf (353.24K)

Word count: 1110

Character count: 5626

Design of a measuring device for the implementation of a method for simultaneous determination of conductivity and diffusivity of building materials

Summary

The thermo-physical characterization of building materials is essential to evaluate their energy performance. In developing countries such as Senegal, the measuring devices available on the market are often expensive and not easily accessible. This work presents the design and experimental validation of a lightweight and economical device allowing the simultaneous determination of the thermal conductivity (λ) and the thermal diffusivity (a) of building materials. The method is based on a simplified physical model integrating the transient and permanent regimes. The measurements carried out on reference materials such as plaster and extruded polystyrene allowed to obtain respectively: for plaster, $a = 2.9 \cdot 10^{-6} \text{ m}^2/\text{s}$ and $\lambda = 0.25 \text{ W/m} \cdot ^\circ\text{C}$, and for extruded polystyrene, $a = 6 \cdot 10^{-6} \text{ m}^2/\text{s}$ and $\lambda = 0.023 \text{ W/m} \cdot ^\circ\text{C}$. These results, consistent with the literature, validate the reliability of the proposed device.

Keywords: characterization, thermal conductivity, thermal diffusivity, plaster, extruded polystyrene, transient.


1. Introduction

Faced with the challenges of climate change and global warming, the energy performance of buildings constitutes a major challenge. In Africa, the energy consumption of buildings represents a significant part of the national bill. Improving energy efficiency requires the development of new building materials adapted to the local climate and offering good thermal insulation properties. The thermo-physical characterization of these materials is then essential to evaluate their ability to meet these requirements. The main methods for measuring thermo-physical properties are the hot plate method, the hot wire method, the hot plane method and the box method. The latter is known for its simplicity and the reliability of its results, but the available devices remain expensive. In this perspective, our study proposes the design of a more accessible measuring device allowing simultaneous determination of thermal conductivity and diffusivity. This device is intended to characterize both conventional materials and bio-sourced materials (laterite, typha, straw, etc.).

2. Methodology

2.1. Theoretical modeling

The thermal field of the studied material is governed by the heat conduction equation (Equation 1) with the appropriate boundary conditions.

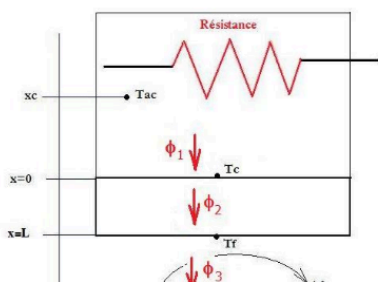

40

41

42

43

44

45

46

47

Figure 1: schematization of the model

48 The thermal field of this sample (**figure 1**) is governed by the equation [1] [7] [16] [17]

$$\frac{\partial^2 T(x,t)}{\partial x^2} = \frac{1}{a} \frac{\partial T(x,t)}{\partial t} \quad 1$$

49 With the boundary conditions:

50 - At the front face (x=0):

$$\lambda \frac{\partial T(x,t)}{\partial x} \Big|_{x=0} = RI^2 - C(T_{ac} - T_a) \quad 2$$

51 - At the rear face (x=L):

$$\lambda \frac{\partial T(x,t)}{\partial x} \Big|_{x=L} = hf(T_f - T_a) \quad 3$$

52 Where: $T_{ac}(t)$: ambient temperature on the high side depending on the parameter t .

53 T_f : temperature of the lower face

54 T_a : ambient temperature on the low side, constant.

55 R: heating resistor

56 I: current passing through the resistance

57 The resolution by the Duhamel method allows obtaining the evolution of temperature and
58 deducing the thermal diffusivity from the experimental slopes. The thermal conductivity
59 λ is then determined in the steady state, after stabilization of temperatures.

2.2. Experimental design

The device designed is a calorimetric box composed of insulating layers in polystyrene. Heating is provided by a film heater, generating a unidirectional flow of heat. The temperature sensors are positioned on both sides of the sample in order to follow the thermal evolution. The lateral insulators ensure minimization of heat losses. (Figures 1 and 3)

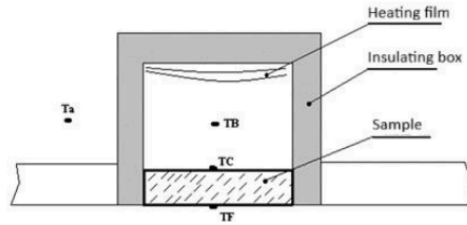


Figure 1: Experimental device



Figure 2: Photo of the experimental

3. Experimental results

3.1. Thermal conductivity

The experimental results are presented in the table below:

Table 1: Different conductivities obtained

Material	Voltage (V)	Speed time	Conductivity λ (W/m·K)
----------	-------------	------------	-----------------------------------

Plaster	220	3 h 30	0,2649
Plaster	220	3 h 00	0,2443
Plaster	200	2 h 30	0,2540

84 The average conductivity of plaster is $\lambda = 0.25 \text{ W/m K}$ with a relative
85 uncertainty estimated at 7%.

86 3.2. Thermal diffusivity

87 **Table 2: Different diffusivities obtained**

Material	Voltage (V)	Measurement time	Diffusivity a (m ² /s)
Plaster	220	1 h 40	$2,89 \times 10^{-7}$
Plaster	220	1 h 45	$3,00 \times 10^{-7}$
Plaster	200	55 min	$2,89 \times 10^{-7}$

88 The average diffusivity obtained is $a = 2.9 \cdot 10^{-7} \text{ m}^2/\text{s}$, with a relative uncertainty of 6%.

89 4. Discussion

90 The results obtained are in good agreement with the literature values for plaster and
91 extruded polystyrene. The designed device demonstrates its ability to faithfully reproduce
92 the thermo-physical properties of materials. However, to ensure the reliability of
93 measurements, the following precautions must be observed: use at least three
94 representative samples, condition the samples before testing, ensure good sensor-sample
95 contact. These recommendations will strengthen the accuracy of the device and allow its
96 extension to the characterization of local bio-sourced materials (typha, straw, laterite).

97 5. Conclusion

98 The device developed allows the ¹simultaneous determination of the thermal conductivity
99 and diffusivity of building materials. Lightweight, economical and reproducible, it is a
100 credible alternative to expensive commercial devices. The results obtained with plaster
101 and extruded polystyrene confirm the validity of the model and the device. Future
102 perspectives include its application to the characterization of local bio-sourced materials
103 for sustainable construction in Senegal.

104 Bibliographic references

- 105 [1] M. Thiam and al., Data processing software for calculating the thermal conductivity
106 of building materials by application of the box method, J. Sci. Eng. Res., Vol. 10,
107 Issue 2, 2023.
108 [2] A. Diop and al., Improving the stability of the inflatable soil of Diamniadio by using
109 Typha Australis, J. Build. Constr. Plan. Res., Vol. 8, pp. 273–284, 2020.

- 110 [3] A. Diop and al., Thermal characterization of dry soil/Typha Australis materials for
111 improving the energy performance of buildings, J. Sci. Eng. Res., Vol. 7, Issue 12,
112 2020.
- 113 [4] A. S. Diaw and al., Thermophysical characterization of Typha concrete with a view to
114 its integration into construction, JBCPR, 2021.
- 115 [5] Y. Jannot & A. Degiovanni, Measurement of thermal properties of materials, ISTE
116 Editions, 2018.
- 117 [6] N. Ozisik, Heat Conduction, Wiley-Interscience, 1980.

UNDER PEER REVIEW IN IJAR

Design of a measuring device for the implementation of a method for simultaneous determination of conductivity and diffusivity of building materials

ORIGINALITY REPORT

7%	4%	3%	0%
SIMILARITY INDEX	INTERNET SOURCES	PUBLICATIONS	STUDENT PAPERS

PRIMARY SOURCES

1	Gobbe, C.. "Hot strip method: application to thermal characterisation of orthotropic media", International Journal of Thermal Sciences, 200410 Publication	3%
2	jsaer.com Internet Source	3%
3	ia803106.us.archive.org Internet Source	1%

Exclude quotes	On	Exclude matches	Off
Exclude bibliography	On		