

Jana Publication & Research

IMPACT OF COW DUNG ADDITION ON THE THERMAL AND MECHANICAL PROPERTIES OF NĀ DJAMENA CLAY

 VRC38

 BioTech

 Institut Seni Indonesia Surakarta

Document Details

Submission ID

trn:oid:::1:3422913318

Submission Date

Nov 24, 2025, 2:03 PM GMT+7

Download Date

Nov 24, 2025, 4:24 PM GMT+7

File Name

IJAR-54927.pdf

File Size

1.1 MB

8 Pages

1,597 Words

8,715 Characters

8% Overall Similarity

The combined total of all matches, including overlapping sources, for each database.

Filtered from the Report

- Bibliography
- Quoted Text

Match Groups

-  **12 Not Cited or Quoted 8%**
Matches with neither in-text citation nor quotation marks
-  **1 Missing Quotations 1%**
Matches that are still very similar to source material
-  **0 Missing Citation 0%**
Matches that have quotation marks, but no in-text citation
-  **0 Cited and Quoted 0%**
Matches with in-text citation present, but no quotation marks

Top Sources

- 4%  Internet sources
- 7%  Publications
- 1%  Submitted works (Student Papers)

Match Groups

- 12 Not Cited or Quoted 8%**
Matches with neither in-text citation nor quotation marks
- 1 Missing Quotations 1%**
Matches that are still very similar to source material
- 0 Missing Citation 0%**
Matches that have quotation marks, but no in-text citation
- 0 Cited and Quoted 0%**
Matches with in-text citation present, but no quotation marks

Top Sources

- 4% Internet sources
- 7% Publications
- 1% Submitted works (Student Papers)

Top Sources

The sources with the highest number of matches within the submission. Overlapping sources will not be displayed.

1	Internet	repository.ub.ac.id	2%
2	Publication	Yves Jannot, Alain Degiovanni. "Thermal Properties Measurement of Materials", ...	1%
3	Publication	Driss Taoukil, Abdelmajid El bouardi, Taib Ajzoul, Hassan Ezbakhe. "Effect of the i...	1%
4	Publication	Brahim Mazhoud, Florence Collet, Sylvie Prétot, Christophe Lanos. "Effect of hem...	<1%
5	Internet	open.metu.edu.tr	<1%
6	Publication	G. Suber, M. Bertolotti, C. Sibilis, A. Ferrari, F. Genel Ricciardiello. "Transverse pho...	<1%
7	Publication	Heping Tan, Xinlin Xia, Liming Ruan, Linhua Liu, Qizheng Yu. "Temperature respo...	<1%
8	Internet	www.scirp.org	<1%
9	Publication	Abderahman Adoum Oumar, Malloum Soultan, Abdallah Dadi, Togdjim Jonas et a...	<1%
10	Publication	Colbert Babé, Dieudonné Kaoga Kidmo, Ahmat Tom, Rachel Raïssa Ngono Mvond...	<1%

IMPACT OF COW DUNG ADDITION ON THE THERMAL AND MECHANICAL PROPERTIES OF N'DJAMENA CLAY.

Manuscript Info

Manuscript History

Received: xxxxxxxxxxxxxxxx

Final Accepted: xxxxxxxxxxxxxxxx

Published: xxxxxxxxxxxxxxxx

Key words:-

Cow dung, Raw earth bricks, Thermal conductivity, Thermal diffusivity, Compressive strength, Bio-based stabilizer, optimization.

Abstract

This study investigates the effect of incorporating cow dung (1–10 wt%) into locally sourced clay from N'Djamena, with the objective of improving the thermal and mechanical performance of raw earth bricks used in social housing. Thermal conductivity was measured using the hot plate method, thermal diffusivity using the flash method (Degiovanni, 1987; Degiovanni, 1993), and compressive strength through standard mechanical testing. Results show a reduction of thermal conductivity from 0.99 to 0.42 W·m⁻¹·K⁻¹ at 10% cow dung, as well as a significant decrease in thermal diffusivity. Compressive strength increases with cow dung content, reaching 8.2 MPa at 10%. This optimal thermomechanical behaviour aligns with earlier reports on organic stabilisation in earthen materials (Gaye, 1998; Sow, 2014).

Copy Right, IJAR, 2019,. All rights reserved.

Introduction:

Earthen materials remain central to housing in the Sahel, particularly in Chad where raw clay ("banco") is widely used. However, raw earth bricks often display limited mechanical resistance and inadequate thermal insulation, as confirmed in previous research on thermophysical characterisation of local soils (Charfadine, 2002; Ball, 2011). Traditional additions such as cow dung have been used historically to improve material behaviour (Sow, 2014). Previous studies on plant-fiber and organic additives indicate improvements in strength and thermal properties (Gaye, 1998; Voumbo et al., 2008). This study experimentally assesses the influence of cow dung on thermal conductivity (λ), thermal diffusivity (α) and compressive strength (R_c) to determine an optimal stabiliser percentage.

2. Materials and Methods

2.1 Materials

- Clay extracted from the Madagua site,
- Fresh, non-fermented cow dung,
- Addition rates: 1%, 3%, 5%, 10% by mass.

Specimens: thermal plates (10 × 10 × 2–3 cm) and mechanical test cubes (5 × 5 × 5 cm).

2.2 Thermal Methods

a) Thermal conductivity — Hot plate method

The hot-plate experimental arrangement follows established configurations for earthen materials (Charfadine, 2002; Thiam, 2011). The setup comprises two aluminium plates, a polystyrene insulator, three thermocouples (T_0 , T_1 , T_2) and a heating film supplying a heat flux Φ (schematic in Figure 1). The direction of heat flux is illustrated in Figure 2.

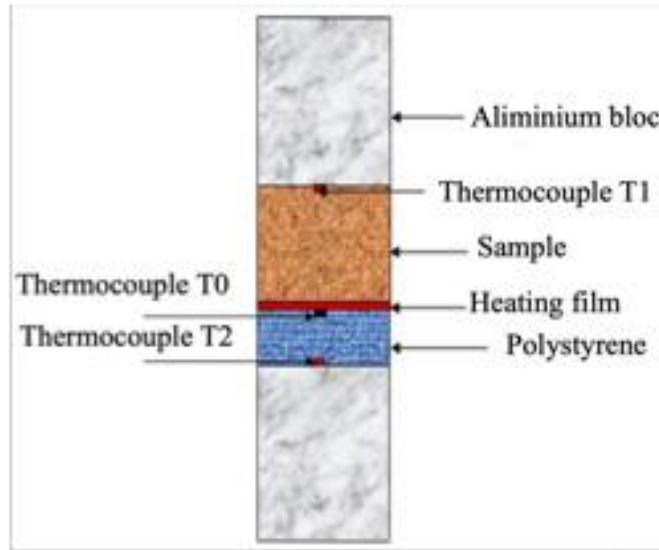


Figure 1. Schematic of the hot-plate experimental setup: aluminium plates, polystyrene insulator, thermocouples T_0 , T_1 , T_2 , and heating film.

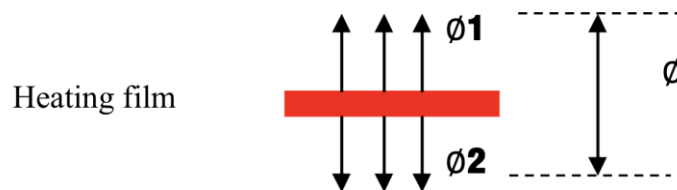


Figure 2. Direction of heat flux in the hot-plate configuration (schematic)

Thermal conductivity λ is derived from:

$$\lambda = \frac{e_1}{T_0 - T_1} \left[\frac{U^2}{R_s} - \frac{\lambda_2}{e_2} (T_0 - T_2) \right] \quad (1)$$

Where:

- U is applied voltage,
- R_s the film resistance,
- e_1 and e_2 the relevant thicknesses,
- and λ_2 the conductivity of the aluminium plate.

b) Thermal diffusivity — Flash method

Thermal diffusivity measurements used the flash method with rear-face temperature recording. The experimental arrangement is shown in Figures 3 and 4, while a representative rear-face thermogram is shown in Figure 5. Data were analysed according to the Degiovanni model (Degiovanni, 1987; Degiovanni, 1993), producing:

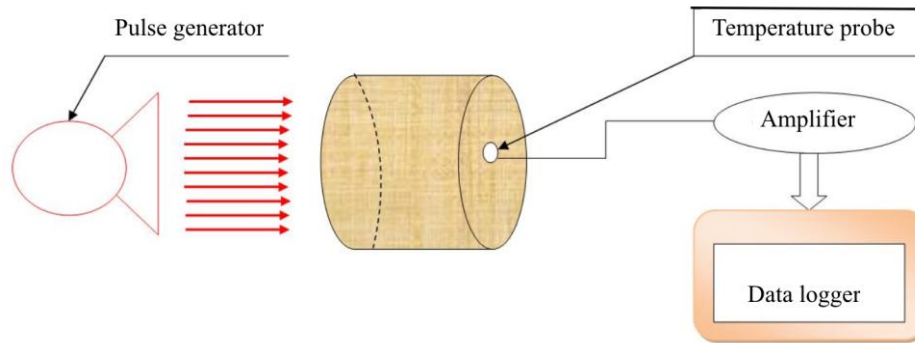


Figure 3. Flash method — experimental arrangement (front irradiation, rear-face temperature acquisition).

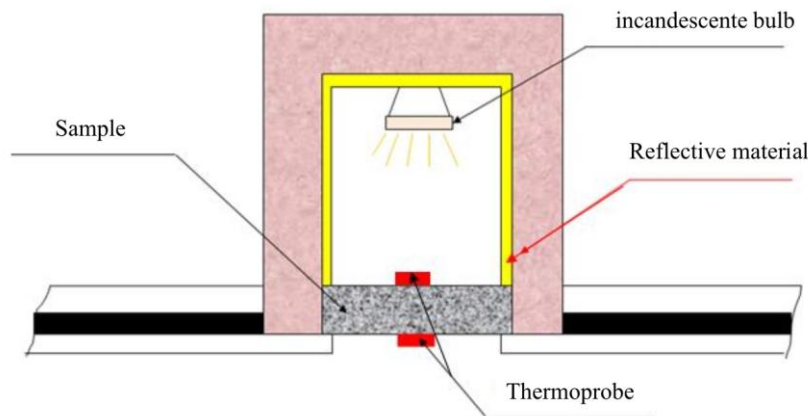


Figure 4: Cross-sectional view of the box method for measuring thermal diffusivity

The thermogram of the non-irradiated face of the specimen (Figure 5) allows the determination of thermal diffusivity α using the Degiovanni model based on Equation (2).

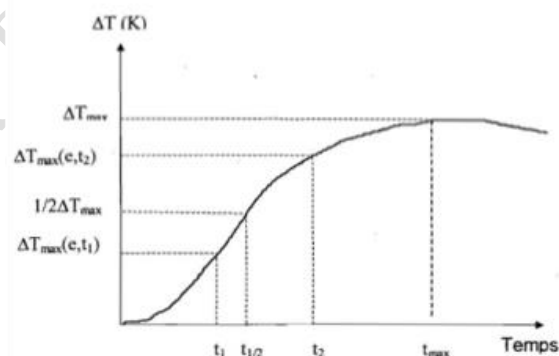


Figure 5. Representative rear-face thermogram from the flash test and definition of $t_{1/3}$, $t_{2/3}$, $t_{5/6}$ times used in the Degiovanni model.

$$\alpha = \frac{\alpha_1 + \alpha_2 + \alpha_3}{3} \quad (2)$$

Where:

$$\alpha_1 = \frac{e^2}{t_{5/6}^2} \left[1,15t_{5/6} - 1,25t_{2/3} \right] \quad (3)$$

$$\alpha_2 = \frac{e^2}{t_{5/6}^2} \left[0,761t_{\frac{5}{6}} - 0,926t_{1/3} \right] \quad (4)$$

$$\alpha_3 = \frac{e^2}{t_{5/6}^2} \left[0,617t_{\frac{5}{6}} - 0,862t_{2/3} \right] \quad (5)$$

3 Mechanical Methods

Compression tests were carried out on a hydraulic press following standard procedures (Dupain et al., 2000; Derriche&Kebaili, 1998). Test setup and specimen loading are shown in Figure 6.

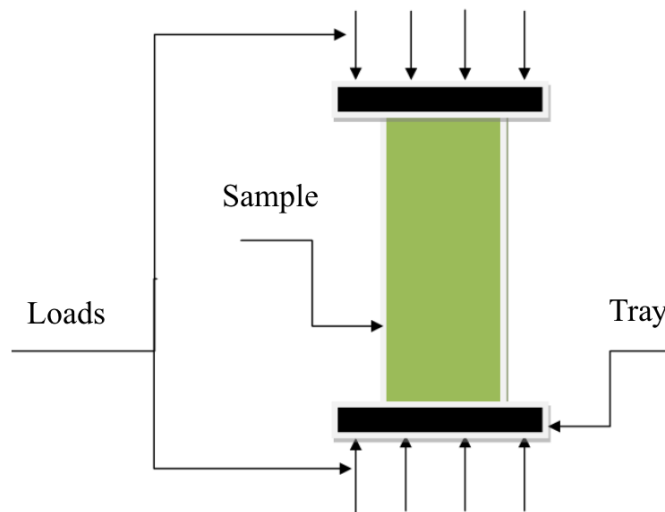


Figure 6. Mechanical test setup: hydraulic press and specimen instrumentation.

Compressive strength is:

$$R_c = \frac{F}{S} \quad (6)$$

Where:

- F is the maximum load
- and S the cross-sectional area.

3. Results

3.1 Thermal conductivity

Thermal conductivity progressively decreases with cow dung content and reaches $0.42 \text{ W} \cdot \text{m}^{-1} \cdot \text{K}^{-1}$ at 10% addition. The conductivity data are plotted in Figure 7. The reduction is attributed to the increased volume fraction of air (low conductivity) in the composite's pore network (Meukam et al., 2004; Voumbo et al., 2008).

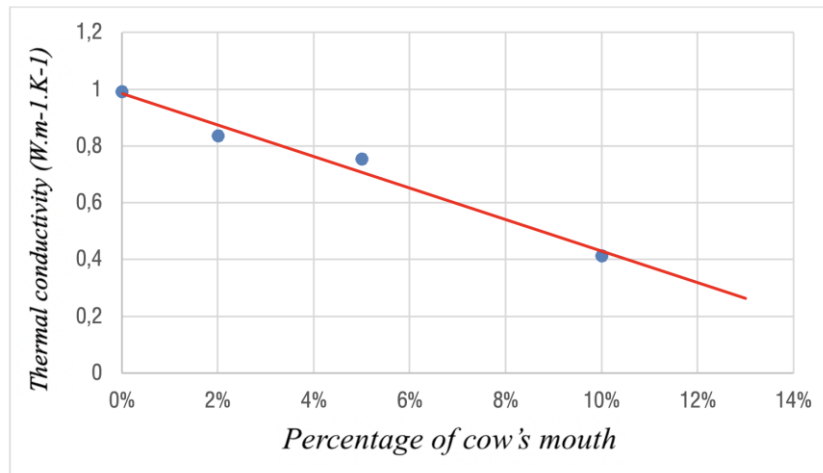


Figure 7. Thermal conductivity λ ($\text{W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$) as a function of cow dung content.

3.3 Thermal diffusivity

Measured thermal diffusivity decreases with increasing cow dung and is shown in Figure 8. The flash thermograms and corresponding fits (Degiovanni model) for representative specimens are given in Figure 5. Reduced diffusivity confirms a slower thermal response of the bio-modified matrix (Degiovanni, 1987; Maillet et al., 1993).

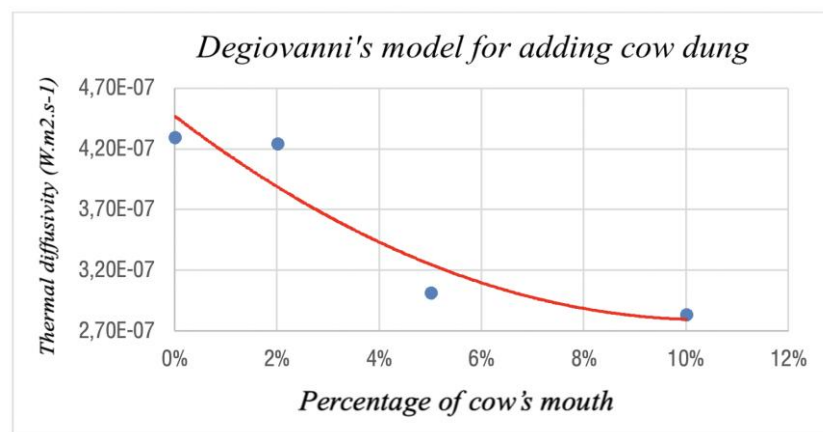


Figure 8. Thermal diffusivity α ($\text{m}^2\cdot\text{s}^{-1}$) as a function of cow dung content.

3.4 Mechanical strength

Compressive strength increases with cow dung content, reaching 8.2 MPa at 10% (Figure 11). The stress-strain curves for representative specimens are provided in Figure 9. The observed mechanical gain is consistent with binding effects of organic constituents previously reported (Gaye, 1998; Dadi et al., 2015).

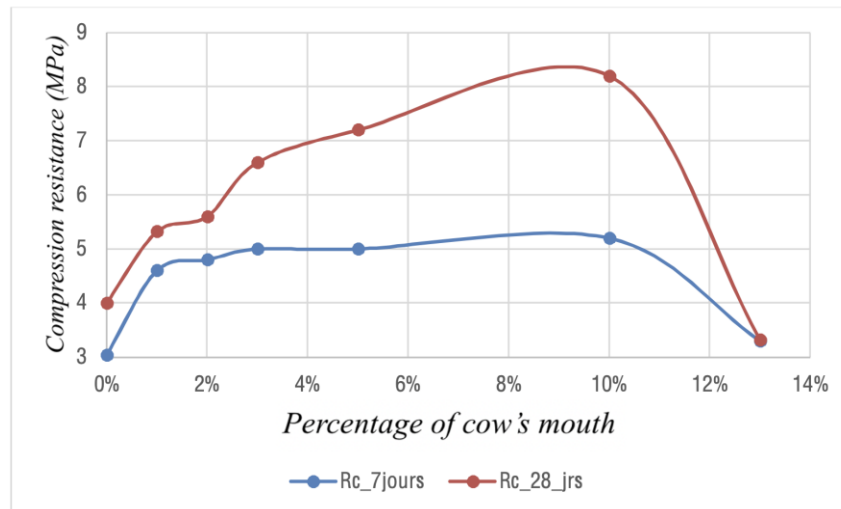


Figure 9. Compressive strength Rc (MPa) as a function of cow dung content

3.5 Thermomechanical optimum

Figure 10 overlays compressive strength and thermal conductivity as functions of cow dung content and demonstrates that 10% provides the optimal compromise: minimized λ and α together with maximized Rc.

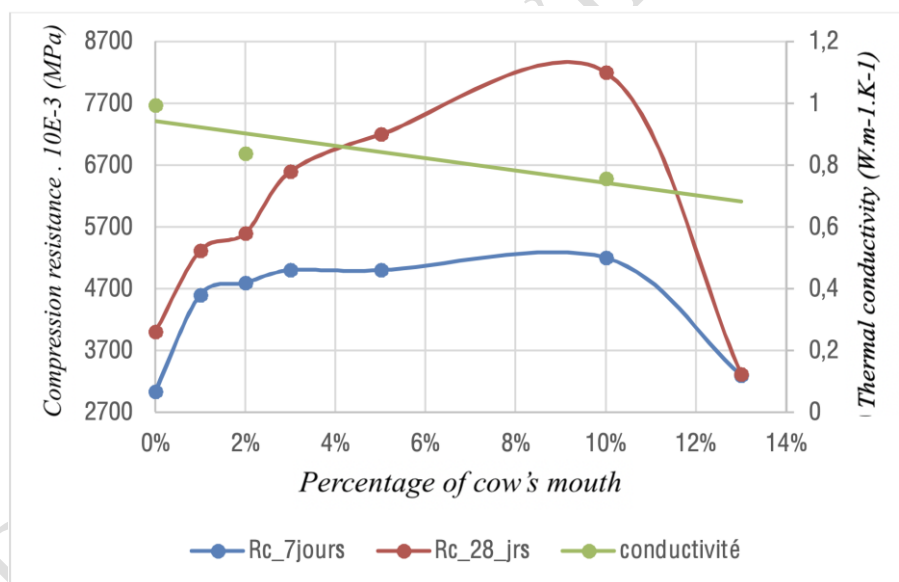


Figure 10. Combined plot: λ and Rc versus cow dung content (thermomechanical optimum illustration).

4. Discussions

4.1 Thermal effects

Cow dung's fibrous and organic composition introduces microcavities that trap air and lower effective thermal conductivity and diffusivity, as discussed in studies on porous bio-materials (Maillet et al., 1993; Sarr, 2008).

4.2 Mechanical effects

Organic constituents act as natural binders, enhancing interparticle cohesion and improving compressive behaviour. Similar mechanisms were described by Sow (2014) and Dadi (2016) for straw/clay and dung/clay composites.

4.3 Thermomechanical synergy

The dual effect—improved cohesion plus increased effective porosity—explains the thermomechanical optimum at 10%, consistent with field-oriented experimental literature on stabilised earth bricks (Meukam et al., 2004; Gaye, 1998).

5. Conclusion

Incorporating cow dung into N'Djamena clay significantly improves thermophysical and mechanical properties of raw earth bricks. A 10% mass fraction is recommended as the optimal stabiliser content for achieving a favourable balance between thermal resistance and mechanical strength. The approach supports low-cost, locally-sourced, and sustainable construction in Sahelian climates.

References

- Bah, A.B.B. (1996). *Caractérisation de matériaux par phénomènes thermiques transitoires*. UCAD.
- Ball, H.M. (2011). *Modélisation et mesures des propriétés thermiques d'un milieu poreux humide : brique de latérite avec la gousse de mil*. Thèse, ESP-UCAD.
- Charfadine, A. (2002). *Caractérisation thermophysique de matériaux locaux de construction au Tchad*. Thèse, Université Claude Bernard Lyon 1.
- Dadi, A.M. (2016). *Étude comparative des caractéristiques mécaniques et thermophysiques de matériaux locaux de construction utilisés dans l'habitat social au Tchad*. Thèse, ED2DS, Thiès.
- Dadi, A.M. et al. (2015). "Effect of cow's dung on thermophysical characteristics of building materials based on clay." *RJASET*.
- Degiovanni, A. (1987). "Diffusivité et méthode Flash." *Revue Générale de Thermique*, n°185.
- Degiovanni, A. (1993). "Les erreurs sur la diffusivité thermique mesurées par méthode flash. Confrontation théorie-expérience." *J. Phys. III France*, 1993, Vol. 3, pp. 883–909.
- Derriche, Z. & Kebaïli, M. (1998). *Prévision du gonflement des argiles d'In-Amenas*. BLPC.
- Dupain, R., Lanchou, R. & Saint-Arronoman, J.C. (2000). *Caractérisation des matériaux de génie civil par les essais de laboratoire*. Casteilla.
- Gaye, S. (1998). *Contribution à l'étude du confort thermique en climat tropical humide*. Thèse de Docteur Ingénieur, UCAD de Dakar.
- Meukam, P., Jannot, Y., Noumane, A. & Kofane, T.C. (2004). "Thermophysical characteristics of economical building materials." *Construction and Building Materials*, 18, pp. 437–443.
- Maillet, D., Sandre, X. & Degiovanni, A. (1993). "Les erreurs sur la diffusivité thermique mesurées par méthode flash." *J. Phys. III France*, Vol. 3, pp. 883–909.
- Meukam, P. (2004). *Valorisation des briques des terres stabilisées en vue de l'isolation thermique de bâtiments*. Thèse, Univ. Cergy-Pontoise & Univ. Yaoundé 1.
- Sarr, C.T. (2008). *Détermination des paramètres thermophysiques des isolants cylindriques : application au kapok*. Thèse, UCAD.
- Sow, D. (2014). *Caractérisation thermomécanique des mélanges de paille de riz et de matériaux à base d'argile...* Thèse, ESP-UCAD.
- Voumbo, M.L., Wereme, A., Tamba, S., Gaye, S., Adj. M. & Sissoko, G. (2008). "Caractérisation des propriétés thermophysiques du kapok." *Journal des Sciences*, N°1, pp. 33–43.

- 145 Azibert, O.A. et al. (2015). "Improvement of the thermal conductivity of a composite material has clay base." *Res. J.*
146 *Appl. Sci. Eng. Technol.*, 11(9), pp. 962–968.

UNDER PEER REVIEW IN IJAR